

## Australian/New Zealand Standard

---

### **Metallic flanges**

---

#### **Part 1: Steel flanges**

---

Global Supply Line Pty Ltd  
Major stockist of valves to AS/ISO/API/ASME standards.  
Contact us: [sales@globalsupplyline.com.au](mailto:sales@globalsupplyline.com.au)

Full stock list at our website [www.globalsupplyline.com.au](http://www.globalsupplyline.com.au)

This Joint Australian/New Zealand Standard was prepared by Joint Technical Committee ME/1, Pressure Equipment. It was approved on behalf of the Council of Standards Australia on 19 July 1995 and on behalf of the council of Standards New Zealand on 24 October 1995. It was published on 5 December 1995.

---

The following interests are represented on Committee ME/1:

A.C.T. Occupational Health and Safety Office  
Aluminium Development Council, Australia  
Australian Chamber of Commerce and Industry  
Australian Institute of Energy  
Australian Institute of Petroleum  
Australian Institute of Pressure Equipment Engineers  
Australian Liquefied Petroleum Gas Association  
Boiler and Pressure Vessel Manufacturers Association of Australia  
Bureau of Steel Manufacturers of Australia  
Department for Industrial Affairs, S.A.  
Department of Employment, Vocational Education, Training and Industrial Relations, Qld.  
Department of Labour, New Zealand  
Department of Occupational Health, Safety and Welfare, W.A.  
Electricity Corporation of New Zealand  
Electricity Supply Association of Australia  
Heavy Engineering Research Association, New Zealand  
Institute of Metals and Materials, Australasia  
Institution of Engineers, Australia  
Insurance Council of Australia  
Metal Trades Industry Association of Australia  
National Association of Testing Authorities, Australia  
New Zealand Engineering Federation  
New Zealand Petrochemical Users Group  
New Zealand Timber Industry Federation  
Occupational Health and Safety Authority, Vic.  
Tasmania Development and Resources  
Welding Technology Institute of Australia  
WorkCover Authority, N.S.W.  
Work Health Authority, N.T.

---

**Review of Standards.** To keep abreast of progress in industry, Joint Australian/New Zealand Standards are subject to periodic review and are kept up to date by the issue of amendments or new editions as necessary. It is important therefore that Standards users ensure that they are in possession of the latest edition, and any amendments thereto.

Full details of all Joint Standards and related publications will be found in the Standards Australia and Standards New Zealand Catalogue of Publications; this information is supplemented each month by the magazines 'The Australian Standard' and 'Standards New Zealand', which subscribing members receive, and which give details of new publications, new editions and amendments, and of withdrawn Standards.

Suggestions for improvements to Joint Standards, addressed to the head office of either Standards Australia or Standards New Zealand, are welcomed. Notification of any inaccuracy or ambiguity found in a Joint Australian/New Zealand Standard should be made without delay in order that the matter may be investigated and appropriate action taken.

---

# Australian/New Zealand Standard

---

## Metallic flanges

---

### Part 1: Steel flanges

---

PUBLISHED JOINTLY BY:

STANDARDS AUSTRALIA  
1 The Crescent,  
Homebush NSW 2140 Australia

STANDARDS NEW ZEALAND  
Level 10, Standards House,  
155 The Terrace,  
Wellington 6001 New Zealand

ISBN 0 7337 0007 1

## PREFACE

This Standard was prepared by the Joint Standards Australia/Standards New Zealand Committee ME/1 on Pressure Equipment. It is identical with and has been reproduced from ISO 7005-1:1992, *Metallic flanges*, Part 1: *Steel flanges*.

The objective of this Standard is to provide designers, manufacturers and users with an international Standard for flanges for use in pressure applications.

This Joint Standard is one of the following series that applies to metallic flanges.

### AS/NZS

- 4331 Metallic flanges
- 4331.1 Part 1: Steel flanges
- 4331.2 Part 2: Cast iron flanges
- 4331.3 Part 3: Copper alloy and composite flanges

Under arrangements made between Standards Australia, Standards New Zealand and ISO, users of this Standard are advised that in Australia copyright is vested in Standards Australia and in New Zealand copyright is vested in Standards New Zealand.

It is not intended this Standard be a mandatory replacement for any flange Standards already in use in Australia or New Zealand. Before flanges to this Standard are used with flanges of other Standards, compatibility for bolting, strength, gasket seating and the like should be checked.

Statements expressed in mandatory terms in notes to text, tables and figures are deemed to be requirements of this Standard.

The terms ‘normative’ and ‘informative’ have been used in this Standard to define the application of the annex to which they apply. A ‘normative’ annex is an integral part of a Standard, whereas an ‘informative’ annex is only for information and guidance.

As this Standard is reproduced from an international Standard, the following applies:

- (a) Its number appears on the cover and title page while the International Standard number appears only on the cover.
- (b) In the source text, ‘this International Standard’ should read ‘this Australia/New Zealand Standard’.
- (c) A full point substitutes for a comma when referring to a decimal marker.

References to international Standards should be replaced by equivalent Australian Standards, as follows:

<i>Reference to International Standard</i>		<i>Australian Standard</i>	
<i>ISO</i>		<i>AS</i>	
7	Pipe threads where pressure-tight joints are made on the threads	1722	Pipe threads of Whitworth form
7-1:1982	Part 1: Designation, dimensions and tolerances	1722.1	Part 1: Sealing pipe threads
7-2:1982	Part 2: Verification by means of limit gauges	1722.1	Part 1: Sealing pipe threads
261:1973	ISO general purpose metric screw threads—General plan	1721	General purpose metric screw threads
887*	Plain washers for metric bolts, screws and nuts for general purposes—General plan	—	

---

\* To be published (Revision of ISO 887:1983).

	AS
ISO 6708:1980	—
Pipe components— Definition of nominal size	—
7268:1983	—
Pipe components— Definition of nominal pressure	—
7483:1991	—
Dimensions of gaskets for use with flanges to ISO 7005	—
ANSI/ASME	—
B1.20.1:1983	—
Pipe threads, general purpose (inch)	—

Equivalent National Material Standards may be substituted for those specified in this Standard.

© Copyright – STANDARDS AUSTRALIA/STANDARDS NEW ZEALAND

Users of Standards are reminded that copyright subsists in all Standards Australia and Standards New Zealand publications and software. Except where the Copyright Act allows and except where provided for below no publications or software produced by Standards Australia or Standards New Zealand may be reproduced, stored in a retrieval system in any form or transmitted by any means without prior permission in writing from Standards Australia or Standards New Zealand. Permission may be conditional on an appropriate royalty payment. Australian requests for permission and information on commercial software royalties should be directed to the head office of Standards Australia. New Zealand requests should be directed to Standards New Zealand.

Up to 10 percent of the technical content pages of a Standard may be copied for use exclusively in-house by purchasers of the Standard without payment of a royalty or advice to Standards Australia or Standards New Zealand.

Inclusion of copyright material in computer software programs is also permitted without royalty payment provided such programs are used exclusively in-house by the creators of the programs.

Care should be taken to ensure that material used is from the current edition of the Standard and that it is updated whenever the Standard is amended or revised. The number and date of the Standard should therefore be clearly identified.

The use of material in print form or in computer software programs to be used commercially, with or without payment, or in commercial contracts is subject to the payment of a royalty. This policy may be varied by Standards Australia or Standards New Zealand at any time.

**CONTENTS**

	<i>Page</i>
<b>Section 1: General .....</b>	1
<b>1.1 Scope .....</b>	1
<b>1.2 Normative references .....</b>	1
<b>1.3 Definitions .....</b>	2
<b>1.4 Designation of types, components and facings .....</b>	2
<b>Section 2: General requirements .....</b>	3
<b>2.1 Pressure/temperature ratings .....</b>	3
<b>2.2 Materials and bolting .....</b>	3
<b>2.3 Repairs .....</b>	3
<b>2.4 Dimensions .....</b>	3
<b>2.5 Facings .....</b>	4
<b>2.6 Spot-facing or back-facing .....</b>	5
<b>2.7 Tolerances .....</b>	5
<b>2.8 Marking .....</b>	5
<b>2.9 Inspection and test .....</b>	6
<b>2.10 Information to be supplied by the purchaser .....</b>	6
<b>Section 3: Dimensions .....</b>	11
<b>Section 4: Tolerances .....</b>	47

<b>Annexes</b>	<b>Page</b>
<b>A</b> Bevel for specified wall thicknesses from 5 mm to 22 mm inclusive and greater than 22 mm . . . . .	49
<b>B</b> Acceptable bevel designs for unequal wall thicknesses (pipeline applications) . . . . .	50
<b>C</b> Recommended bevel for equal wall thicknesses $t$ the end of the flange hub from 5 mm to 22 mm inclusive and greater than 22 mm (pipeline applications) . . . . .	51
<b>D</b> Guidance on flange materials . . . . .	52
<b>E</b> Guidance on pressure/temperature ratings . . . . .	62
<b>F</b> Design criteria (pipeline applications) . . . . .	78
<b>G</b> Bibliography . . . . .	79
 <b>Tables</b>	
<b>1</b> Surface finish for facings types A, B and E/F (large) . . . . .	5
<b>2</b> Surface finish values for facings types C/D, E/F (small), G/H and J . . . . .	5
<b>3</b> Synoptic table . . . . .	11
<b>4</b> Dimensions of flange facings for PN 2,5, PN 6, PN 10, PN 16, PN 25 and PN 40	15
<b>5</b> Dimensions of flange facings up to nominal size DN 900 for PN 20, PN 50, PN 110, PN 150, PN 260 and PN 420 . . . . .	17
<b>6</b> Dimensions of flange facings for nominal sizes DN 950 to DN 1 500 for PN 20, PN 50, PN 110 and PN 150 . . . . .	17
<b>7</b> Dimensions of ring-joint facings . . . . .	19
<b>8</b> Dimensions of PN 2,5 flanges . . . . .	23
<b>9</b> Dimensions of PN 6 flanges . . . . .	25
<b>10</b> Dimensions of PN 10 flanges . . . . .	27
<b>11</b> Dimensions of PN 16 flanges . . . . .	29
<b>12</b> Dimensions of PN 20 flanges . . . . .	31
<b>13</b> Dimensions of PN 25 flanges . . . . .	33
<b>14</b> Dimensions of PN 40 flanges . . . . .	35
<b>15</b> Dimensions of PN 50 flanges . . . . .	37
<b>16</b> Dimensions of PN 110 flanges . . . . .	39
<b>17</b> Dimensions of PN 150 flanges . . . . .	41
<b>18</b> Dimensions of PN 260 flanges . . . . .	43
<b>19</b> Dimensions of PN 420 flanges . . . . .	45
<b>20</b> Tolerances . . . . .	47
<b>21</b> Minimum hub radius after back-facing . . . . .	48

	<i>Page</i>
<b>D.1</b> Basic properties and reference standards for materials used for PN 2,5, PN 6, PN 10, PN 16, PN 25 and PN 40 flanges .....	53
<b>D.2</b> Reference standards for materials used for PN 20, PN 50, PN 110, PN 150, PN 260 and PN 420 flanges .....	57
<b>D.3</b> Materials applicable to tables 12, 15, 16 and 17 covering PN 20, PN 50, PN 110 and PN 150 flanges types 05 and 11 in the size range DN 300 and larger for pipeline applications .....	60
<b>E.1</b> Pressure/temperature (P/T) ratings for flanges made using material groups 1E0 to 6E0 .....	63
<b>E.2</b> Pressure/temperature (P/T) ratings for flanges made using material groups 7E0 to 9E0 .....	64
<b>E.3</b> Pressure/temperature (P/T) ratings for flanges made using austenitic stainless steels (based on 0,2% proof stress), material groups 10E0 to 15E0 .....	65
<b>E.4</b> Pressure/temperature (P/T) ratings for flanges made using austenitic stainless steels (based on 1% proof stress), material groups 10E0 to 15E0 .....	66
<b>E.5</b> Pressure/temperature (P/T) ratings for flanges made using group 1A1 materials .....	67
<b>E.6</b> Pressure/temperature (P/T) ratings for flanges made using group 1A2 materials .....	67
<b>E.7</b> Pressure/temperature (P/T) ratings for flanges made using group 1A3 materials .....	68
<b>E.8</b> Pressure/temperature (P/T) ratings for flanges made using group 1A4 materials .....	68
<b>E.9</b> Pressure/temperature (P/T) ratings for flanges made using group 1A5 materials .....	69
<b>E.10</b> Pressure/temperature (P/T) ratings for flanges made using group 1A7 materials .....	69
<b>E.11</b> Pressure/temperature (P/T) ratings for flanges made using group 1A9 materials .....	70
<b>E.12</b> Pressure/temperature (P/T) ratings for flanges made using group 1A10 materials .....	70
<b>E.13</b> Pressure/temperature (P/T) ratings for flanges made using group 1A13 materials .....	71
<b>E.14</b> Pressure/temperature (P/T) ratings for flanges made using group 1A14 materials .....	71
<b>E.15</b> Pressure/temperature (P/T) ratings for flanges made using group 2A1 materials .....	72
<b>E.16</b> Pressure/temperature (P/T) ratings for flanges made using group 2A2 materials .....	73
<b>E.17</b> Pressure/temperature (P/T) ratings for flanges made using group 2A3 materials .....	73
<b>E.18</b> Pressure/temperature (P/T) ratings for flanges made using group 2A4 materials .....	74
<b>E.19</b> Pressure/temperature (P/T) ratings for flanges made using group 2A5 materials .....	75

<b>E.20</b> Pressure/temperature (P/T) ratings for flanges made using group 2A6 materials .....	76
<b>E.21</b> Pressure/temperature (P/T) ratings for flanges made using group 2A7 materials .....	77
<b>E.22</b> Pressure/temperature (P/T) ratings for pipeline flanges .....	77

**Figures**

1 Flanges — Types 01 to 05 .....	7
2 Flanges — Types 11 to 15 .....	8
3 Flange — Type 21 .....	9
4 Ancillary components for flanges — Types 32 to 34 .....	9
5 Illustration of flange facings (types A to J) .....	10
6 PN 2,5, PN 6, PN 10, PN 16, PN 25 and PN 40 flange facing dimensions .....	14
7 PN 20, PN 50, PN 110, PN 150, PN 260 and PN 420 flange facing dimensions .....	16
8 Minimum hub radius after back-facing .....	48
A.1 Bevel for specified wall thicknesses $t$ .....	49
B.1 Acceptable bevel designs for unequal wall thicknesses .....	50
C.1 Recommended bevel for equal wall thicknesses $t$ at the end of the flange hub ..	51

# AUSTRALIAN/NEW ZEALAND STANDARD

## Metallic flanges —

### Part 1: Steel flanges

#### Section 1: General

##### 1.1 Scope

This part of ISO 7005 for a single system of flanges specifies requirements for circular steel flanges in the following PN designations:

Series 1 <sup>1)</sup>	Series 2 <sup>1)</sup>
PN 10	PN 2,5
PN 16	PN 6
PN 20	PN 25
PN 50	PN 40
PN 110	
PN 150	
PN 260	
PN 420	

It specifies the types of steel flanges and their facings, dimensions, tolerances, threading, bolt sizes, flange face surface finish, marking, testing and inspection.

It does not specify pressure/temperature ratings or materials for steel flanges. However, annex D gives guidance on selected materials and annex E gives guidance on the pressure/temperature ratings for some flanges made from the materials listed in annex D.

This part of ISO 7005 does not apply to flanges made from bar stock by turning.

Nor does it apply to flanges of types 11, 12, 13, 14 and 15 made from plate material.

The various gasket types, dimensions, design characteristics and materials used are not within the scope of this part of ISO 7005.

NOTE — Dimensions of gaskets are given in ISO 7483.

##### 1.2 Normative references

The following standards contain provisions which, through reference in this text, constitute provisions of this part of ISO 7005. At the time of publication, the editions indicated were valid. All standards are subject to revision, and parties to agreements based on this part of ISO 7005 are encouraged to investigate the possibility of applying the most recent editions of the standards indicated below. Members of IEC and ISO maintain registers of currently valid International Standards.

ISO 7-1 : 1982, *Pipe threads where pressure-tight joints are made on the threads — Part 1: Designation, dimensions and tolerances*.

ISO 7-2 : 1982, *Pipe threads where pressure-tight joints are made on the threads — Part 2: Verification by means of limit gauges*.

ISO 261 : 1973, *ISO general purpose metric screw threads — General plan*.

ISO 887: — <sup>1)</sup>, *Plain washers for metric bolts, screws and nuts for general purposes — General plan*.

ISO 6708 : 1980, *Pipe components — Definition of nominal size*.

ISO 7268 : 1983, *Pipe components — Definition of nominal pressure*.

ISO 7483 : 1991, *Dimensions of gaskets for use with flanges to ISO 7005*.

ANSI/ASME B1.20.1 : 1983, *Pipe threads, general purpose (inch)*.

<sup>1)</sup> Series 1 flanges are the basic flanges; series 2 flanges may have a limited application in the future.

1) To be published. (Revision of ISO 887 : 1983.)

### 1.3 Definitions

For the purposes of this part of ISO 7005, the definitions of nominal size (DN) as given in ISO 6708, and nominal pressure (PN) as given in ISO 7268 and the following definition apply.

**1.3.1 pipeline:** Cross-country fluid transmission line, e.g. for oil or gas.

### 1.4 Designation of types, components and facings

Figures 1 to 4 illustrate flanges and flanged components grouped according to type and figure 5 illustrates facing types.

Figure 1: Flanges — Types 01 to 05 inclusive, comprising flanges generally manufactured from plate materials.

NOTE — Types 02 and 03 are identical; it is their ancillary components which differ (see figure 4).

Figure 2: Flanges — Types 11 to 15 inclusive, comprising flanges generally manufactured from forgings or castings.

Figure 3: Flange — Type 21 integral flange, as part of some other equipment or component.

Figure 4: Ancillary components for flanges — Types 32 to 34 inclusive, comprising parts or components for use with flange types 02, 03 and 04.

Figure 5: Facings — Types A to J inclusive, comprising the various types of flange facings which may be used where applicable in conjunction with the groups of flanges or flanged components in figures 1 to 4.

NOTE — Type numbers are not consecutive to permit possible future additions to any particular group.

## Section 2: General requirements

### 2.1 Pressure/temperature ratings

Guidance on pressure/temperature ratings of flanges forming the subject of this part of ISO 7005 is given in annex E for some flanges made from the materials listed in annex D.

### 2.2 Materials and bolting

#### 2.2.1 Range of materials

Guidance on selected materials is given in annex D.

#### 2.2.2 Gaskets

See the note in 1.1.

#### 2.2.3 Bolting

The material of the bolting should be chosen by the user according to the pressure, temperature, flange material and the selected gasket so that the flanged joint remains tight under the expected operating conditions.

For PN 20, PN 50, PN 110, PN 150, PN 260 and PN 420 flanges up to and including bolt size M45, coarse series bolts to ISO 261 shall be used; from bolt size M48 upwards, the fine series having a uniform 4 mm pitch shall be used.

### 2.3 Repairs

**2.3.1** Where not otherwise prohibited by the applicable material standard, repairs by welding are permitted when there is a proven method. All welding shall be in accordance with a written procedure.

**2.3.2** Any filler rod used for weld repairs shall be such as to produce a weld having characteristics similar to those of the parent metal. Flanges shall be heat treated after repair welding when the material specification requires such treatment.

### 2.4 Dimensions

#### 2.4.1 Range of nominal sizes

The range of nominal sizes applicable to each flange type and each nominal pressure shall be as specified in table 3.

#### 2.4.2 Tables giving dimensions

Dimensions of flanges shall be in accordance with the following tables, as appropriate.

Tables 4, 5, 6 and 7: Dimensions of flange facings

#### Series 1 flanges

Table 10: Dimensions of PN 10 flanges  
 Table 11: Dimensions of PN 16 flanges  
 Table 12: Dimensions of PN 20 flanges  
 Table 15: Dimensions of PN 50 flanges  
 Table 16: Dimensions of PN 110 flanges  
 Table 17: Dimensions of PN 150 flanges  
 Table 18: Dimensions of PN 260 flanges  
 Table 19: Dimensions of PN 420 flanges

#### Series 2 flanges

Table 8: Dimensions of PN 2,5 flanges  
 Table 9: Dimensions of PN 6 flanges  
 Table 13: Dimensions of PN 25 flanges  
 Table 14: Dimensions of PN 40 flanges

#### 2.4.3 Threads for threaded flanges

**2.4.3.1** The threads shall be taper or parallel threads in accordance with ISO 7-1 or taper threads in accordance with ANSI/ASME B1.20.1 as appropriate.

NOTE — Unless otherwise specified, parallel threads in accordance with ISO 7-1 will be supplied for flanges PN 2,5, PN 6, PN 10, PN 16, PN 25 and PN 40 and taper threads in accordance with ANSI/ASME B1.20.1 for flanges PN 20, PN 50, PN 110, PN 150, PN 260 and PN 420.

**2.4.3.2** The threads shall be concentric with the axes of the flanges and variations in alignment shall not exceed 5 mm/m. Flanges up to and including PN 40 shall be manufactured without a counterbore. The threads shall be chamfered approximately to the major diameter of the threads at the back of the flanges at an angle of approximately 45° with the axes of the threads. The chamfers shall be concentric with the threads and permitted to be included in the measurement of the thread lengths provided that the chamfers do not exceed one pitch in length.

Flanges PN 50 and above shall be provided with a counterbore at the back. The threads shall be chamfered to the diameters of the counterbores at an angle of approximately 45° with the axes of the threads. The counterbores and chamfers shall be concentric with the threads.

**2.4.3.3** Gauging shall be in accordance with ISO 7-2 or ANSI/ASME B1.20.1 as appropriate.

#### 2.4.4 Hubs — General applications

**2.4.4.1** The hub of threaded (type 13), slip-on (type 12), socket weld (type 14) and lapped (type 15) flanges shall be cylindrical or alternatively shall have a draft of not more than 7° on the outside surface for forging or casting purposes. For the limiting profile of weld neck hubs, see annex A.

**2.4.4.2** The hub dimensions of threaded (type 13) and slip-on (type 12) flanges having a reduced bore shall be at least as large as those of the standard flange of the size to which the reduction is being made. For welding neck (type 11) flanges having a reduced bore, the hub dimensions shall be the same as those of the standard flange of the size to which the reduction is being made.

#### 2.4.5 Hubs — Pipeline applications

**2.4.5.1** The hub diameter and wall thickness at the welding end shall be determined as specified in 2.4.5.1.1 to 2.4.5.1.3 as appropriate.

**2.4.5.1.1** When the minimum yield strength of the hub portion of any flange or its representative test specimen is the same as that of the mating pipe, the minimum thickness at the welding end shall be the same as that of the mating pipe.

**2.4.5.1.2** When the minimum yield strength of the hub portion of any flange or its representative test specimen is less than that specified for the pipe to be matched, the minimum thickness of the hub at the welding end shall be such that the product of its thickness times its yield strength (at the welding end) shall at least equal the product of the specified wall thickness and the minimum specified yield strength of the pipe to be matched.

**2.4.5.1.3** When the hub thickness at the welding end is greater than the wall thickness of the adjoining pipe, the joint design shall be as shown in any of the three sketches in figure B.1.

**2.4.5.2** The minimum hub outside diameter at the point of weld shall be determined by adding twice the minimum wall thickness determined in 2.4.5.1.1 or 2.4.5.1.2 to the bore specified by the customer.

**2.4.5.3** For sizes DN 300 to DN 600, when the mechanical (minimum yield strength) properties of all sections of the flanges are equal to or higher than those of the pipe to be matched, the hub dimensions are permitted to be the same as those of the general flanges as indicated in annex A.

#### 2.4.6 Welding end preparation

For welding type 11 flanges to pipe, the typical end preparation of the flange shall be as shown in annex A. When PN 20, PN 50, PN 110 and PN 150 flanges are used in pipeline applications the typical welding end preparations are as shown in annex C.

NOTE — Other welding end preparations agreed between manufacturer and purchaser do not invalidate compliance with this part of ISO 7005.

### 2.5 Facings

#### 2.5.1 Range of facings

The range of flange facings and flange face designations shall be as given in figure 5. Dimensions of facings according to the PN designation shall be in accordance with figures 6 and 7 and tables 4, 5, 6 and 7, as appropriate.

#### NOTES

1 For types B (as shown in figure 6 only), D, F, G and J the transition from the raised face diameter to the flange face is at the option of the manufacturer.

2 For PN 20 and PN 50 to PN 420 there are large and small versions of C, D, E and F types of facing. In such cases two sets of dimensions have been given in the related tables. For small male and female joints care should be taken to ensure that the inside diameter of the pipe is small enough to permit sufficient bearing surface.

3 The type B raised face on steel flanges may be removed when bolted to cast iron or copper alloy flanges for designations up to and including PN 50 in order to provide full-face gasketing if such be required. On a flanged component or fitting this will reduce the thickness and the overall length accordingly.

#### 2.5.2 Facing height/depth

For PN 2,5, PN 6, PN 10, PN 16, PN 25 and PN 40 flanges all facing heights shall be included in the minimum flange thickness and are measured from the face of the flange. The same requirement applies for PN 20 and PN 50 flanges when they have the (type B1) raised face. For PN 20, PN 50, PN 110, PN 150, PN 260 and PN 420 flanges with other facings, e.g. type B2, spigot and recess, tongue and groove, the height or depth shall be added to the minimum flange thickness. For PN 110 to PN 420 flanges all facings shall be added to the minimum flange thickness. Special requirements apply to ring-joint facings (see 2.5.3).

#### 2.5.3 Ring-joint facings

The bottom of the ring-joint groove shall not encroach below the plane of the flange edge of the appropriate minimum thickness flange. Where the depth of the ring-type joint groove would violate this requirement, sufficient metal shall be added to the flange thickness or raised face height so that the bottom of the groove shall be in the same plane as the flange edge of a minimum thickness flange.

#### 2.5.4 Lapped joints

For type 33 ancillary components for flanges, the finished height of the facing shall be not less than the pipe thickness used. If a tongue, groove or ring-joint face is required, the thickness of the lap remaining after machining the facing shall not be less than the specified thickness of the pipe used.

#### 2.5.5 Surface finish of flanges

**2.5.5.1** All flange jointing faces shall be finished in accordance with table 1 or table 2, as appropriate. The surface finishes of the faces shall be compared by visual or tactile means with reference specimens which conform to the  $R_a$  and  $R_z$  values given in tables 1 and 2.

**Table 1 — Surface finish for facings types A, B and E/F (large)**

Method of machining	Approximate depth of serration mm	Approximate radius of tool nose mm	Approximate pitch of serration mm	$R_z$ <sup>1)</sup> µm		$R_a$ <sup>1)</sup> µm	
				min.	max.	min.	max.
Turning <sup>2)</sup>	0,05	1,6	0,8	12,5	50,0	3,2	12,5
Other than turning	—	—	—	12,5	25,0	3,2	6,3

1)  $R_a$  and  $R_z$  are defined in ISO 468.

2) The term "turning" includes any method of machine operation producing either serrated concentric or serrated spiral grooves.

NOTE — For certain applications, e.g. for searching media such as low temperature gases, and for flanges of PN 150 and above, it may be necessary to stipulate closer control on the surface finish.

**NOTES**

1 It is not intended that instrument measurements are taken on the flange faces, and the  $R_a$  and  $R_z$  values as defined in ISO 468 relate to the reference specimens.

2 Other finishes may be agreed between the manufacturer and purchaser.

**2.5.5.2** The dimensions given for facings (particularly tongue and groove types) in this part of ISO 7005 apply to flanges in the condition as delivered.

When special coatings or finishes are required this should be stated in the order so that an appropriate allowance may be incorporated in the machining of any relevant mating dimensions.

**2.5.5.3** Flat face, raised face and large spigot/recess facings [i.e. types A, B and E/F (large)] shall be turned. Turning shall be carried out with a round-nosed tool in accordance with table 1.

**2.5.5.4** For tongue/groove, small spigot/recess, "O"-ring recess/groove and ring-joint facings [i.e. types C/D, E/F (small), G/H and J] the gasket surfaces shall be machined in accordance with the values shown in table 2.

**Table 2 — Surface finish values for facings types C/D, E/F (small), G/H and J**

Facing type	$R_z$ <sup>1)</sup> µm		$R_a$ <sup>1)</sup> µm	
	min.	max.	min.	max.
Tongue/groove (C/D) and small spigot/recess (E/F)	3,2	12,5	0,8	3,2
Ring-joint (J) (including side walls) and "O"-ring recess/groove (G/H)	1,6	6,3	0,4	1,6

1)  $R_a$  and  $R_z$  are defined in ISO 468.

**2.6 Spot-facing or back-facing**

Any spot-facing or back-facing required shall not reduce the flange thickness to less than the thickness specified.

When spot-facing is used, the diameter shall be large enough to accommodate the outside diameter of the equivalent normal series of ISO washers complying with ISO 887 for the metric bolt size being fitted. When a flange is back-faced, it is permissible for the fillet radius to be reduced but it shall not be eliminated entirely. The bearing surfaces for the bolting shall be parallel to the flange face within the limits shown in table 20.

When a flange is back-faced a minimum fillet radius at the hub,  $R_{min}$  (see figure 8), shall be maintained as given in table 21.

**2.7 Tolerances**

Flange dimensions shall comply with the tolerances specified in table 20.

**2.8 Marking****2.8.1 Flanges other than integral flanges**

Flanges other than integral flanges shall be marked with the following information:

- a) the number of this part of ISO 7005 (i.e. ISO 7005-1);
- b) the nominal size (DN) and the PN designation;
- c) the material designation (see 2.8.2);
- d) the manufacturer's name or trade-mark;
- e) the thread identification where appropriate (see 2.8.3);
- f) the heat (cast) number or suitable quality control number traceable to the heat number.

**NOTES**

1 Additionally, flange facing designations may be given (see also 2.8.4).

2 Where a flange is subsequently used to form an integral part of a component and the component has a lower pressure rating than that of the flange, the lower rating should be clearly marked on the component.

**2.8.2 Material designation**

The material designation shall be as specified in 2.8.2.1, 2.8.2.2 and 2.8.2.3, as appropriate.

**2.8.2.1** The material designation shall be the minimum information required to identify the material, e.g. the grade identification, preceded by the specification (standard) number where necessary.

EXAMPLES (for materials in tables D.1 and D.2)

- a) 16Mo3
- b) C26-52H
- c) X7 CrNiNb 18 10

**2.8.2.2** For flanges of nominal size DN 300 and greater, manufactured specifically for pipeline applications, the material designation shall be the material group and grade identification number in accordance with table D.3.

EXAMPLE

4.A.250

**2.8.2.3** For flanges manufactured in accordance with 2.4.5.1.2, the material designation shall comprise the material group and grade identification number for the flange and the strength grade of the pipe for which the flange has been made, presented as shown in the following example.

EXAMPLE

4.A.290/XXX

where XXX is the strength grade of the pipe, taken from the appropriate steel tube standard.

### 2.8.3 Identification of internally threaded flanges

Internally threaded flanges shall be marked to indicate the type of thread used.

Threads to ISO 7-1 shall be designated by the letter symbols Rc or Rp, as appropriate, in accordance with ISO 7-1 followed by the nominal size, e.g. Rc 3/4. Threads to ANSI/ASME B1.20.1 shall be designated by the nominal size, number of threads per inch and the letters NPT, e.g. 3/4-14NPT.

### 2.8.4 Groove number

Flanges grooved for standard ring-joints shall be marked with the letter "R" and the corresponding ring number.

### 2.8.5 Stamping

Where steel stamps are used, the marking shall be applied to the rim of the flange.

## 2.9 Inspection and test

NOTES

1 The PN 20, PN 50, PN 110, PN 150, PN 260 and PN 420 flanges specified are designed to be interchangeable with Class rated flanges to ANSI/ASME B16.5 and MSS 5P44, but they are not identical in all respects; for inspection purposes, it is recommended that the dimensions of PN 20, PN 50, PN 110, PN 150, PN 260 and PN 420 flanges are deemed to comply with the dimensions specified in ANSI/ASME B16.5 or MSS 5P44 as appropriate.


2 This part of ISO 7005 does not make provision for routine inspection or pressure testing of separate flanges. However, flanges may be required to be pressure tested after attachment of a pipe or other equipment or when forming an integral part of such equipment. The test pressure is then dependent on the requirements of the appropriate standard or code of practice in accordance with which the equipment has been manufactured. Any test pressures should not exceed 1,5 times the maximum allowable working pressure at 20°C rounded off to the next higher 1 bar<sup>1)</sup> increment.

## 2.10 Information to be supplied by the purchaser

The following information should be supplied by the purchaser in the enquiry and/or order:


- a) the number of this part of ISO 7005 (i.e. ISO 7005-1);
- b) the nominal size — DN followed by the appropriate number (see 1.3);
- c) the PN designation — PN followed by the appropriate number (see 1.3);
- d) the flange type number (see 1.4), together with reference to the ancillary component type number if appropriate;
- e) the facing type letter (see 1.4);
- f) the material designation by reference to a national standard or International Standard and grade of steel (see 2.8.2), if appropriate;
- g) the internal thread designation (see 2.4.3);
- h) the external diameter and thickness of pipe;
- i) material certification requirements;
- j) details of special coatings (see 2.5.5.2);
- k) the neck thickness S where appropriate;
- l) the bore diameter B where appropriate;
- m) the bore diameter for welding neck (type 11) or socket weld (type 14) flanges, if different from those specified in this part of ISO 7005;
- n) for pipeline flanges, the mating pipe wall thickness and yield strength (see 2.4.5.1.3) and weld preparation (see annex B);
- o) the bolting material when bolts are ordered with the flange(s).

1) 1 bar = 10<sup>5</sup> Pa

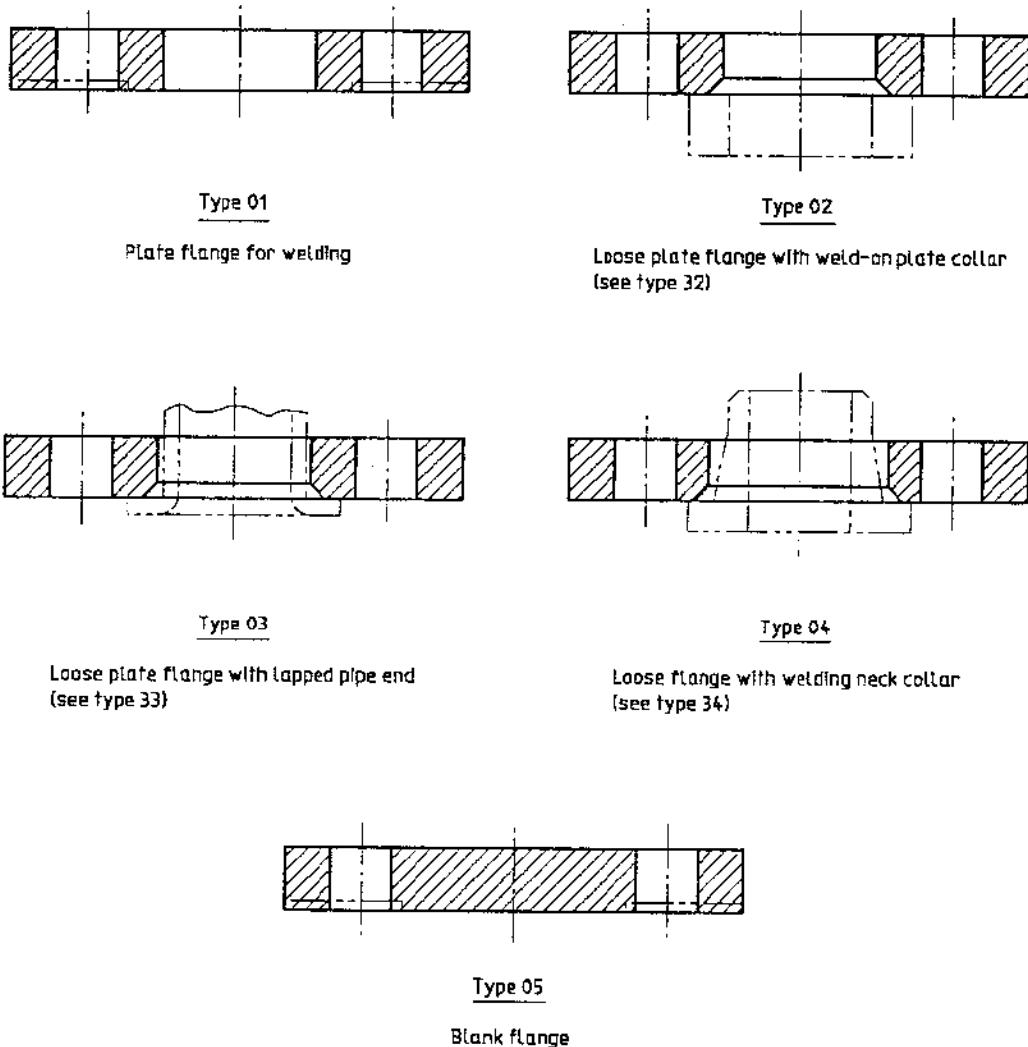


NOTE — These sketches are diagrammatic only.

Figure 1 — Flanges — Types 01 to 05

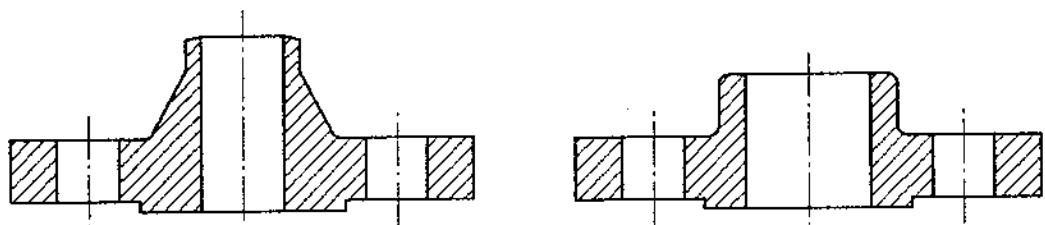


Type 11  
Welding neck flange

Type 12  
Hubbed slip-on flange for welding

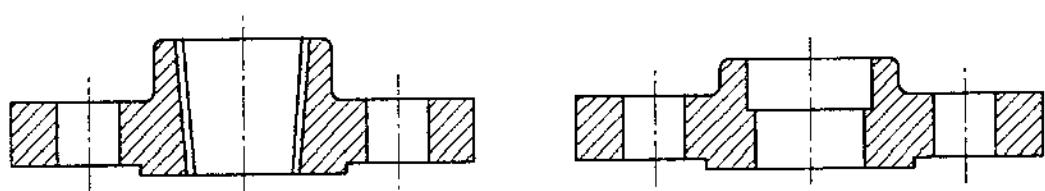

Type 13  
Hubbed threaded flange


Type 14  
Hubbed socket welding flange

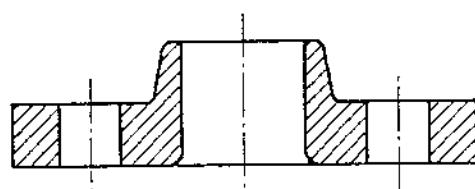

Type 15  
Loose hubbed flange for tapped pipe end

NOTE — These sketches are diagrammatic only.



**Figure 2 — Flanges — Types 11 to 15**

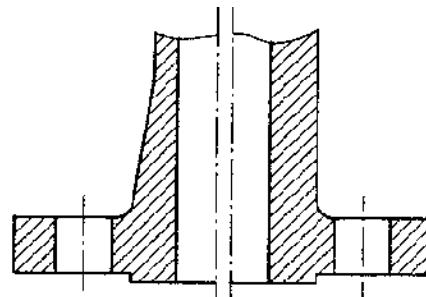

Type 21  
Integral flange, showing alternative forms

NOTE — This sketch is diagrammatic only.

Figure 3 — Flange — Type 21

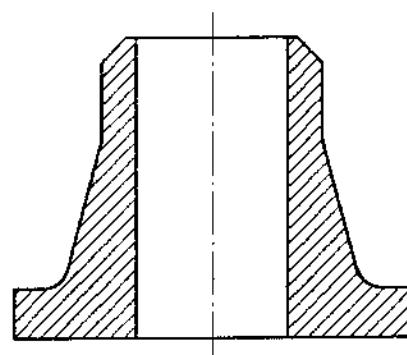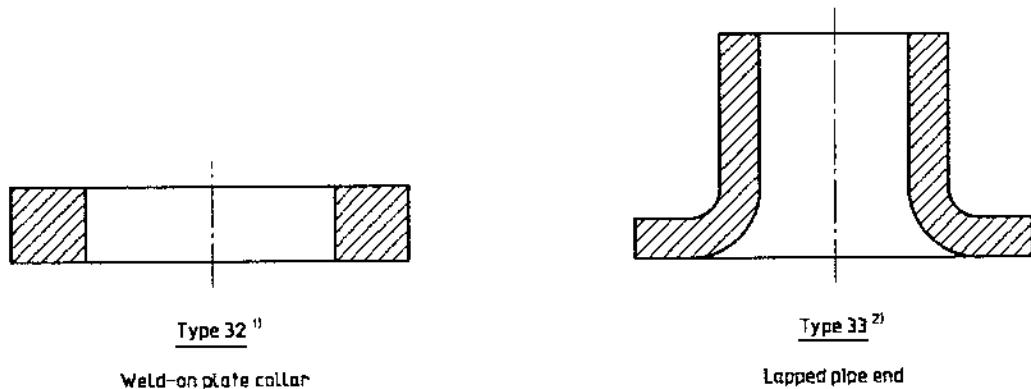


Type 34<sup>3)</sup>  
Welding neck collar

NOTE — These sketches are diagrammatic only.

- 1) Type 32 corresponds to type 02 flange.
- 2) Type 33 corresponds to type 03 flange.
- 3) Type 34 corresponds to type 04 flange.

Figure 4 — Ancillary components for flanges — Types 32 to 34

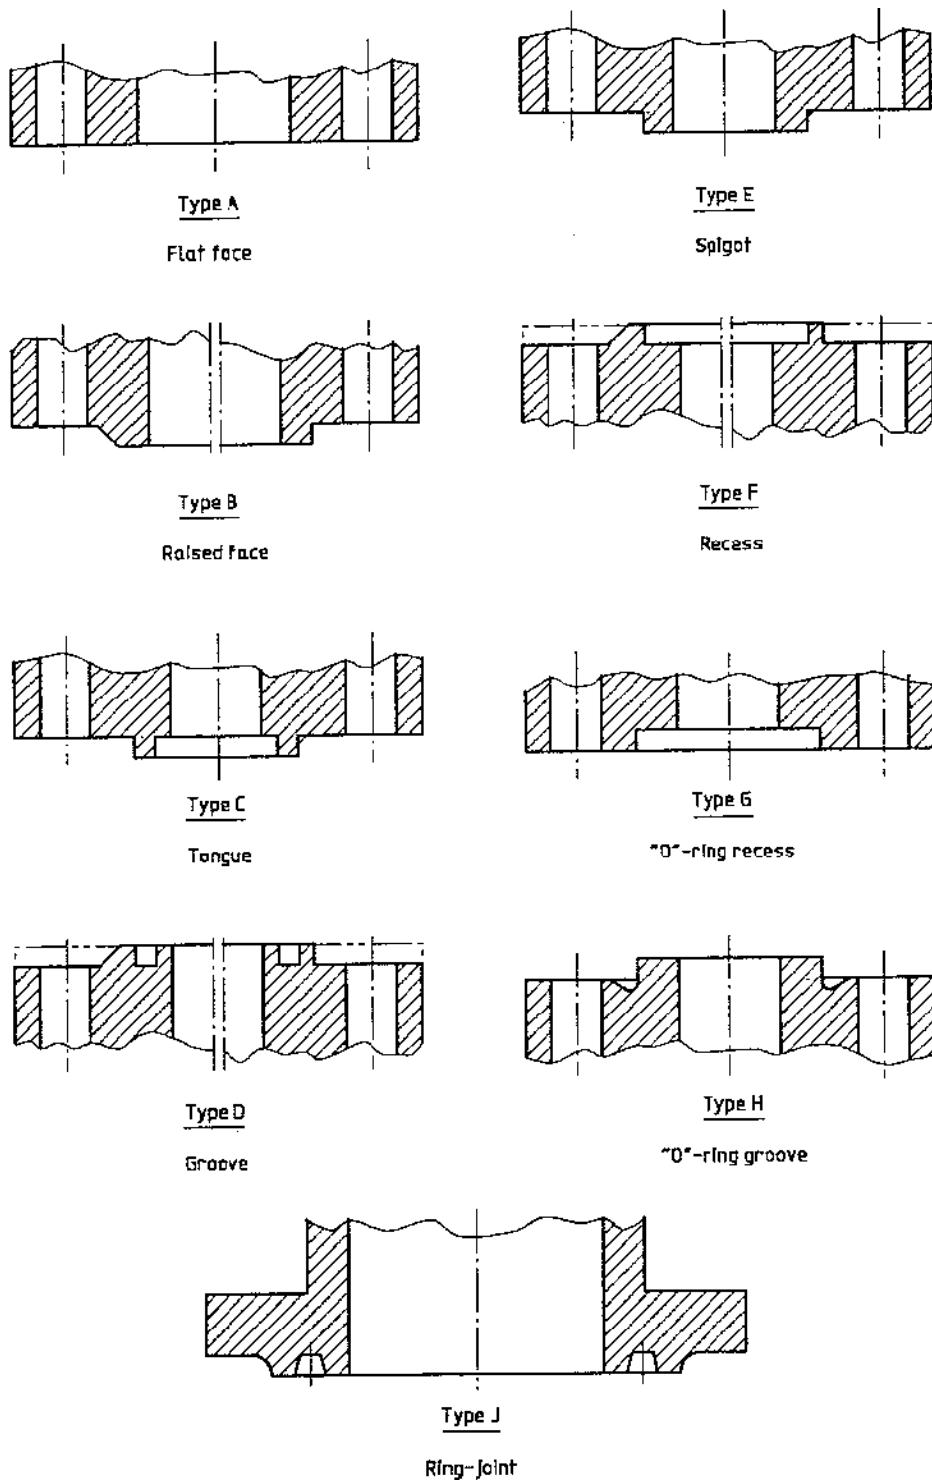

NOTE — These sketches are diagrammatic only.

**Figure 5 — Illustration of flange facings (types A to J)**

### Section 3: Dimensions

Table 3—Synoptic table

(1) Not applicable to type 04.

**Table 3** (*continued*)

**Table 3** (*concluded*)


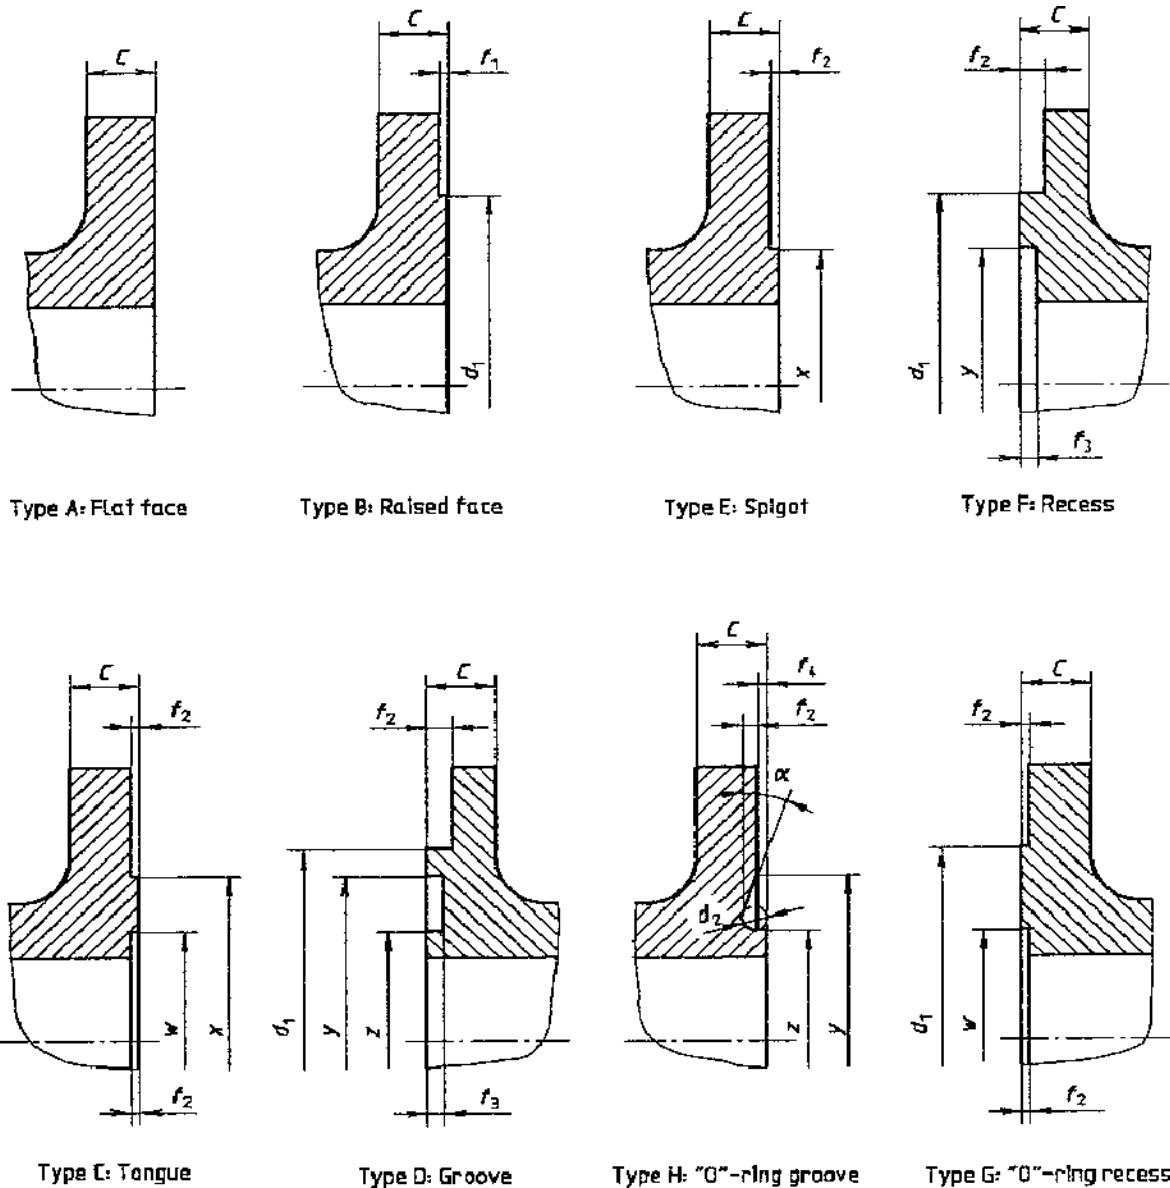


Figure 6 — PN 2,5, PN 6, PN 10, PN 16, PN 25 and PN 40 flange facing dimensions

**Table 4 — Dimensions of flange facings for PN 2,5, PN 6, PN 10, PN 16, PN 25 and PN 40 (see figure 6)**

Dimensions in millimetres

Nominal size DN	<i>d</i> <sub>1</sub>						<i>f</i> <sub>1</sub>	<i>f</i> <sub>2</sub>	<i>f</i> <sub>3</sub>	<i>f</i> <sub>4</sub>	<i>w</i>	<i>x</i>	<i>y</i>	<i>z</i>	$\alpha$	<i>d</i> <sub>2</sub>		
	PN 2,5	PN 6	PN 10	PN 16	PN 25	PN 40												
10	Use PN 6	33					41				24	34	35	23	—			
15		38					46				29	39	40	28				
20		48					56				36	50	51	35				
25		58					65				43	57	58	42				
32		69					76	4	3	2	51	65	66	50			5	
40		78					84				61	75	76	60	41°16'			
50		88					99				73	87	88	72				
65		108					118				95	109	110	94				
80		124					132				106	120	121	105				
100		144					156				129	149	150	128				
125		174					184				156	175	176	154				
150		199					211				183	203	204	182				
200		254	266	266	274		284	2	4,5	3,5	2,5	239	259	260	238	32°15'	6	
250		309	319	319	330	345						292	312	313	291			
300		363	370	370	389	409						343	363	364	342			
350		413	429	429	448	465						395	421	422	394			
400		463	480	480	503	535						447	473	474	446			
450		518	530	548	548	560						497	523	524	496			
500		568	582	609	609	615						549	575	576	548			
600		667	682	720	720	735		5	4	3		649	675	676	648	27°24'	7	
700		772	794	794	820	—						751	777	778	750			
800		878	901	901	928	—						856	882	883	855			
900		978	1 001	1 001	1 028	—						961	987	988	960			
1 000		1 078	1 112	1 112	1 140	—						1 062	1 092	1 094	1 060			
1 200		1 295	1 328	1 328	1 350	—		5				1 262	1 292	1 294	1 260			
1 400		1 510	1 530	1 530	1 560	—			6	5	4	1 462	1 492	1 494	1 460			
1 600		1 710	1 750	1 750	1 780	—						1 662	1 692	1 694	1 660	28°39'	8	
1 800		1 918	1 950	1 950	1 985	—						1 862	1 892	1 894	1 860			
2 000		2 125	2 150	2 150	2 210	—						2 062	2 092	2 094	2 060			
2 200	2 295	2 335	2 370	—	—	—												
2 400	2 495	2 545	2 570	—	—	—												
2 600	2 695	2 750	2 780	—	—	—												
2 800	2 910	2 960	3 000	—	—	—												
3 000	3 110	3 160	3 210	—	—	—												
3 200	3 310	3 370	—	—	—	—		6	—	—	—	—	—	—	—	—	—	
3 400	3 510	3 580	—	—	—	—												
3 600	3 720	3 790	—	—	—	—												
3 800	3 920	—	—	—	—	—												
4 000	4 120	—	—	—	—	—												

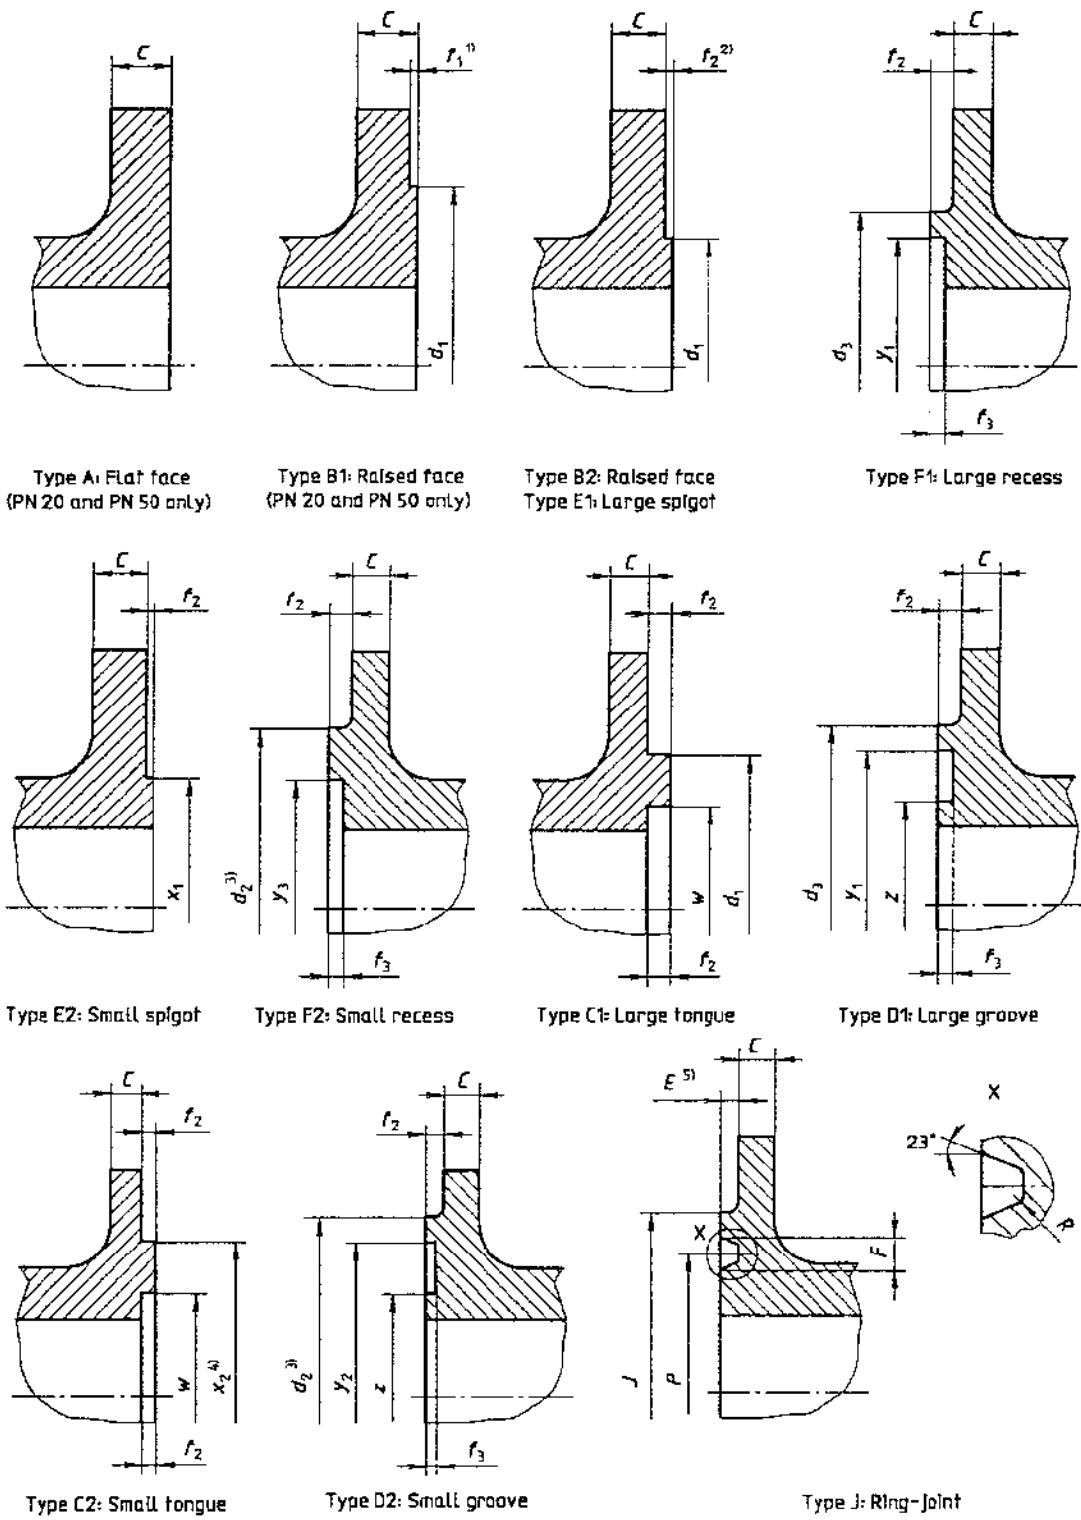

- 1)  $f_1$  applies to PN 20 and PN 50 and is included in flange thickness  $C$ .
- 2)  $f_2$  applies to PN 110, PN 150, PN 260 and PN 420, and is additional to flange thickness  $C$ .
- 3)  $d_2$  is larger than  $d_1$  for DN 15, DN 20, DN 25 and DN 32; otherwise  $d_2$  is equal to  $d_1$ .
- 4)  $x_2$  is equal to  $d_1$  for DN 15 and DN 20.
- 5) Height of raised portion  $E$  is equal to groove depth  $E$  but is not subject to tolerance (see 2.5.3).

Figure 7 — PN 20, PN 50, PN 110, PN 150, PN 260 and PN 420 flange facing dimensions

**Table 5 — Dimensions of flange facings up to nominal size DN 900 for PN 20, PN 50, PN 110, PN 150, PN 260 and PN 420**  
(see figure 7)

Nominal size	Outside diameter			Inside diameter of large and small tongue	Outside diameter			Inside diameter of large and small groove	Height		Depth of groove or recess	Dimensions in millimetres	
	Raised face, Large spigot <sup>1)</sup> , Large tongue <sup>1)</sup>	Small spigot	Small tongue		Large recess <sup>1)</sup> , Large groove <sup>1)</sup>	Small recess	Small groove		Raised face	Large and small spigot and tongue		d <sub>2</sub>	d <sub>3</sub> <sup>1)</sup>
	DN	d <sub>1</sub>	x <sub>1</sub>	x <sub>2</sub>	w	y <sub>1</sub>	y <sub>3</sub>	y <sub>2</sub>	z	f <sub>1</sub> <sup>2)</sup>	f <sub>2</sub> <sup>3)</sup>	f <sub>2</sub>	f <sub>3</sub>
15	35	18,5	35	25,5	36,5	20	36,5	24	2	7	7	5	44 46
20	43	24	43	33,5	44,5	25,5	44,5	32	2	7	7	5	52 54
25	51	30,5	48	38	52,5	32	49,5	36,5	2	7	7	5	57 62
32	63,5	38	57	47,5	65	39,5	58,5	46	2	7	7	5	67 73
40	73	44,5	63,5	54	74,5	46	65	52,5	2	7	7	5	73 84
50	92	57,5	82,5	73	93,5	59	84	71,5	2	7	7	5	92 103
65	105	68,5	95,5	85,5	106,5	70	97	84	2	7	7	5	105 116
80	127	84	117,5	108	128,5	85,5	119	106,5	2	7	7	5	127 138
100	157,5	109,5	144,5	132	159	111	146	130,5	2	7	7	5	157,5 168
125	186	136,5	173	160,5	187,5	138	174,5	159	2	7	7	5	186 197
150	216	162	203,5	190,5	217,5	163,5	205	189	2	7	7	5	216 227
200	270	213	254	238	271,5	214,5	255,5	236,5	2	7	7	5	270 281
250	324	267	305	286	325,5	268,5	306,5	284,5	2	7	7	5	324 335
300	381	317,5	362	343	382,5	319	363,5	341,5	2	7	7	5	381 392
350	413	349,5	394	374,5	414,5	351	395,5	373	2	7	7	5	413 424
400	470	400	447,5	425,5	471,5	401,5	449	424	2	7	7	5	470 481
450	533,5	451	511,5	489	535	452,5	513	487,5	2	7	7	5	533,5 544
500	584,5	501,5	559	533,5	586	503	560,5	532	2	7	7	5	584,5 595
550	641								2	7			
600	692,5	603	667	641,5	694	605	668,5	640	2	7	7	5	692,5 703,5
650	749								2	7			
700	800								2	7			
750	857								2	7			
800	914								2	7			
850	965								2	7			
900	1022								2	7			

1) Large spigot and recess faces and large tongue and groove are not applicable to PN 20 because of potential dimensional conflicts.

2) f<sub>1</sub> applies to PN 20 and PN 50, and is included in the minimum flange thickness.

3) f<sub>2</sub> applies to PN 110, PN 150, PN 260 and PN 420, and is additional to the minimum flange thickness.




NOTE — For small spigot and recess joints care should be taken in the use of these dimensions to ensure that the inside diameter of the fitting or pipe is small enough to ensure sufficient bearing surfaces.

**Table 6 — Dimensions of flange facings for nominal sizes DN 950 to DN 1 500 for PN 20, PN 50, PN 110 and PN 150**

Nominal size	Outside diameter of raised face d <sub>1</sub>				Height of raised face	Dimensions in millimetres	
	DN	PN 20	PN 50	PN 110	PN 150	f <sub>1</sub> <sup>1)</sup>	f <sub>2</sub> <sup>2)</sup>
950	1 073	1 029	1 054	1 099	2	7	
1 000	1 124	1 086	1 111	1 162	2	7	
1 050	1 194	1 137	1 168	1 213	2	7	
1 100	1 245	1 194	1 226	1 270	2	7	
1 150	1 295	1 245	1 276	1 334	2	7	
1 200	1 359	1 308	1 334	1 384	2	7	
1 250	1 410	1 359	1 384		2	7	
1 300	1 460	1 410	1 435		2	7	
1 350	1 511	1 467	1 492		2	7	
1 400	1 575	1 518	1 543		2	7	
1 450	1 626	1 575	1 600		2	7	
1 500	1 676	1 625	1 657		2	7	

1) f<sub>1</sub> applies to PN 20 and PN 50.

2) f<sub>2</sub> applies to PN 110 and PN 150.

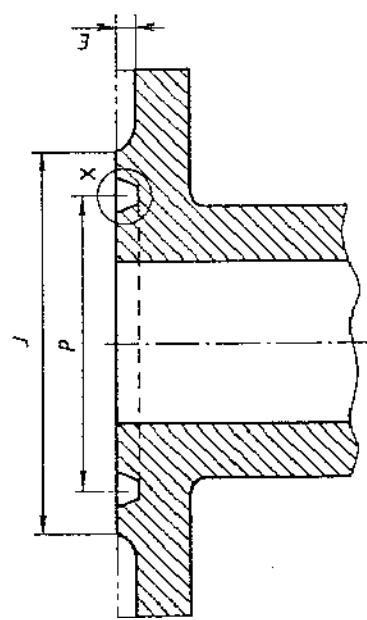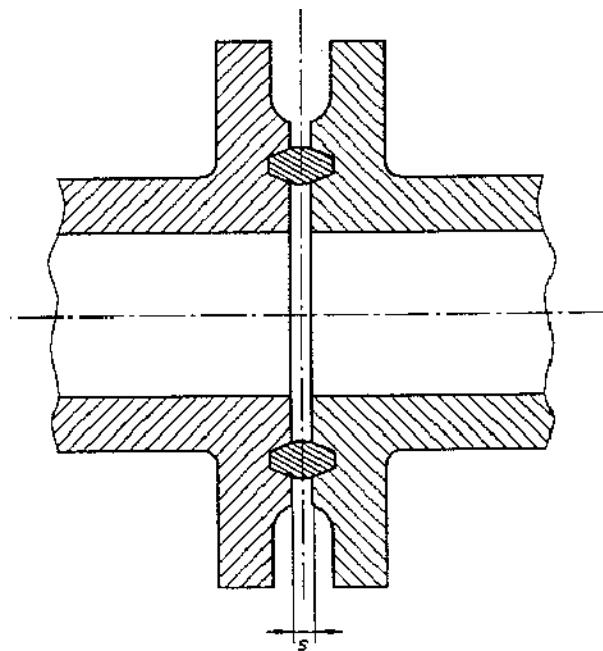

See table 7.

Table 7 — Dimensions of ring-joint facings<sup>1), 2), 3), 4)</sup>

Dimensions in millimetres

Pipe nominal size DN	Groove dimensions						Diameter of raised portion J min.						Approximate distance between flanges <sup>s</sup>															
	PN 20	PN 50	PN 110	PN 150 <sup>5)</sup>	PN 260	PN 420	Groove number	Pitch diameter $P$ $\pm 0,13$	E $+ 0,4$ 0	Depth <sup>6)</sup>	Width $F \pm 0,2$	Radius at bottom R max.	PN 20	PN 50 and PN 110	PN 150	PN 260	PN 420	PN 20	PN 50	PN 110	PN 150	PN 260	PN 420					
—	15	—	—	—	—	—	R11	34,14	5,56	7,14	0,8	—	51	—	—	—	—	3	3	—	—	—	—					
—	—	20	—	—	15	—	R12	39,67	6,35	8,74	0,8	—	—	63,5	—	—	60,5	—	—	—	4	—	4	—				
—	—	—	—	—	—	—	R13	42,88	6,35	8,74	0,8	—	—	—	—	—	65	—	—	—	4	—	4	—				
—	—	—	—	—	—	—	R14	44,45	6,35	8,74	0,8	—	—	—	—	—	66,5	—	—	—	4	—	4	—				
—	—	—	—	—	—	—	R15	47,62	6,35	8,74	0,8	—	—	63,5	—	—	—	4	—	—	—	—	—	—	—			
—	—	25	—	—	25	20	R16	50,8	6,35	8,74	0,8	—	70	—	—	71,5	73	—	4	4	—	4	4	—				
—	—	32	—	—	—	25	R17	57,15	6,35	8,74	0,8	—	73	—	—	—	4	—	—	—	4	—	4	—				
—	—	40	—	—	—	—	R18	60,32	6,35	8,74	0,8	—	79,5	—	—	81	82,5	—	4	4	—	4	4	—				
—	—	—	—	—	—	—	R19	65,07	6,35	8,74	0,8	—	82,5	—	—	—	4	—	—	—	4	—	4	—				
—	—	—	—	—	—	—	R20	68,28	6,35	8,74	0,8	—	90,5	—	—	92	—	—	4	4	—	4	4	—				
—	—	—	—	—	—	—	R21	72,24	7,92	11,91	0,8	—	—	—	—	—	102	—	—	—	—	—	—	—				
—	—	50	—	—	—	—	R22	82,55	6,35	8,74	0,8	102	—	—	—	—	—	4	—	—	—	—	—	—	3			
—	—	—	—	—	—	—	R23	82,55	7,92	11,91	0,8	—	108	—	—	—	—	114	—	—	6	5	—	—	3			
—	—	—	—	—	—	—	R24	95,25	7,92	11,91	0,8	—	—	—	—	—	124	—	—	—	—	—	—	—				
—	—	—	—	—	—	—	R25	101,6	6,35	8,74	0,8	121	—	—	—	—	—	4	—	—	—	—	—	—	—			
—	—	65	65	—	—	50	R26	101,6	7,92	11,91	0,8	—	127	—	—	—	—	133	—	—	6	5	—	—	3			
—	—	—	—	—	—	65	R27	107,95	7,92	11,91	0,8	—	—	—	—	—	137	—	—	—	—	—	—	—				
—	—	—	—	—	—	—	R28	111,12	9,52	13,49	1,5	—	—	—	—	—	149	—	—	4	—	—	—	—				
—	—	80	—	—	—	—	R29	114,3	6,35	8,74	0,8	133	—	—	—	—	—	—	—	—	—	—	—	—	—			
—	—	—	—	—	—	—	R30	117,48	7,92	11,91	0,8	—	—	—	—	—	—	—	—	—	—	—	—	—				
—	—	—	80 <sup>7)</sup>	80 <sup>7)</sup>	—	—	R31	123,82	7,92	11,91	0,8	—	146	156	—	—	—	168	—	—	6	5	—	—	3			
—	—	—	—	—	—	80	R32	127	9,52	13,49	1,5	—	—	—	—	—	168	—	—	4	—	—	—	3				
—	—	—	—	—	—	—	R33	131,78	6,35	8,74	0,8	154	—	—	—	—	—	—	—	—	6	5	—	—	3			
—	—	—	—	—	—	—	R34	131,78	7,92	11,91	0,8	—	159	—	—	—	—	—	—	—	—	—	—	—	—			
—	—	—	—	—	—	—	R35	136,52	7,92	11,91	0,8	—	—	—	—	—	168	—	—	—	—	—	—	—				
—	—	—	—	—	—	—	R36	149,22	6,35	8,74	0,8	171	—	—	—	—	175	181	—	—	4	—	—	—	3			
—	—	—	—	—	—	—	R37	149,22	7,92	11,91	0,8	—	—	—	—	—	—	—	—	203	—	—	6	5	—	—	3	
—	—	—	—	—	—	—	R38	157,18	11,13	16,66	1,5	—	—	—	—	—	—	—	194	—	—	4	—	—	—	4		
—	—	—	—	—	—	—	R39	161,92	7,92	11,91	0,8	—	—	—	—	—	—	—	—	—	—	—	—	—	—			
—	—	—	—	—	—	—	R40	171,45	6,35	8,74	0,8	194	—	—	—	—	—	—	—	—	—	4	—	—	—			
—	—	—	—	—	—	—	R41	180,98	7,92	11,91	0,8	—	210	216	—	—	—	—	—	—	6	5	—	4	—	—	—	
—	—	—	—	—	—	—	R42	190,5	12,7	19,84	1,5	—	—	—	—	—	—	—	—	241	—	—	4	—	—	—	4	
—	—	—	—	—	—	—	R43	193,68	6,35	8,74	0,8	219	—	—	—	—	—	—	—	—	229	—	—	4	—	—	—	3
—	—	—	—	—	—	—	R44	193,68	7,92	11,91	0,8	—	241	—	—	—	—	—	—	—	6	5	—	4	—	—	—	
—	—	—	—	—	—	—	R45	211,12	7,92	11,91	0,8	—	241	—	—	—	—	—	—	—	—	6	5	—	4	—	—	—

Table 7 (continued)

Dimensions in millimetres

Pipe nominal size DN			Groove dimensions				Diameter of raised portion J min.						Approximate distance between flanges <sup>s</sup>								
PN 20	PN 50	PN 110	PN 150 <sup>b</sup>	PN 260	PN 420	Groove number	Pitch diameter $P$ $\pm 0,13$	Depth <sup>6)</sup> $E$ $+ 0,4$ $0$	Width $F$ $\pm 0,2$	Radius at bottom $R$ max.	PN 20	PN 50 and PN 110	PN 150	PN 260	PN 420	PN 20	PN 50	PN 110	PN 150	PN 260	PN 420
—	—	—	—	150	—	R46	211,12	9,52	13,49	1,5	—	—	248	—	—	—	—	—	3	—	
—	—	—	—	—	150	R47	228,6	12,7	19,84	1,5	—	—	—	279	—	—	—	—	—	4	
200	—	—	—	200	—	R48	247,65	6,35	8,74	0,8	273	—	—	—	4	—	—	—	—	—	
—	—	—	—	—	200	R49	269,88	7,92	11,91	0,8	—	302	308	—	—	6	5	4	4	—	
—	—	—	—	—	—	R50	269,88	11,13	16,66	1,5	—	—	318	—	—	—	—	—	—	—	
—	—	—	—	—	—	200	R51	279,4	14,27	23,01	1,5	—	—	—	340	—	—	—	—	—	5
250	—	—	—	—	—	R52	304,8	6,35	8,74	0,8	330	—	—	—	4	—	—	—	—	—	—
—	250	—	—	250	—	R53	323,85	7,92	11,91	1,5	—	356	362	—	—	6	5	4	4	—	6
—	—	—	—	—	—	R54	323,85	11,13	16,66	2,4	—	—	—	—	—	—	—	—	—	—	
—	—	—	—	—	—	R55	342,9	17,48	30,18	2,4	—	—	—	425	—	—	—	—	—	—	
300	—	—	—	—	—	R56	381	6,35	8,74	0,8	406	—	—	—	4	—	—	—	—	—	—
—	300	—	300	—	—	R57	381	7,92	11,91	0,8	413	419	—	—	6	5	4	—	—	—	—
350	—	—	—	300	—	R58	381	14,27	23,01	1,5	—	425	—	—	—	3	—	—	—	—	—
—	—	—	—	—	—	R59	396,88	6,35	8,74	0,8	—	—	—	495	—	—	—	—	—	8	
—	—	—	—	—	300	R60	406,4	17,48	33,32	2,4	—	—	—	—	—	—	—	—	—	—	
—	350	—	—	—	—	R61	419,1	7,92	11,91	0,8	—	457	—	—	—	6	5	4	—	—	—
—	—	350	—	—	—	R62	419,1	11,13	16,66	1,5	—	467	—	—	—	4	—	—	—	—	—
400	—	—	—	350	—	R63	419,1	15,88	26,97	2,4	—	489	—	—	—	6	5	4	—	—	—
—	—	—	—	—	—	R64	454,02	6,35	8,74	0,8	483	—	—	—	3	—	—	—	—	—	—
—	—	350	—	—	—	R65	469,9	7,92	11,91	0,8	—	508	—	—	—	6	5	4	—	—	—
—	—	—	400	—	—	R66	469,9	11,13	16,66	1,5	—	—	—	524	—	—	—	6	5	4	
450	—	450	—	400	—	R67	469,9	17,48	30,18	2,4	—	—	—	546	—	—	—	4	—	8	
—	—	—	—	—	400	R68	517,52	6,35	8,74	0,8	—	546	—	—	—	3	—	—	—	—	—
—	—	—	—	—	—	R69	533,4	7,92	11,91	0,8	—	575	—	—	—	6	5	5	—	—	—
—	—	—	—	—	—	R70	533,4	12,7	19,84	1,5	—	594	—	—	—	—	—	—	—	—	—
—	—	—	—	—	400	—	R71	533,4	17,48	30,18	2,4	—	—	—	613	—	—	—	—	—	—
500	—	500	—	—	—	R72	558,8	6,35	8,74	0,8	597	—	—	—	3	—	—	—	—	—	8
—	—	—	—	—	—	R73	584,2	9,52	13,49	1,5	—	635	—	—	—	6	5	5	—	—	—
—	—	—	—	—	—	R74	584,2	12,7	19,84	2,4	—	648	—	—	—	—	—	—	—	—	10
—	—	—	—	—	—	R75	584,2	17,48	33,32	2,4	—	673	—	—	—	—	—	—	—	—	—
600	—	600	—	—	—	R76	673,1	6,35	8,74	0,8	711	—	—	—	3	—	—	—	—	—	—
—	—	—	—	—	—	R77	692,15	11,13	16,66	1,5	—	749	—	—	—	6	5	6	—	—	—
—	—	—	—	—	—	R78	692,15	15,88	26,97	2,4	—	772	—	—	—	—	—	—	—	—	—
—	—	—	—	—	—	R79	692,15	20,62	36,53	2,4	—	794	—	—	—	—	—	—	—	—	11

**Table 7 (concluded)**

Dimensions in millimetres

Pipe nominal size DN						Groove dimensions			Diameter of raised portion <i>J</i> min.						Approximate distance between flanges <sup>s</sup>							
PN 20	PN 50	PN 110	PN 150 <sup>b)</sup>	PN 260	PN 420	Groove number	Pitch diameter $\pm 0,13$	Depth <sup>d)</sup> $E + 0,4$ 0	Width $F \pm 0,2$	Radius at bottom <i>R</i> max.	PN 20	PN 50 and PN 110	PN 150	PN 260	PN 420	PN 20	PN 50	PN 110	PN 150	PN 260	PN 420	
—	—	—	—	—	—	R93	749,3	12,7	19,85	2	810	—	—	—	—	6	—	—	—	—	—	
—	—	—	—	—	—	R93	749,3	12,7	19,85	2	810	—	—	—	—	—	5	—	—	—	—	
—	—	—	—	—	—	R100	749,3	17,46	30,16	2	—	832	—	—	—	—	—	8	—	—	—	
—	—	—	—	—	—	R94	800,1	12,7	19,85	2	860	—	—	—	—	6	—	—	—	—	—	
—	—	—	—	—	—	R94	800,1	12,7	19,85	2	860	—	—	—	—	5	—	—	—	—	—	
—	—	—	—	—	—	R101	800,1	17,46	33,34	2	—	889	—	—	—	—	10	—	—	—	—	
—	—	—	—	—	—	R95	857,25	12,7	19,85	2	918	—	—	—	—	6	—	—	—	—	—	
—	—	—	—	—	—	R95	857,25	12,7	19,85	2	918	—	—	—	—	5	—	—	—	—	—	
—	—	—	—	—	—	R102	857,25	17,46	33,34	2	—	946	—	—	—	—	10	—	—	—	—	
—	—	—	—	—	—	R96	914,4	14,3	23	2	984	—	—	—	—	7	—	—	—	—	—	
—	—	—	—	—	—	R96	914,4	14,3	23	2	984	—	—	—	—	6	—	—	—	—	—	
—	—	—	—	—	—	R103	914,4	17,46	33,34	2	—	1003	—	—	—	—	10	—	—	—	—	
—	—	—	—	—	—	R97	965,2	14,3	23	2	1035	—	—	—	—	7	—	—	—	—	—	
—	—	—	—	—	—	R97	965,2	14,3	23	2	1035	—	—	—	—	6	—	—	—	—	—	
—	—	—	—	—	—	R104	965,2	20,64	36,51	2	—	1067	—	—	—	—	11	—	—	—	—	
—	—	—	—	—	—	R98	1022,35	14,3	23	2	1092	—	—	—	—	7	—	—	—	—	—	
—	—	—	—	—	—	R98	1022,35	14,3	23	2	1092	—	—	—	—	6	—	—	—	—	—	
—	—	—	—	—	—	R105	1022,35	20,64	36,51	2	—	1124	—	—	—	—	11	—	—	—	—	—

1) For facing requirements for flanges and flanged fittings, see figure 6.

2) For facing requirements for lapped joints, see 2.5.4 and figure 6.





3) For ring dimensions, see ISO 7483.

4) See 2.8 for marking requirements.

5) Use PN 260 in sizes DN 15 to DN 65 for PN 150.

6) Height of raised portion is equal to the depth of groove *E* but is not subject to the tolerance for *E*. The former full-face contour may be used.

7) For ring joints with lapped flanges in PN 50 and PN 110, ring and groove number R30 are used instead of R31.

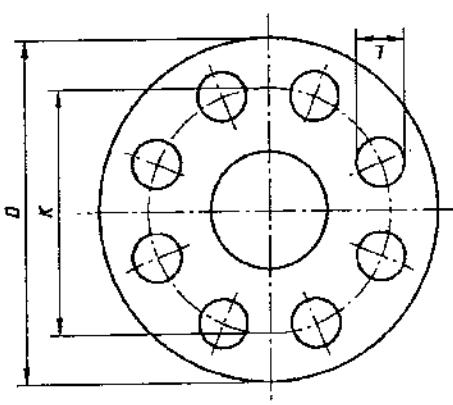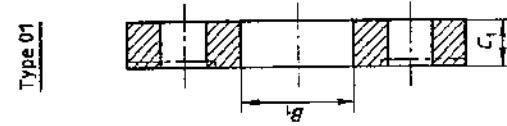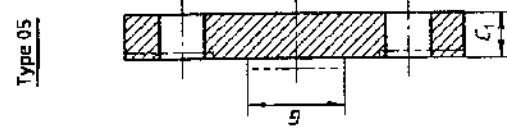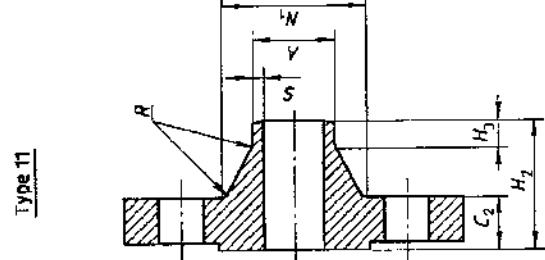

This diagram illustrates the arrangement but  
not necessarily the correct number of bolt holes.  
Refer to the column "number of bolts" in table 8  
for the actual number.

**Table 8 — Dimensions of PN 2,5 flanges**  
(See the notes on page 46.)


Nominal size DN	Outside diameter of flange D	Mating dimensions			Bore diameter B <sub>1</sub>	Flange thickness C <sub>2</sub>	Shoulder diameter G	Length of hub H <sub>2</sub>	Neck diameter N <sub>1</sub>	Corner radius R	Neck thickness (see note 6) S	Nominal size DN
		Outsize diameter of bolt circle K	Diameter of bolt holes L	Bolts Number								
		01, 05, 11		11	01	01, 05	11	05	11	11	11	11
10 to 600												
700	860	810	26	24	M24	36	26	—	70	16	740	12
800	975	920	29,5	24	M27	38	26	—	70	16	842	12
900	1 075	1 020	29,5	24	M27	40	26	—	70	16	942	12
1 000	1 175	1 120	29,5	28	M27	42	26	—	70	16	1 045	12
1 200	1 375	1 320	29,5	32	M27	44	26	—	70	16	1 245	16
1 400	1 575	1 520	29,5	36	M27	48	26	—	70	16	1 445	16
1 600	1 790	1 730	29,5	40	M27	51	26	—	80	20	1 645	16
1 800	1 990	1 930	29,5	44	M27	54	26	—	80	20	1 845	16
2 000	2 190	2 130	29,5	48	M27	58	26	—	80	22	2 045	16
2 200	2 405	2 340	32,5	52	M30	—	28	—	90	25	2 248	18
2 400	2 605	2 540	32,5	56	M30	—	28	—	90	25	2 448	18
2 600	2 805	2 740	32,5	60	M30	—	28	—	90	25	2 648	18
2 800	3 030	2 960	35,5	64	M33	—	30	—	90	25	2 848	18
3 000	3 230	3 160	35,5	68	M33	—	30	—	90	25	3 050	18
3 200	3 430	3 360	35,5	72	M33	—	30	—	90	25	3 250	20
3 400	3 630	3 560	35,5	76	M33	—	32	—	95	28	3 450	20
3 600	3 840	3 770	35,5	80	M33	—	32	—	100	28	3 652	20
3 800	4 045	3 970	39	80	M36	—	34	—	100	28	3 852	20
4 000	4 245	4 170	39	84	M36	—	34	—	100	28	4 052	20
												4 000

NOTE — For facing dimensions, see table 4.


To be specified by the purchaser

Use PN 6


Use PN 16

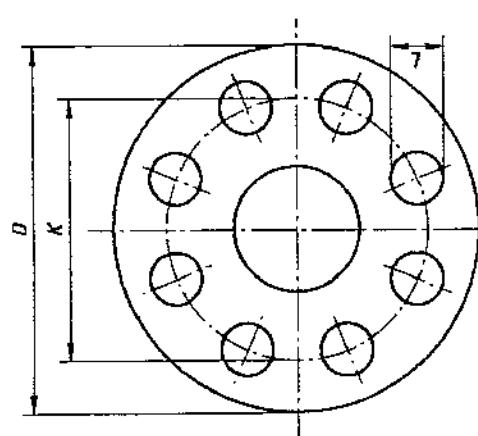


Type 05

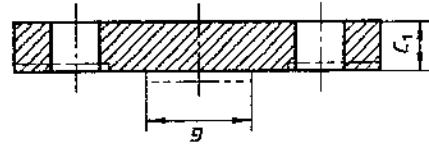


Type 03

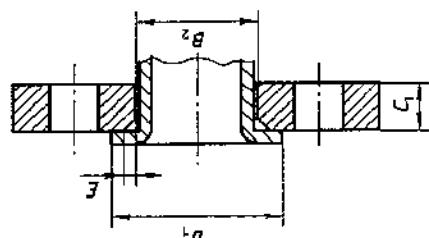

Type 02

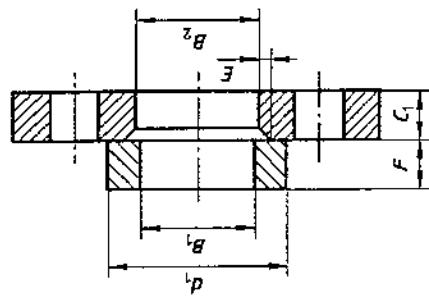


Type 01

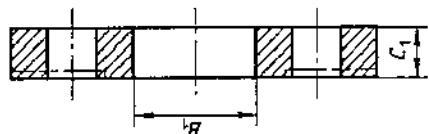


This diagram illustrates the arrangement but not necessarily the correct number of bolt holes.  
Refer to the column "number of bolts" in table 9  
for the actual number.


Type 11

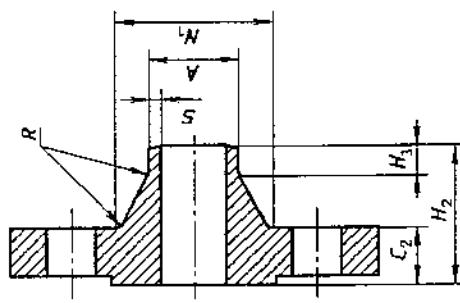


Type 21

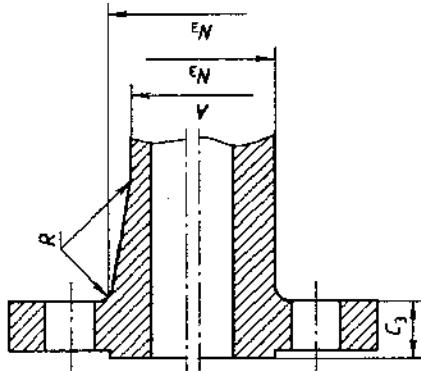

Type 13

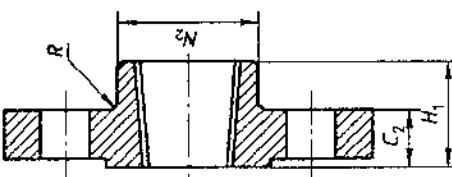

Type 12

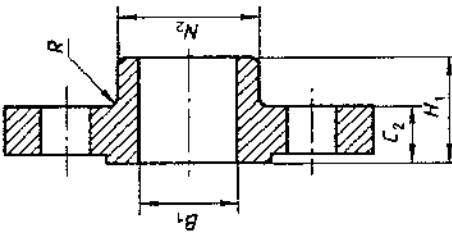


**Table 9 — Dimensions of PN 6 flanges**  
(See the notes on page 46.)

Dimensions in millimetres

Nominal size DN	Mating dimensions			Bore diameter A	Outside diameter of neck	Flange thickness	Chamfer G	Collar thickness F	Shoulder diameter C	Length of hub H <sub>1</sub>	Neck diameter N <sub>1</sub>	Corner radius R	Neck thickness (see note 6) S	Nominal size DN
	Outside diameter of flange D	Diameter of bolt circle K	Bolt Number L											
	01, 02, 03, 05, 11, 12, 13, 21			11, 21	01, 02, 02, 03	01, 05 02, 03	01, 21 02, 13	02	05	12, 13	11	11	12, 13	11
10	75	50	11	4	M10	172	18	21	12	3	10	—	20	25
15	80	55	11	4	M10	213	22	25	12	3	10	—	20	26
20	90	65	11	4	M10	269	27.5	31	14	4	10	—	24	30
25	100	75	11	4	M10	337	34.5	38	14	4	10	—	24	35
32	120	90	14	4	M12	42.4	43.5	46	16	5	10	—	26	35
40	130	100	14	4	M12	48.3	49.5	53	16	5	10	—	26	38
50	140	110	14	4	M12	60.3	61.5	65	16	5	12	—	28	38
65	160	130	14	4	M12	76.1	77.5	81	16	6	12	—	32	38
80	190	150	18	4	M16	88.9	90.5	94	18	6	12	—	34	42
100	210	170	18	4	M16	114.3	116	120	18	6	14	—	40	45
125	240	200	18	8	M16	139.7	141.5	145	20	6	14	—	115	144
150	265	225	18	8	M16	168.3	170.5	174	20	6	14	—	140	148
200	320	280	18	8	M16	219.1	221.5	226	22	6	16	—	190	—
250	375	335	18	12	M16	273	276.5	281	24	8	18	—	235	—
300	440	395	22	12	M20	323.9	327.5	333	24	24	8	—	285	—
350	490	445	22	12	M20	355.6	359.5	365	24	8	18	—	325	—
400	540	495	22	16	M20	406.4	411	416	28	24	8	—	375	—
450	595	550	22	16	M20	457	462	467	30	24	8	—	425	—
500	645	600	22	20	M20	508	513.5	519	32	26	8	22	475	—
600	755	705	26	20	M24	610	616.5	622	36	30	8	22	575	—
700	860	810	26	24	M24	711	—	40 <sup>1)</sup>	40	26	—	—	—	—
800	975	920	29.5	24	M27	813	—	44 <sup>1)</sup>	44	26	—	—	—	—
900	1 075	1 020	29.5	24	M27	914	—	—	48 <sup>1)</sup>	48	26	—	—	—
1 000	1 175	1 120	29.5	28	M27	1 016	—	—	52 <sup>1)</sup>	52	26	—	—	—
1 200	1 405	1 340	32.5	32	M30	1 220	—	—	60 <sup>1)</sup>	60	28	—	—	—
1 400	1 630	1 560	35.5	36	M33	1 420	—	—	68 <sup>1)</sup>	68	32	—	—	—
1 600	1 830	1 760	35.5	40	M33	1 620	—	—	76 <sup>1)</sup>	76	34	—	—	—
1 800	2 045	1 970	39	44	M36	1 820	—	—	84 <sup>1)</sup>	84	36	—	—	—
2 000	2 265	2 180	42	48	M39	2 020	—	—	92 <sup>1)</sup>	92	38	—	—	—
2 200	2 475	2 390	42	52	M39	2 220	—	—	42	—	—	—	—	—
2 400	2 685	2 600	42	56	M39	2 420	—	—	44	—	—	—	—	—
2 600	2 905	2 810	48	60	M45	2 620	—	—	46	—	—	—	—	—
2 800	3 115	3 020	48	64	M45	2 820	—	—	48	—	—	—	—	—
3 000	3 315	3 220	48	68	M45	3 020	—	—	50	—	—	—	—	—
3 200	3 525	3 430	48	72	M45	3 220	—	—	54	—	—	—	—	—
3 400	3 735	3 640	48	76	M45	3 420	—	—	56	—	—	—	—	—
3 600	3 970	3 860	55	80	M52	3 620	—	—	60	—	—	—	—	—

1) For type 01 flanges only.


NOTE — For d<sub>1</sub> and facing dimensions, see table 4.

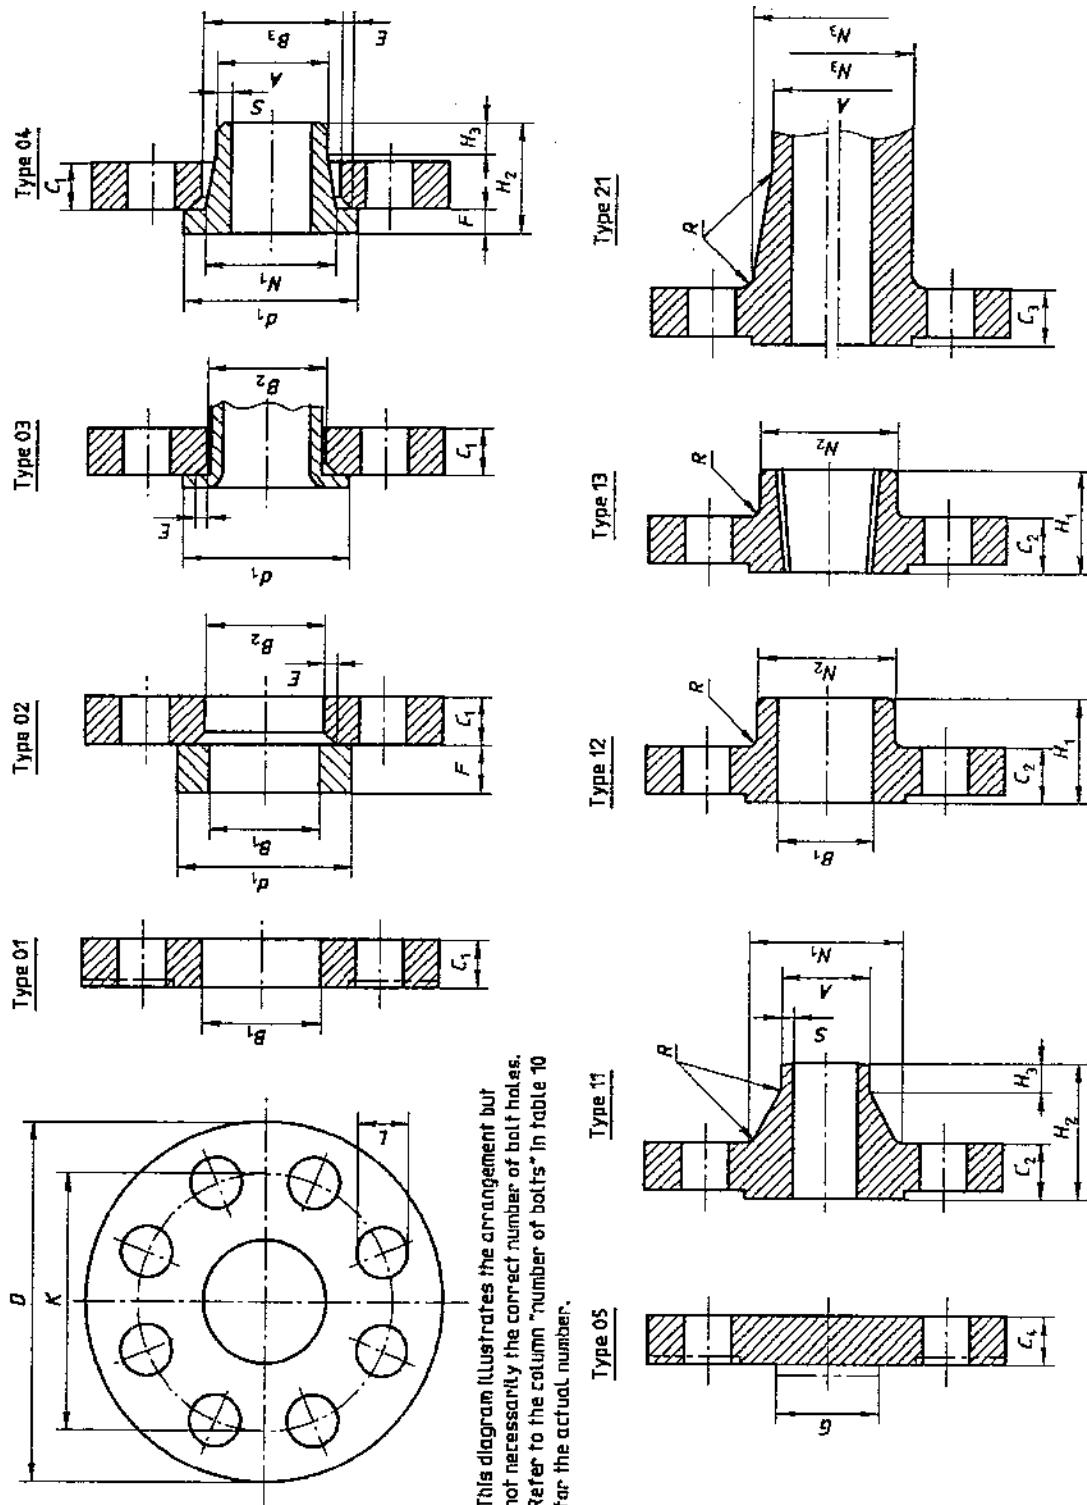

**Table 10 — Dimensions of PN 10 flanges**  
 (See the notes on page 46.)

Nominal size DN	Matting dimensions				Bore diameter $B_1$	$B_2$	$B_3$	Chamfer	Collar thickness	Shoulder diameter	Length of hub	Neck diameter	Corner radius	Neck thickness (see note 6)	Nominal size DN							
	Outside diameter of flange $D$	Diameter of bolt circle $K$	Diameter of bolt holes $L$	Number of bolts																		
01, 02, 03, 04, 05, 11, 12, 13, 21	04, 11, 21	01, 12	01, 02	02, 03	04	01, 11	02, 12	03, 13	02, 03, 04	02, 04	05	12, 13	04, 11	11, 12, 13, 21	04, 11							
10	15	20														10						
25	32	40														15						
50	65	80														20						
100	125	150														25						
200	340	295	22	8	M20	219,1	221,5	226	240	24	6	20	190	44	62	16	234	246	8	6,3		
250	395	350	22	12	M20	273	276,5	327,5	333	294	26	26	22	235	46	68	16	288	298	10	6,3	
300	445	400	22	12	M20	323,9	327,5	348	348	28	26	8	22	285	46	68	16	342	350	10	7,1	
350	505	460	22	16	M20	355,6	359,5	400	411	406,4	30	26	8	22	325	53	68	16	390	400	10	8
400	565	515	26	16	M24	406,4	416	450	457	462	32	28	8	24	375	57	72	16	440	456	10	8,8
450	615	565	26	20	M24	457	467	498	498	462	35	28	8	24	425	63	72	16	488	502	12	10
500	670	620	26	20	M24	508	513,5	519	550	58	28	8	26	475	67	75	16	540	559	12	11	
600	780	725	29,5	24	M27	610	616,5	622	650	42	34	8	26	575	75	80	18	640	658	12	12,5	
700	895	840	29,5	24	M27	711	—	—	—	—	30	34	8	—	670	—	80	18	746	—	72	12
800	1 015	950	32,5	24	M30	813	—	—	—	—	32	36	42	—	770	—	90	18	848	—	876	12
900	1 115	1 050	32,5	28	M30	914	—	—	—	—	34	38	46	—	860	—	95	20	948	—	976	12
1 000	1 230	1 160	35,5	28	M33	1 016	—	—	—	—	34	38	52	—	960	—	95	20	1 050	—	1 080	12
1 200	1 455	1 380	39	32	M36	1 220	—	—	—	—	38	42	48	—	1 160	—	115	25	1 256	—	1 292	12
1 400	1 675	1 590	42	36	M39	1 420	—	—	—	—	42	48	60	—	1 200	25	1 460	—	1 496	12	1 460	12
1 600	1 915	1 820	48	40	M45	1 620	—	—	—	—	46	52	—	—	130	25	1 666	—	1 712	12	1 712	12
1 800	2 115	2 020	48	44	M45	1 820	—	—	—	—	50	56	—	—	140	30	1 866	—	1 910	15	1 910	15
2 000	2 325	2 230	48	48	M45	2 020	—	—	—	—	54	60	—	—	150	30	2 070	—	2 120	15	2 120	15
2 200	2 550	2 440	55	52	M52	2 220	—	—	—	—	58	—	—	—	160	35	2 275	—	18	18	2 200	18
2 400	2 760	2 650	55	56	M52	2 420	—	—	—	—	62	—	—	—	170	40	2 478	—	18	18	2 400	18
2 600	2 960	2 850	55	60	M52	2 620	—	—	—	—	66	—	—	—	180	40	2 680	—	18	18	2 600	18
2 800	3 180	3 070	55	64	M52	2 820	—	—	—	—	70	—	—	—	190	40	2 882	—	18	18	2 800	18
3 000	3 405	3 290	60	68	M56	3 020	—	—	—	—	75	—	—	—	200	45	3 085	—	—	—	3 000	—

卷之三

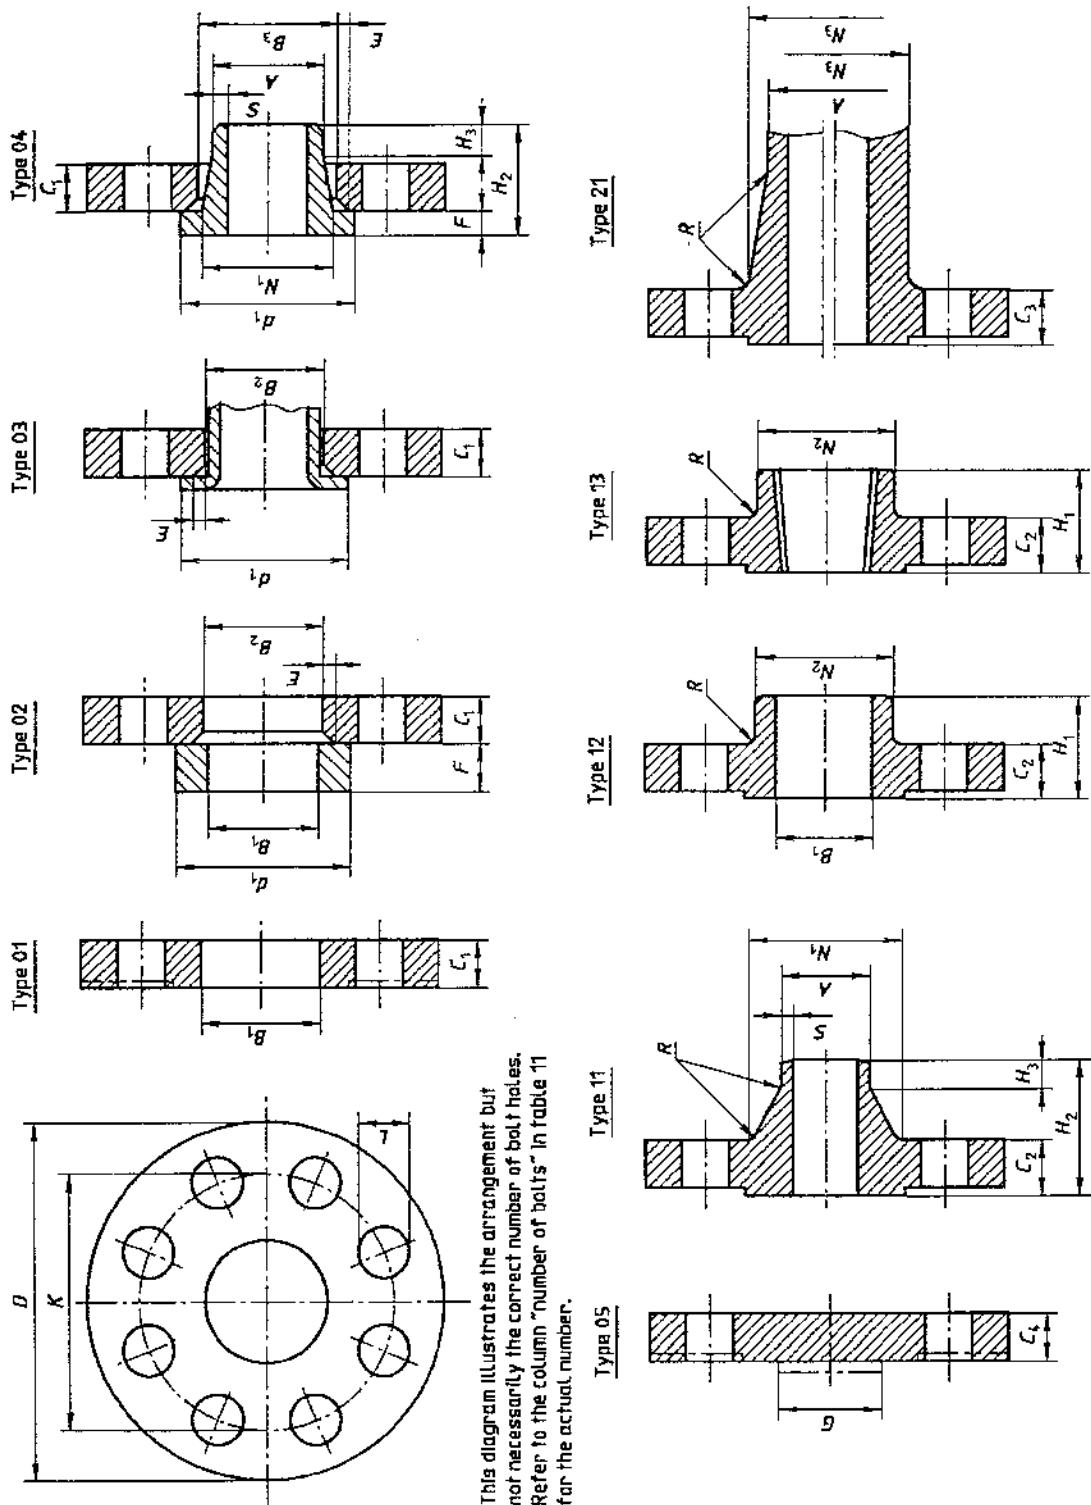


**Table 11 — Dimensions of PN 16 flanges**  
(See the notes on page 46.)

Nominal size DN	Mating dimensions				Bore diameter A	Outside diameter of neck C <sub>1</sub>	Bore diameter B <sub>1</sub>	Bore diameter B <sub>2</sub>	Bore diameter B <sub>3</sub>	Flange thickness E	Chamfer F	Shoulder diameter G	Length of hub H <sub>1</sub>	Length of hub H <sub>2</sub>	Length of hub H <sub>3</sub>	Neck diameter N <sub>1</sub>	Neck diameter N <sub>2</sub>	Neck diameter N <sub>3</sub>	Corner radius R	Neck thickness S	Neck thickness (see note 6)	Nominal size DN		
	Outer diameter of flange D	Diameter of bolt circle K	Diameter of bolt holes L	Bolts Number																				
	Nominal size DN	Outer diameter of neck C <sub>1</sub>	Number of bolt holes L	Nominal size																				
01, 02, 03, 04, 05, 11, 12, 13, 21	04, 11, 21	01, 02, 12	03	04, 01, 02, 11, 12, 13	04, 11, 21	01, 02, 12	03	04, 03, 04	04, 11, 21	02, 03, 04	02, 04	05	12, 13	11	04, 11, 12, 13	11	21	11, 12, 13, 21	04, 11	—	—			
10	15	20	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—		
15	25	32	40	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	
20	25	32	40	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	
25	32	40	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	
32	40	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	
40	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	
50	65	80	100	125	150	200	250	300	350	400	450	500	600	700	800	900	1 000	1 200	1 400	1 600	1 800	2 000	—	
65	185	145	180	180	180	205	295	340	355	410	580	715	840	910	1 025	1 125	1 255	1 485	1 685	1 930	2 130	2 345	—	
80	160	18	8	18	8	M16	M16	M16	M16	M20	M20	M20	M20	M24	M24	M24	M24	M24	M24	M27	M27	M27	M27	—
100	220	180	18	18	8	M16	M16	M16	M16	M20	M20	M20	M20	M24	M24	M24	M24	M24	M24	M27	M27	M27	M27	—
125	250	210	18	22	8	M16	M16	M16	M16	M20	M20	M20	M20	M24	M24	M24	M24	M24	M24	M27	M27	M27	M27	—
150	285	240	22	8	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—
200	340	295	22	12	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—
250	405	355	26	12	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—
300	460	410	26	12	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—
350	520	470	26	16	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—
400	580	525	29,5	16	M24	M24	M24	M24	M27	M27	M27	M27	M27	M27	M27	M27	M27	M27	M27	M27	M27	M27	M27	M27
450	640	585	29,5	20	M27	M27	M27	M27	M27	M27	M27	M27	M27	M27	M27	M27	M27	M27	M27	M27	M27	M27	M27	M27
500	715	650	32,5	20	M30	M30	M33	M33	M33	M33	M33	M33	M33	M33	M36	M36	M36	M36	M36	M36	M36	M36	M36	M36
600	840	770	35,5	20	M33	M33	M33	M33	M33	M33	M33	M33	M33	M33	M36	M36	M36	M36	M36	M36	M36	M36	M36	M36
700	910	840	35,5	24	M33	M33	M33	M33	M33	M33	M33	M33	M33	M33	M36	M36	M36	M36	M36	M36	M36	M36	M36	M36
800	1 025	950	39	24	M36	M36	M36	M36	M36	M36	M36	M36	M36	M36	M36	M36	M36	M36	M36	M36	M36	M36	M36	M36
900	1 125	1 050	39	28	M36	M36	M36	M36	M36	M36	M36	M36	M36	M36	M36	M36	M36	M36	M36	M36	M36	M36	M36	M36
1 000	1 255	1 170	42	28	M39	M39	M39	M39	M39	M39	M39	M39	M39	M39	M39	M39	M39	M39	M39	M39	M39	M39	M39	M39
1 200	1 485	1 390	48	32	M45	M45	M45	M45	M45	M45	M45	M45	M45	M45	M45	M45	M45	M45	M45	M45	M45	M45	M45	M45
1 400	1 685	1 590	48	36	M45	M45	M45	M45	M45	M45	M45	M45	M45	M45	M45	M45	M45	M45	M45	M45	M45	M45	M45	M45
1 600	1 930	1 820	55	40	M52	M52	M52	M52	M52	M52	M52	M52	M52	M52	M52	M52	M52	M52	M52	M52	M52	M52	M52	M52
1 800	2 130	2 020	55	44	M52	M52	M52	M52	M52	M52	M52	M52	M52	M52	M52	M52	M52	M52	M52	M52	M52	M52	M52	M52
2 000	2 345	2 230	60	48	M56	M56	M56	M56	M56	M56	M56	M56	M56	M56	M56	M56	M56	M56	M56	M56	M56	M56	M56	M56


1) For type 01 flanges only.

NOTE — For  $d_1$  and facing dimensions, see table 4.

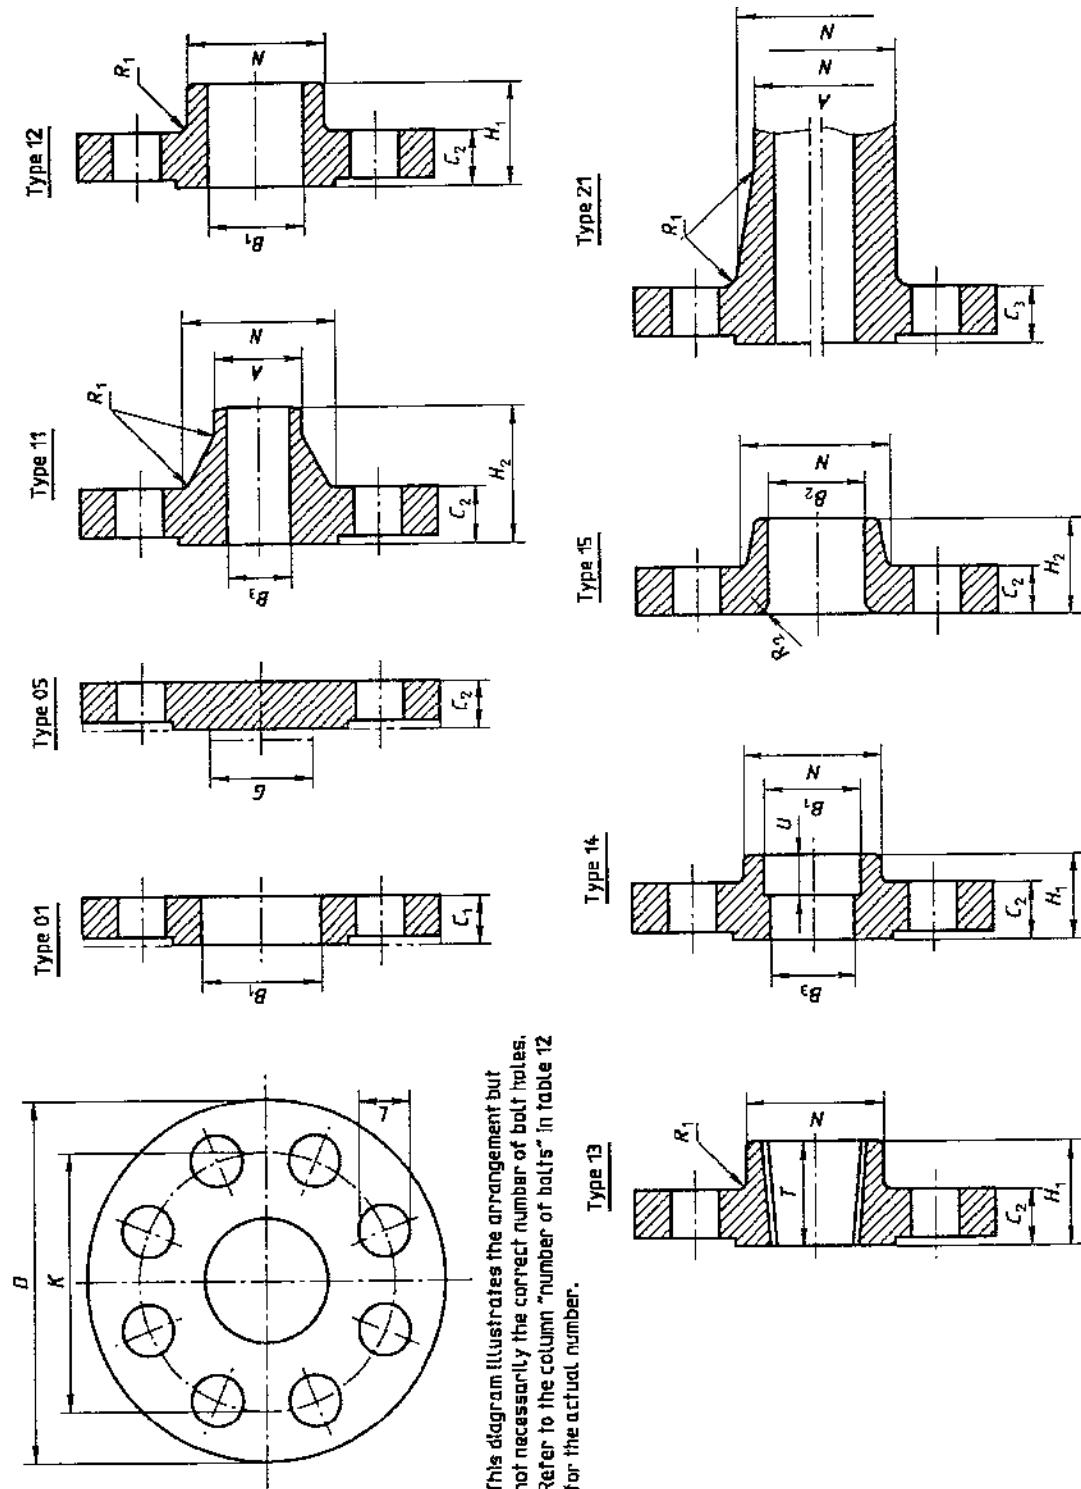

**Table 12 — Dimensions of PN 20 flanges**  
(See the notes on page 46.)


Nominal size DN	Mating dimensions				Bore diameter (see note 8)				Flange type (see note 9)			Shoulder diameter			Length of hub		Neck diameter			Corner radius		Lap radius (at pipe end)		Minimum thread length of flange (see note 5)		Depth of socket		Nominal size		Dimensions in millimetres																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																											
Outside diameter of flange D	Diameter of bolt circle K	Bolts Number	Diameter of bolt holes L	A	B<sub>1</sub>	B<sub>2</sub>	B<sub>3</sub>	C<sub>1</sub>	C<sub>2</sub>	C<sub>3</sub>	G	H<sub>1</sub>	H<sub>2</sub>	N	R<sub>1</sub>	R<sub>2</sub>	U	Fillet radius (at hub end)	Corner radius (at hub end)	Radius (at pipe end)	Minimum thread length of flange (see note 5)	T	U	V	W	X	Y	Z	AA	BB	CC	DD	EE	FF	GG	HH	II	JJ	KK	LL	MM	NN	OO	PP	QQ	RR	SS	TT	UU	VV	WW	XX	YY	ZZ																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																																			
	01, 05, 11, 12, 13, 14, 15, 21				11, 21	01, 12, 14	15	11, 14	01, 05, 11, 12, 13, 15	21	05	12, 13, 14	15	11	11, 12, 13, 14, 15, 21	15, 21	15	13	14	10	11	12	13, 21	15	16	17	18	19	20	21	22	23	24	25	26	27	28	29	30	31	32	33	34	35	36	37	38	39	40	41	42	43	44	45	46	47	48	49	50	51	52	53	54	55	56	57	58	59	60	61	62	63	64	65	66	67	68	69	70	71	72	73	74	75	76	77	78	79	80	81	82	83	84	85	86	87	88	89	90	91	92	93	94	95	96	97	98	99	100	101	102	103	104	105	106	107	108	109	110	111	112	113	114	115	116	117	118	119	120	121	122	123	124	125	126	127	128	129	130	131	132	133	134	135	136	137	138	139	140	141	142	143	144	145	146	147	148	149	150	151	152	153	154	155	156	157	158	159	160	161	162	163	164	165	166	167	168	169	170	171	172	173	174	175	176	177	178	179	180	181	182	183	184	185	186	187	188	189	190	191	192	193	194	195	196	197	198	199	200	201	202	203	204	205	206	207	208	209	210	211	212	213	214	215	216	217	218	219	220	221	222	223	224	225	226	227	228	229	230	231	232	233	234	235	236	237	238	239	240	241	242	243	244	245	246	247	248	249	250	251	252	253	254	255	256	257	258	259	260	261	262	263	264	265	266	267	268	269	270	271	272	273	274	275	276	277	278	279	280	281	282	283	284	285	286	287	288	289	290	291	292	293	294	295	296	297	298	299	300	301	302	303	304	305	306	307	308	309	310	311	312	313	314	315	316	317	318	319	320	321	322	323	324	325	326	327	328	329	330	331	332	333	334	335	336	337	338	339	340	341	342	343	344	345	346	347	348	349	350	351	352	353	354	355	356	357	358	359	360	361	362	363	364	365	366	367	368	369	370	371	372	373	374	375	376	377	378	379	380	381	382	383	384	385	386	387	388	389	390	391	392	393	394	395	396	397	398	399	400	401	402	403	404	405	406	407	408	409	410	411	412	413	414	415	416	417	418	419	420	421	422	423	424	425	426	427	428	429	430	431	432	433	434	435	436	437	438	439	440	441	442	443	444	445	446	447	448	449	450	451	452	453	454	455	456	457	458	459	460	461	462	463	464	465	466	467	468	469	470	471	472	473	474	475	476	477	478	479	480	481	482	483	484	485	486	487	488	489	490	491	492	493	494	495	496	497	498	499	500	501	502	503	504	505	506	507	508	509	510	511	512	513	514	515	516	517	518	519	520	521	522	523	524	525	526	527	528	529	530	531	532	533	534	535	536	537	538	539	540	541	542	543	544	545	546	547	548	549	550	551	552	553	554	555	556	557	558	559	560	561	562	563	564	565	566	567	568	569	570	571	572	573	574	575	576	577	578	579	580	581	582	583	584	585	586	587	588	589	590	591	592	593	594	595	596	597	598	599	600	601	602	603	604	605	606	607	608	609	610	611	612	613	614	615	616	617	618	619	620	621	622	623	624	625	626	627	628	629	630	631	632	633	634	635	636	637	638	639	640	641	642	643	644	645	646	647	648	649	650	651	652	653	654	655	656	657	658	659	660	661	662	663	664	665	666	667	668	669	670	671	672	673	674	675	676	677	678	679	680	681	682	683	684	685	686	687	688	689	690	691	692	693	694	695	696	697	698	699	700	701	702	703	704	705	706	707	708	709	710	711	712	713	714	715	716	717	718	719	720	721	722	723	724	725	726	727	728	729	730	731	732	733	734	735	736	737	738	739	740	741	742	743	744	745	746	747	748	749	750	751	752	753	754	755	756	757	758	759	760	761	762	763	764	765	766	767	768	769	770	771	772	773	774	775	776	777	778	779	780	781	782	783	784	785	786	787	788	789	790	791	792	793	794	795	796	797	798	799	800	801	802	803	804	805	806	807	808	809	810	811	812	813	814	815	816	817	818	819	820	821	822	823	824	825	826	827	828	829	830	831	832	833	834	835	836	837	838	839	840	841	842	843	844	845	846	847	848	849	850	851	852	853	854	855	856	857	858	859	860	861	862	863	864	865	866	867	868	869	870	871	872	873	874	875	876	877	878	879	880	881	882	883	884	885	886	887	888	889	890	891	892	893	894	895	896	897	898	899	900	901	902	903	904	905	906	907	908	909	910	911	912	913	914	915	916	917	918	919	920	921	922	923	924	925	926	927	928	929	930	931	932	933	934	935	936	937	938	939	940	941	942	943	944	945	946	947	948	949	950	951	952	953	954	955	956	957	958	959	960	961	962	963	964	965	966	967	968	969	970	971	972	973	974	975	976	977	978	979	980	981	982	983	984	985	986	987	988	989	990	991	992	993	994	995	996	997	998	999	1000	1001	1002	1003	1004	1005	1006	1007	1008	1009	1010	1011	1012	1013	1014	1015	1016	1017	1018	1019	1020	1021	1022	1023	1024	1025	1026	1027	1028	1029	1030	1031	1032	1033	1034	1035	1036	1037	1038	1039	1040	1041	1042	1043	1044	1045	1046	1047	1048	1049	1050	1051	1052	1053	1054	1055	1056	1057	1058	1059	1060	1061	1062	1063	1064	1065	1066	1067	1068	1069	1070	1071	1072	1073	1074	1075	1076	1077	1078	1079	1080	1081	1082	1083	1084	1085	1086	1087	1088	1089	1090	1091	1092	1093	1094	1095	1096	1097	1098	1099	1100	1101	1102	1103	1104	1105	1106	1107	1108	1109	1110	1111	1112	1113	1114	1115	1116	1117	1118	1119	1120	1121	1122	1123	1124	1125	1126	1127	1128	1129	1130	1131	1132	1133	1134	1135	1136	1137	1138	1139	1140	1141	1142	1143	1144	1145	1146	1147	1148	1149	1150	1151	1152	1153	1154	1155	1156	1157	1158	1159	1160	1161	1162	1163	1164	1165	1166	1167	1168	1169	1170	1171	1172	1173	1174	1175	1176	1177	1178	1179	1180	1181	1182	1183	1184	1185	1186	1187	1188	1189	1190	1191	1192	1193	1194	1195	1196	1197	1198	1199	1200	1201	1202	1203	1204	1205	1206	1207	1208	1209	1210	1211	1212	1213	1214	1215	1216	1217	1218	1219	1220	1221	1222	1223	1224	1225	1226	1227	1228	1229	1230	1231	1232	1233	1234	1235	1236	1237	1238	1239	1240	1241	1242	1243	1244	1245	1246	1247	1248	1249	1250	1251	1252	1253	1254	1255	1256	1257	1258	1259	1260	1261	1262	1263	1264
<th

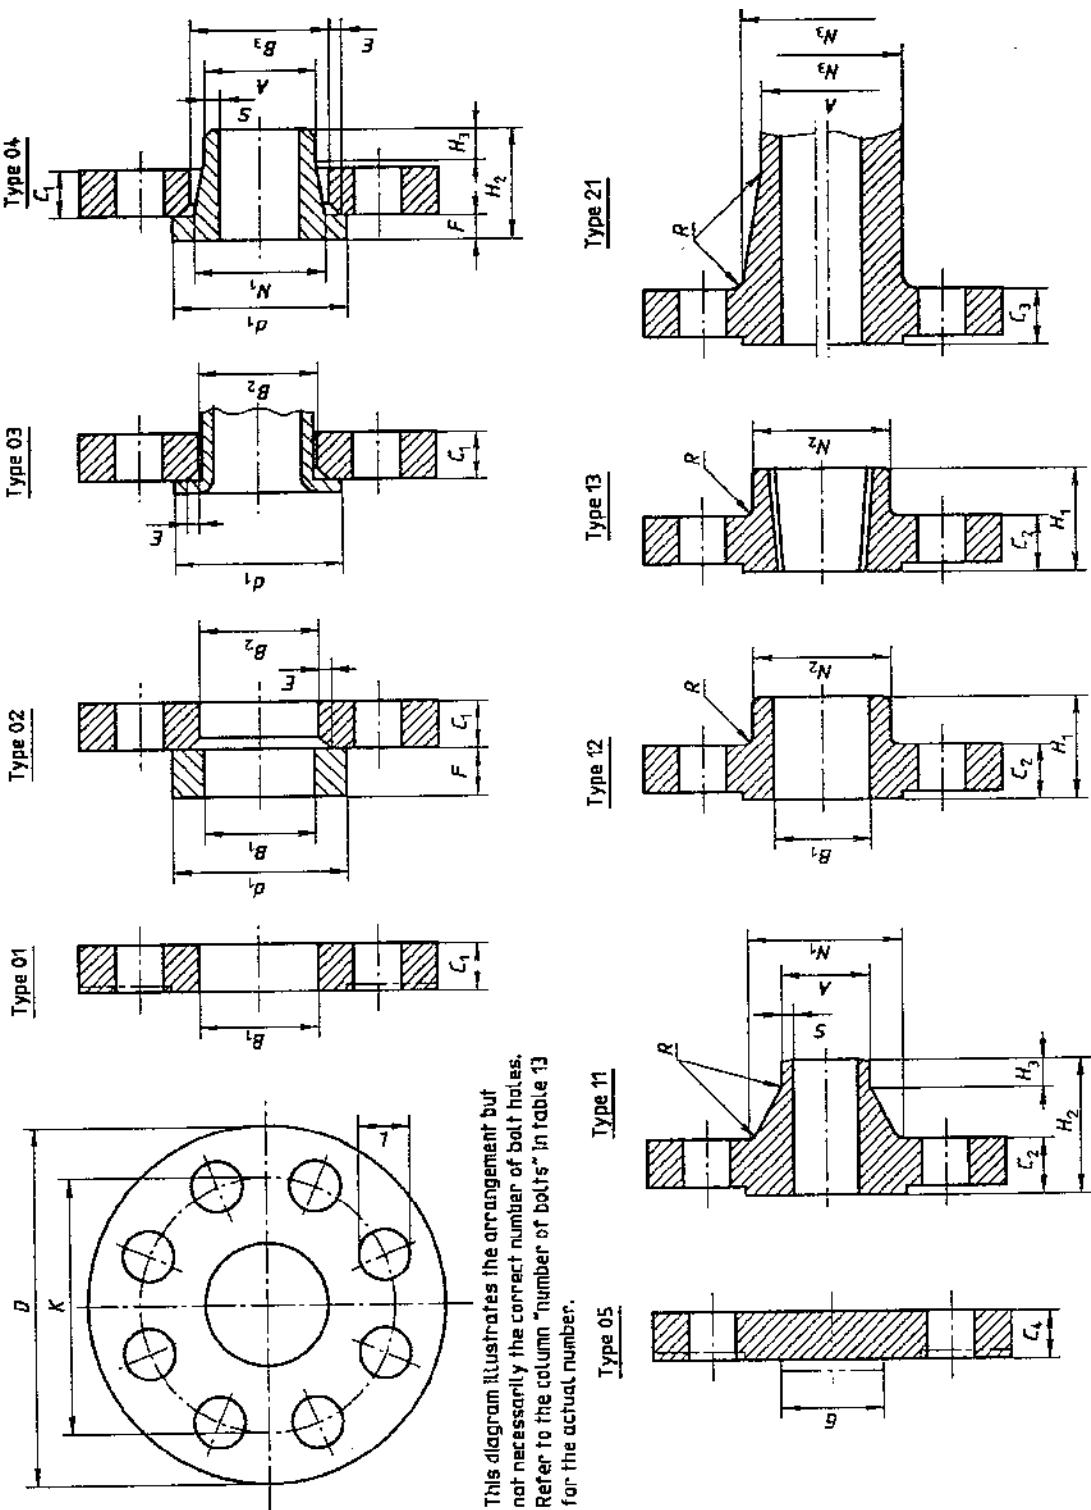

**Table 13 — Dimensions of PN 25 flanges**  
 (See the notes on page 46.)

Nominal size DN	Outside diameter of flange D	Mating dimensions			Bore diameter	Outside diameter of neck A	Shoulder diameter G	Collar thickness F	Chamfer E	Flange thickness C <sub>1</sub>	Flange thickness C <sub>2</sub>	Flange thickness C <sub>3</sub>	Flange thickness C <sub>4</sub>	Neck diameter H <sub>1</sub>	Neck diameter H <sub>2</sub>	Neck diameter H <sub>3</sub>	Corner radius R	Neck thickness S (see note 6)	Nominal size DN			
		Diameter of bolt circle K	Diameter of bolt holes L	Number of bolt holes																		
01, 02, 03, 04, 05, 11, 12, 13, 21		04, 11, 21	01, 02	02, 03	04	01, 02	11, 21	05	02, 03, 04	02, 04	05	12, 13	04, 11	04, 11	N <sub>1</sub>	N <sub>2</sub>	N <sub>3</sub>	21	11, 12, 13, 21	04, 11		
10																				10		
15																				15		
20																				20		
25																				25		
32																				32		
40																				40		
50																				50		
65																				65		
80																				80		
100																				100		
125																				125		
150																				150		
200	360	310	26	12	M24	219,1	221,5	226	250	32	30	30	6	26	190	52	80	16	244	252	8	
250	425	370	29,5	12	M27	273	276,5	281	302	35	32	32	8	26	235	60	88	18	296	310	10	
300	485	430	29,5	16	M27	323,9	327,5	333	356	38	34	34	8	28	285	67	92	18	350	364	10	
350	555	490	32,5	16	M30	355,6	359,5	365	408	42	38	38	8	32	325	72	100	20	398	418	10	
400	620	550	35,5	16	M33	406,4	411	416	462	46	40	40	8	34	375	78	110	20	452	472	10	
450	670	600	35,5	20	M33	457	462	467	510	50	46	46	8	36	425	84	110	20	500	520	12	
500	730	660	35,5	20	M33	508	513,5	519	568	56	48	48	8	38	475	90	125	20	558	580	12	
600	845	770	39	20	M36	610	616,5	622	670	68	58	58	8	40	575	100	125	20	660	684	12	
700	960	875	42	24	M39	711	—	—	—	—	46	50	—	—	—	—	125	20	760	—	780	12
800	1 085	990	48	24	M45	813	—	—	—	—	50	54	—	—	—	135	22	864	—	882	12	
900	1 185	1 090	48	28	M45	914	—	—	—	—	54	58	—	—	—	145	24	968	—	982	12	
1 000	1 320	1 210	55	28	M52	1 016	—	—	—	—	58	62	—	—	—	155	24	1 070	—	1 086	12	
1 200	1 530	1 420	55	32	M52	1 220	—	—	—	—	—	—	—	—	—	70	—	—	—	1 296	12	
1 400	1 755	1 640	60	36	M56	1 420	—	—	—	—	—	—	—	—	—	84	—	—	—	1 508	12	
1 600	1 975	1 860	60	40	M56	1 620	—	—	—	—	—	—	—	—	—	—	—	—	1 726	12		
1 800	2 195	2 070	68	44	M64	1 820	—	—	—	—	—	—	—	—	—	90	—	—	—	1 920	15	
2 000	2 425	2 300	68	48	M64	2 020	—	—	—	—	—	—	—	—	—	96	—	—	—	2 150	15	

**NOTE** — For  $d_1$  and facing dimensions, see table 4.

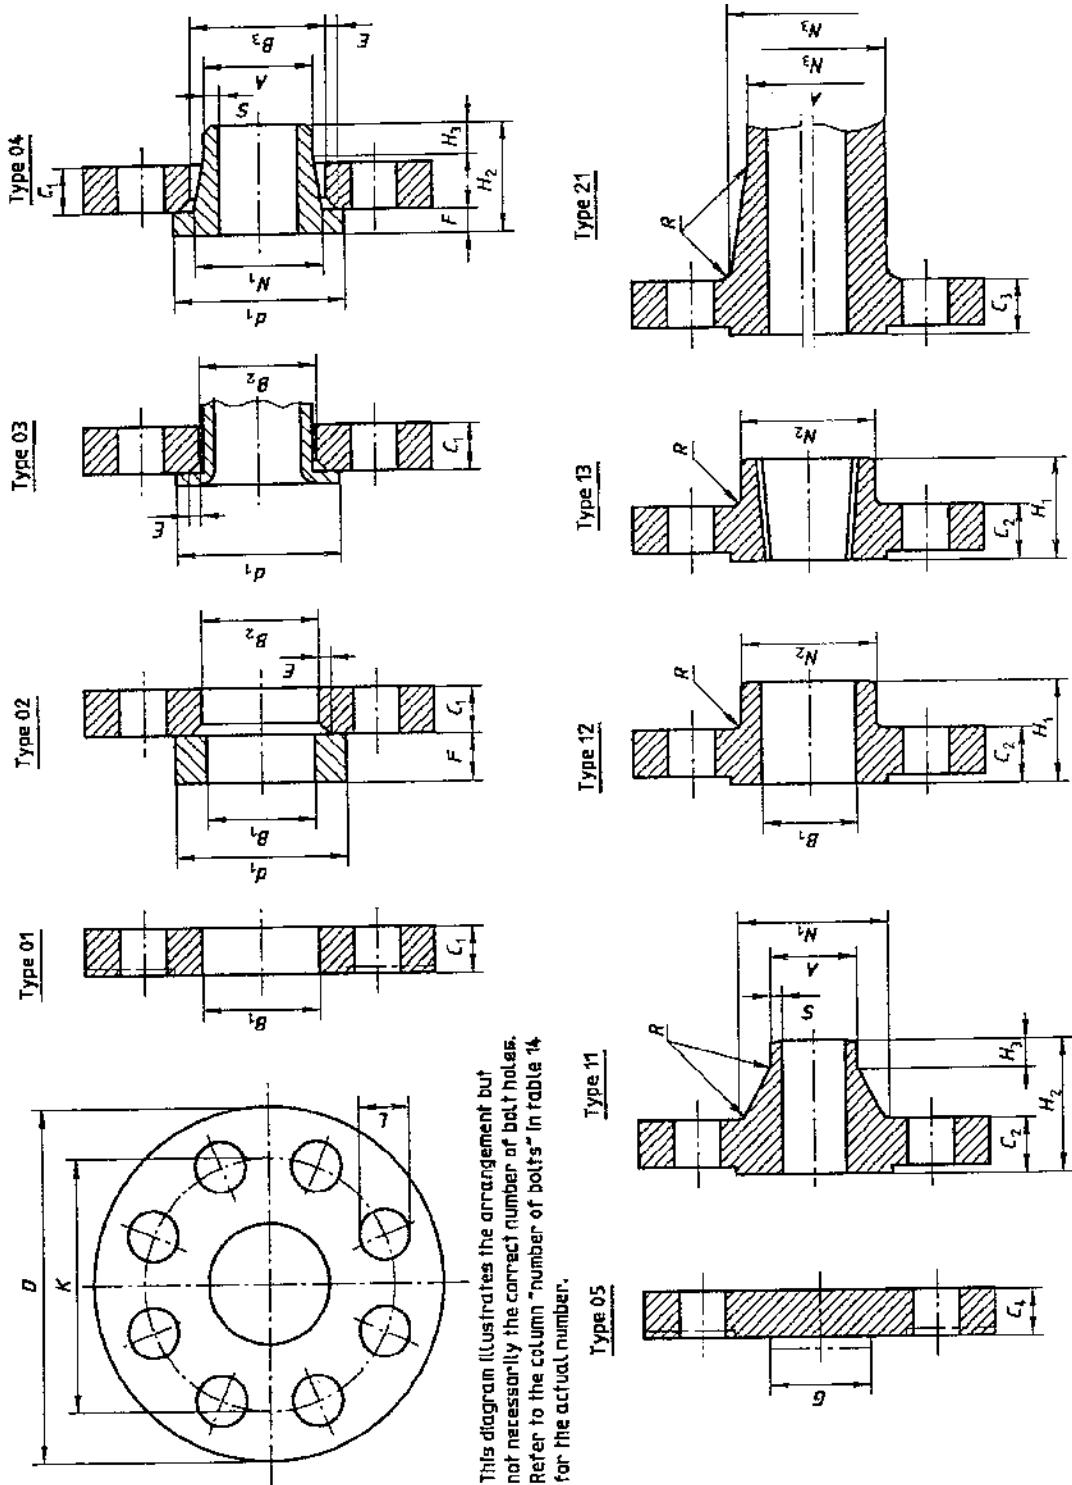


**Table 14 — Dimensions of PN 40 flanges**  
(See the notes on page 46.)

Dimensions in millimetres



Nominal size DN	Outside diameter of flange D	Mating dimensions			Bore diameter A	Outside diameter of neck B <sub>1</sub>	Bore diameter B <sub>2</sub>	Bore diameter B <sub>3</sub>	Flange thickness C <sub>1</sub>	Flange thickness C <sub>2</sub>	Chamfer C <sub>3</sub>	Collar thickness C <sub>4</sub>	Shoulder diameter G	Length of hub H <sub>1</sub>	Length of hub H <sub>2</sub>	Length of hub H <sub>3</sub>	Neck diameter N <sub>1</sub>	Neck diameter N <sub>2</sub>	Neck diameter N <sub>3</sub>	Corner radius R	Neck thickness (see note 6) S	Nominal size DN	
		Diameter of bolt circle K	Diameter of bolt holes L	Bolts Number																			
		0,1, 02, 03, 04, 05, 11, 12, 13, 21			04, 11, 21	01, 02, 03, 04, 05, 02, 03, 04	01, 02, 03	02, 03	04, 01, 11, 21, 02, 03, 04	04, 01, 11, 21, 02, 03, 04	04, 01, 11, 21, 02, 03, 04	04, 01, 11, 21, 02, 03, 04	05	12, 13	04, 01, 11, 21, 02, 03, 04	12, 13	04, 01, 11, 21, 02, 03, 04	12, 13	04, 01, 11, 21, 02, 03, 04	12, 13	04, 01, 11, 21, 02, 03, 04	12, 13	04, 01, 11, 21, 02, 03, 04
10	90	60	14	4	M12	17,2	18	21	31	14	14	3	12	—	22	35	6	28	30	28	3	2,3	10
15	95	65	14	4	M12	21,3	22	25	35	14	14	3	12	—	22	38	6	32	35	32	3	3,2	15
20	105	75	14	4	M12	26,9	27,5	31	42	16	16	4	14	—	26	40	6	40	45	40	4	3,2	20
25	115	85	14	4	M12	33,7	34,5	38	49	16	16	4	14	—	28	40	6	46	52	50	4	3,2	25
32	140	100	18	4	M16	42,4	43,5	47	59	18	18	5	14	—	30	42	6	56	60	56	5	3,6	32
40	150	110	18	4	M16	48,3	49,5	53	67	18	18	5	14	—	32	45	7	64	70	70	5	3,6	40
50	165	125	18	4	M16	60,3	61,5	65	77	20	20	5	16	—	34	48	8	74	84	84	5	4	50
65	185	145	18	8	M16	76,1	77,5	81	96	22	22	6	16	55	38	10	92	104	104	6	5	65	80
80	200	160	18	8	M16	88,9	90,5	94	114	24	24	6	18	70	40	58	12	110	118	120	6	5,6	80
100	235	190	22	8	M20	114,3	116	120	138	26	24	6	20	90	44	65	134	145	142	6	6,3	100	
125	270	220	26	8	M24	139,7	141,5	145	166	28	26	6	22	115	48	68	12	162	170	162	6	6,3	125
150	300	250	26	8	M24	168,3	168,3	170,5	174	30	28	6	24	140	52	75	12	190	200	192	8	7,1	150
200	375	320	29,5	12	M27	219,1	221,5	226	250	36	34	6	28	190	—	88	16	244	—	254	8	8	200
250	450	385	32,5	12	M30	273	276,5	281	312	42	38	8	30	235	—	105	18	306	—	312	10	10	250
300	515	450	32,5	16	M30	323,9	327,5	333	368	48	42	8	34	285	—	115	18	362	—	378	10	10	300
350	580	510	35,5	16	M33	355,6	359,5	365	418	55	46	8	36	325	—	125	20	408	—	432	10	11	350
400	660	585	39	16	M36	406,4	416	472	60	50	8	42	375	—	135	20	462	—	498	10	11	400	
450	685	610	39	20	M36	457	467	510	66	57	8	46	425	—	135	20	500	—	522	12	12	450	
500	755	670	42	20	M39	508	513,5	519	572	72	57	8	50	475	—	140	20	562	—	576	12	12	500
600	890	795	48	20	M45	610	616,5	622	676	84	72	8	54	575	—	150	20	666	—	686	12	12	600

NOTE — For  $d_1$  and facing dimensions, see table 4.

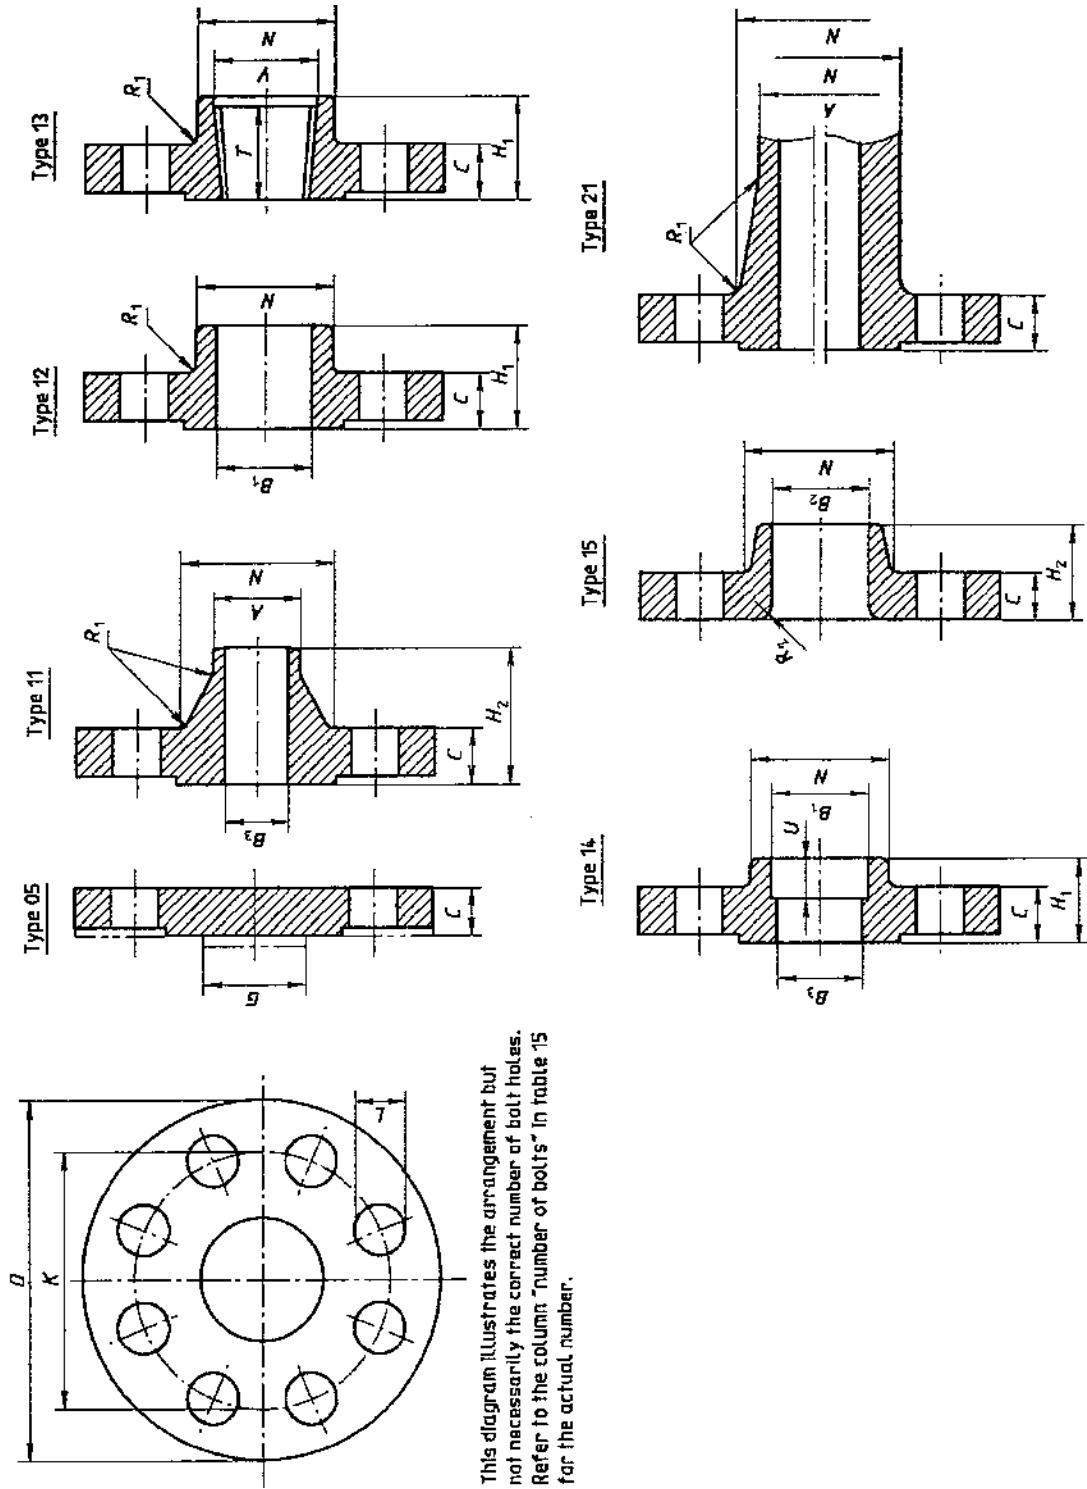

**Table 15 — Dimensions of PN 50 flanges**  
 (See the notes on page 46.)


**NOTE** — For facing dimensions, see tables 5, 6 and 7.

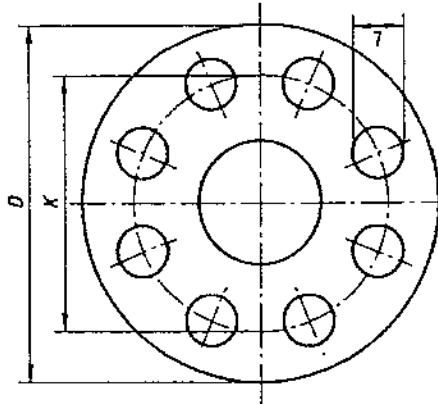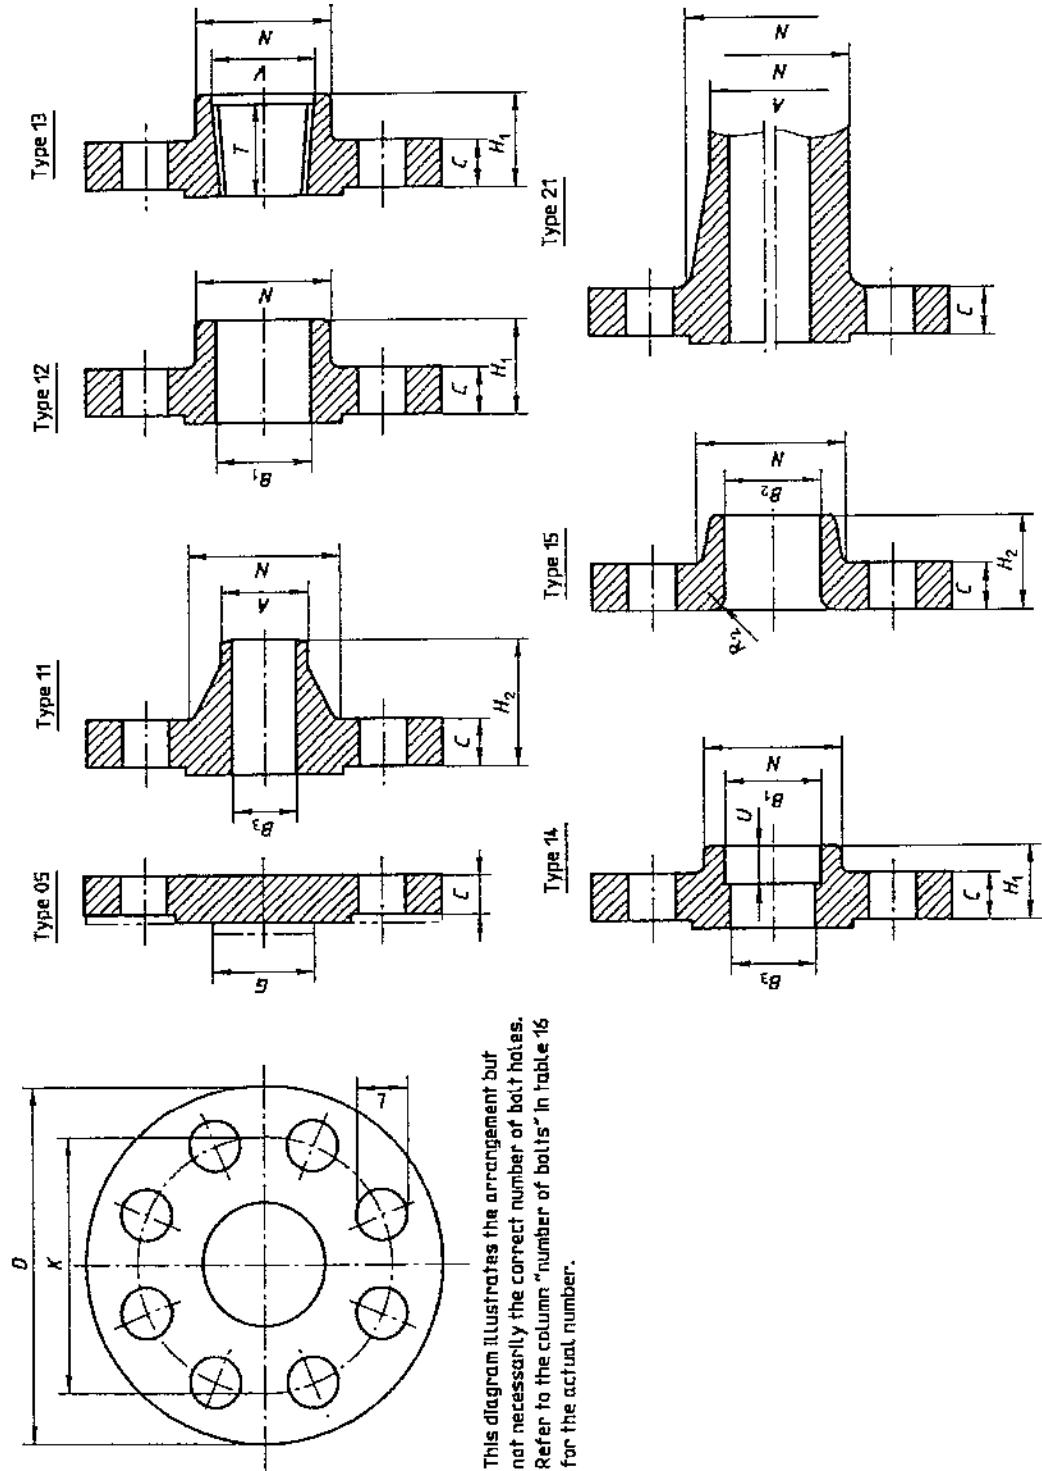

**Table 16 — Dimensions of PN 110 flanges**  
(See the notes on page 46.)


Nominal size	Mating dimensions				Bore diameter (see note 8)	Flange thickness	Shoulder diameter	Length of hub	Neck diameter (see note 9)	Lap radius (at pipe end)	Minimum thread length of threaded flange (see note 5)	Depth of socket	Minimum diameter of counter-bore of threaded flange	Nominal size	Dimensions in millimetres				
	Outside diameter of flange	Diameter of bolt circle	Diameter of bolt holes	Number of bolts															
DN	D	K	L	05, 11, 12, 13, 14, 15, 21	11, 21	12, 14	15	11, 14	05, 11, 12, 13, 14, 15, 21	—	14,5	—	22	52	10	24	15		
15	95	66,5	16	4	M14	21,5	22	23	—	16	4,8	3	16	10	29	20	20		
20	120	82,5	18	4	M16	26,5	28	—	17,5	—	5,4	3	16	11	29	25	25		
25	125	89	18	4	M16	36,5	34,5	—	21	—	6,4	5	21	13	36	32	32		
32	135	98,5	18	4	M16	42	43,5	43,5	—	22,5	—	6,4	5	22	14	45	40		
40	155	114,5	22	4	M20	48,5	49,5	50	—	25,5	—	6	22	16	51	45	40		
50	165	127	18	8	M16	60,5	62	62,5	—	29	—	8	29	17	64	50	50		
65	190	149	22	8	M20	73	74,5	75,5	—	32	—	8	32	19	76,5	65	65		
80	210	168,5	22	8	M20	89	90,5	91,5	—	38	41	79	100	8	35	21	92,5		
100	275	216	26	8	M24	114,5	116	117	—	32	51	46	83	117	10	35	100	100	
125	330	267	29,5	8	M27	141,5	143,5	145	—	38,5	76	54	102	152	11	41	—	118	
150	355	292	29,5	12	M27	168,5	171,5	171,5	—	44,5	102	60	114	189	11	48	—	145	
200	420	349	32,5	12	M30	219	221,5	222	—	48	127	67	114	222	13	51	—	171,5	
250	510	432	35,5	16	M33	273	276	277,5	—	55,5	175	76	133	273	13	57	—	222,5	
300	560	489	35,5	20	M33	324	327	328	—	63,5	222	86	111	343	13	65	—	250	
350	605	527	39	20	M36	355,5	359	360	—	67	273	92	117	156	13	70	—	276,5	
400	685	603	42	20	M39	406,5	410,5	411	—	76,5	302	94	127	165	13	73	—	300	
450	745	654	45	20	M42	457	462	462,5	—	83	349	106	140	178	13	78	—	350	
500	815	724	45	24	M42	508	513	514,5	—	89	394	117	152	184	13	79	—	411,5	
550	870	778	48	24	M45	559	—	—	—	95	438	127	165	197	13	82	—	450	
600	940	838	51	24	M48	609,5	616	616	—	102	53,3	—	—	184	203	13	92	—	500
Flange types affected for DN 650 and above are types 05 and 11 only.																			
650	1 015	914	51	28	M48	—	—	—	—	125	108	—	—	—	—	—	—	650	
700	1 075	965	55	28	M52	—	—	—	—	132	111	—	—	—	—	—	—	700	
750	1 130	1 022	55	28	M56	—	—	—	—	140	114	—	—	—	—	—	—	750	
800	1 195	1 080	60	28	M56	—	—	—	—	148	117	—	—	—	—	—	—	800	
850	1 245	1 130	60	28	M56	—	—	—	—	154	121	—	—	—	—	—	—	850	
900	1 315	1 194	68	28	M64	—	—	—	—	162	124	—	—	—	—	—	—	900	
950	1 270	1 162	60	28	M56	—	—	—	—	156	152	—	—	—	—	—	—	950	
1 000	1 320	1 213	60	32	M56	—	—	—	—	162	159	—	—	—	—	—	—	1 000	
1 050	1 405	1 283	68	28	M64	—	—	—	—	171	168	—	—	—	—	—	—	1 050	
1 100	1 455	1 334	68	32	M64	—	—	—	—	178	173	—	—	—	—	—	—	1 100	
1 150	1 510	1 391	68	32	M64	—	—	—	—	186	179	—	—	—	—	—	—	1 150	
1 200	1 595	1 460	74	32	M70	—	—	—	—	195	189	—	—	—	—	—	—	1 200	
1 250	1 670	1 524	80	28	M76	—	—	—	—	203	197	—	—	—	—	—	—	1 250	
1 300	1 720	1 575	80	32	M76	—	—	—	—	210	203	—	—	—	—	—	—	1 300	
1 350	1 780	1 632	80	32	M76	—	—	—	—	217	210	—	—	—	—	—	—	1 350	
1 400	1 855	1 695	86	32	M82	—	—	—	—	225	217	—	—	—	—	—	—	1 400	
1 450	1 905	1 746	86	32	M82	—	—	—	—	232	222	—	—	—	—	—	—	1 450	
1 500	1 995	1 822	94	28	M90	—	—	—	—	243	233	—	—	—	—	—	—	1 500	

NOTE — For facing dimensions, see tables 5, 6 and 7.

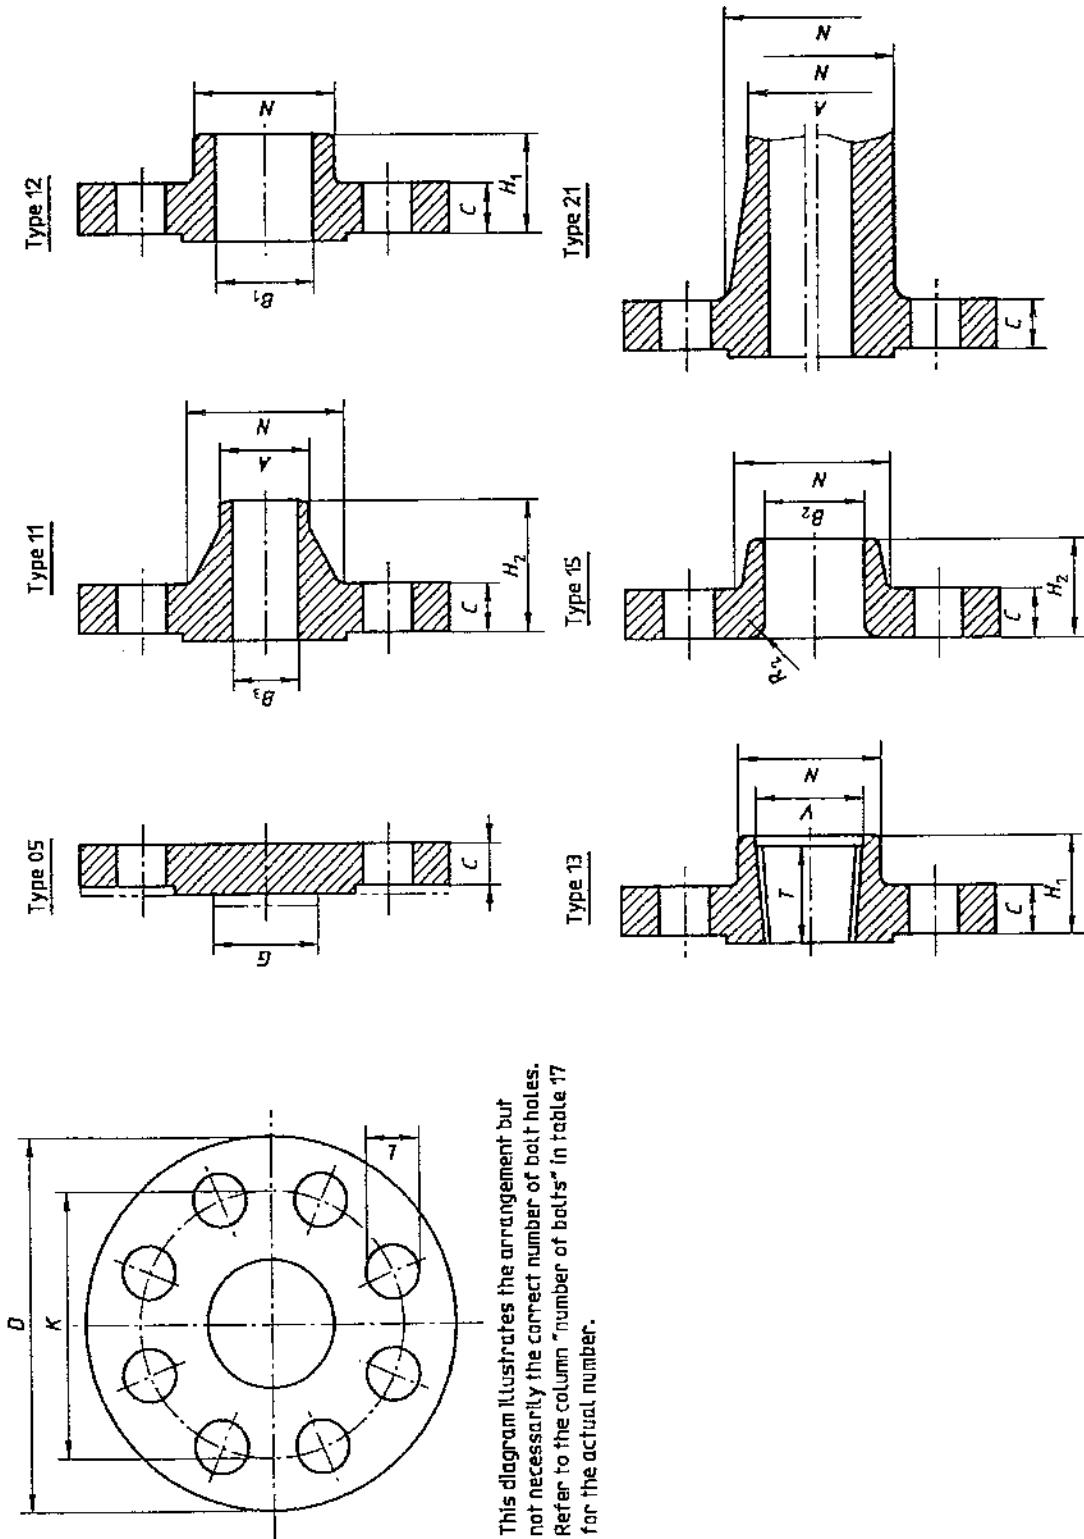

**Table 17 — Dimensions of PN 150 flanges**  
 (See the notes on page 46.)


Nominal size DN	Mating dimensions				Bore diameter (see note 8)	Flange thickness C	Shoulder diameter G	Length of hub H <sub>1</sub>	Length of hub H <sub>2</sub>	Neck diameter N	Lap radius (at pipe end) R <sub>2</sub>	Nominal size DN	Dimensions in millimetres				
	Outside diameter of flange D	Diameter of bolt circle K	Diameter of bolt holes L	Number of bolts B <sub>1</sub>													
15																	
20																	
25																	
32																	
40																	
50																	
65																	
80	240	190,5	26	8	M24	89	90,5	91,5	—	38,5	48	54	102	127	10	42	92
100	290	235	32,5	8	M30	114,5	116	117	—	44,5	73	70	114	159	11	48	118
125	350	279,5	35,5	8	M33	141,5	143,5	144,5	—	51	95	79	127	190	11	54	144,5
150	380	317,5	32,5	12	M30	168,5	170,5	171,5	—	56	121	86	140	235	13	57	171,5
200	470	393,5	39	12	M36	219	221,5	222,5	—	63,5	165	102	114	162	13	64	222,5
250	545	470	39	16	M36	273	276	277,5	—	70	213	108	127	184	13	71	276,5
300	610	533,5	39	20	M36	324	327	328	—	79,5	257	117	143	200	13	76	329
350	640	559	42	20	M39	355,5	359	360	—	86	286	130	156	213	13	83	360,5
400	705	616	45	20	M42	406,5	410,5	411	—	89	381	133	165	216	13	86	411,5
450	785	686	51	20	M48	457	462	462,5	—	102	419	152	191	229	13	89	462
500	855	749,5	55	20	M52	508	513	514,5	—	108	451	159	210	248	13	92	513
600	1 040	901,5	68	20	M64	609,5	616	616	—	140	508	203	292	267	13	102	600
Flange types affected for DN 650 and above are types 05 and 11 only.																	
650	1 085	952	74	20	M70	—	—	—	—	—	160	140	—	—	—	—	—
700	1 165	1 022	80	20	M76	—	—	—	—	171	143	—	—	—	—	—	—
750	1 230	1 086	80	20	M76	—	—	—	—	183	149	—	—	—	—	—	—
800	1 315	1 156	86	20	M82	—	—	—	—	194	159	—	—	—	—	—	—
850	1 395	1 226	86	20	M82	—	—	—	—	205	165	—	—	—	—	—	—
900	1 460	1 289	94	20	M90	—	—	—	—	214	171	—	—	—	—	—	—
950	1 460	1 289	94	20	M90	—	—	—	—	216	190	—	—	—	—	—	—
1 000	1 510	1 340	94	24	M90	—	—	—	—	224	197	—	—	—	—	—	—
1 050	1 560	1 391	94	24	M90	—	—	—	—	232	206	—	—	—	—	—	—
1 100	1 650	1 464	99	24	M95	—	—	—	—	243	214	—	—	—	—	—	—
1 150	1 735	1 537	105	24	M100	—	—	—	—	256	225	—	—	—	—	—	—
1 200	1 785	1 588	105	24	M100	—	—	—	—	264	233	—	—	—	—	—	—
NOTE — For facing dimensions, see tables 5, 6 and 7.																	

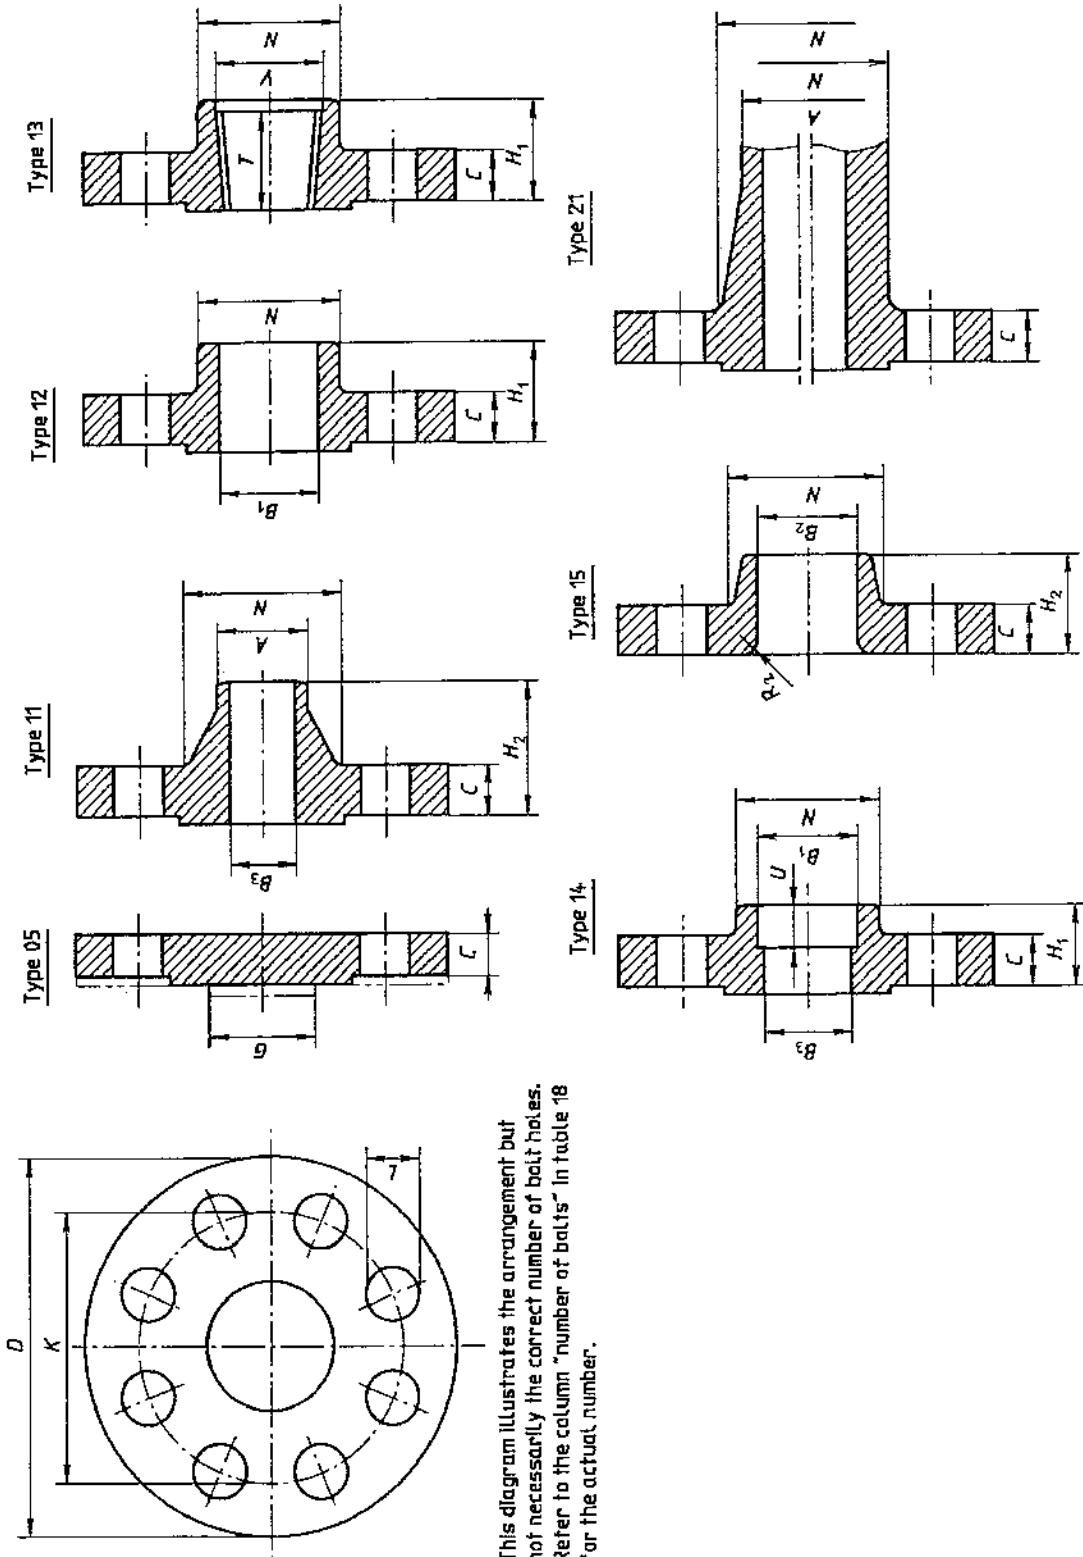

**Table 18 — Dimensions of PN 260 flanges**  
 (See the notes on page 46.)

Nominal size DN	Mating dimensions			Bore diameter (see note 7)	Flange thickness (see note 8)	Shoulder diameter	Length of hub	Neck diameter N	Lap radius (at pipe end) $R_2$	Minimum thread length of threaded flange (see note 5) $T$	Depth of socket	Minimum diameter of counter-bore-threaded flange $V$	Nominal size DN	
	Outside diameter of flange D	Diameter of bolt circle K	Diameter of bolt holes L											
05, 11, 12, 13, 14, 15, 21	11, 21	12, 14	15	11, 14 13, 15, 21	105, 112, 114, 121, 13, 14, 15, 21	05	12, 13, 14	11 14, 15, 21	15	13	10	24	15	
15	120	82,5	22	4	M20	21,5	22	23	—	32	32	3	23	24
20	130	89	22	4	M20	26,5	28	28	—	35	35	3	26	20
25	150	101,5	26	4	M24	33,5	34,5	35	—	41	41	3	29	25
32	160	111	26	4	M24	42	43,5	43,5	—	41	41	5	31	32
40	180	124	29,5	4	M27	48,5	49,5	50	—	44	44	83	70	40
50	215	165	26	8	M24	60,5	62	62,5	—	57	57	105	8	50
65	245	190,5	29,5	8	M27	73	74,5	75,5	—	41,5	32	64	105	65
80	265	203	32,5	8	M30	89	—	91,5	—	48	44	73	117	80
100	310	241,5	35,5	8	M33	114,5	—	117	—	54	66	90	124	100
125	375	292	42	8	M33	141,5	—	144,5	—	73,5	86	105	155	125
150	395	317,5	39	12	M36	168,5	—	171,5	—	83	111	119	171	150
200	485	393,5	45	12	M42	219	—	222	—	92	152	143	213	200
250	585	482,5	51	12	M48	273	—	277,5	—	108	197	159	178	250
300	675	571,5	55	16	M52	324	—	328	—	124	238	181	219	300
350	750	635	60	16	M56	355,5	—	360	—	133,5	263	—	241	350
400	825	705	68	16	M64	406,5	—	411	—	146,5	305	—	260	400
450	915	774,5	74	16	M70	457	—	462,5	—	162	346	—	276	450
500	985	832	80	16	M76	508	—	514,5	—	178	390	—	292	500
600	1 170	990,5	94	16	M90	609,5	—	616	—	203,5	473	—	330	600

NOTE — For facing dimensions, see tables 5 and 7.

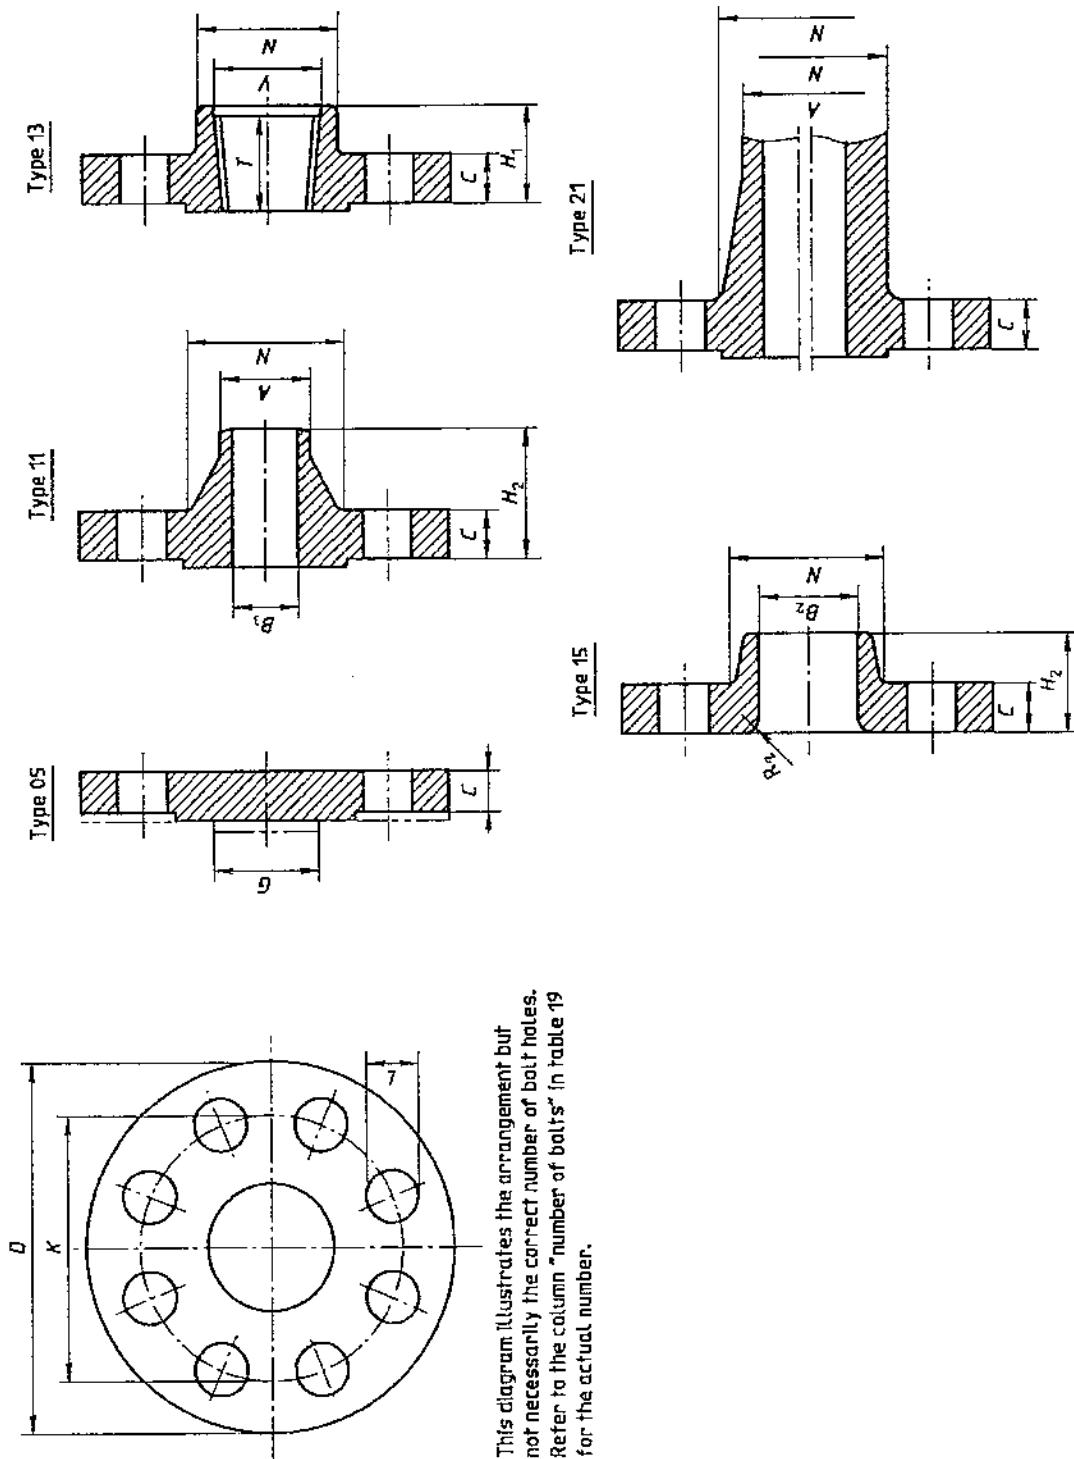

**Table 19—Dimensions of PN 420 flanges**  
(See the notes on page 46.)

Nominal size DN	Mating dimensions				Outside diameter of neck (see note 7)	Bore diameter (see note 8) $B_2 \mid B_3$	Flange thickness C	Shoulder diameter G	Length of hub $H_1 \mid H_2$	Neck diameter N	Lap radius (at pipe end) $R_2$	Minimum thread length of threaded flange (see note 5) $T$	Nominal size DN	Dimensions in millimetres		
	Outside diameter of bolt circle D	Diameter of bolt holes K	Number of bolt holes L	Nominal size M20										15	24	
15	135	89	22	4	M20	21,5	23	—	30,5	—	40	40	3	29	15	
20	140	95	22	4	M20	26,5	28,5	—	32	—	43	43	3	32	20	
25	160	108	26	4	M24	33,5	35	—	35	—	48	48	3	35	25	
32	185	130	29,5	4	M27	42	43,5	—	38,5	—	52	52	5	38	32	
40	205	146	32,5	4	M30	48,5	50	—	44,5	—	60	60	6	44	40	
50	235	171,5	29,5	8	M27	60,5	62,5	—	51	—	70	70	8	51	50	
65	265	197	32,5	8	M30	73	75,5	—	57,5	22	79	79	8	57	65	
80	305	228,5	35,5	8	M33	89	91,5	—	67	32	92	92	10	64	80	
100	355	273	42	8	M39	114,5	117	—	76,5	48	108	108	11	70	100	
125	420	324	48	8	M45	141,5	144,5	—	92,5	67	130	130	11	77	125	
150	485	368,5	55	8	M52	168,5	171,5	—	108	86	152	152	13	83	150	
200	550	438	55	12	M52	219	222	—	127	96	178	178	13	96	200	
250	675	593,5	68	12	M64	273	277,5	—	165,5	159	229	229	13	108	250	
300	760	619	74	12	M70	324	328	—	184,5	193	254	254	13	121	300	

NOTE — For facing dimensions, see tables 5 and 7.

**Notes to tables 8, 9 10, 11, 13 and 14**

- 1 For tolerances, see 2.7 and section 4.
- 2 For facings, see 2.5, figure 6 and table 4.
- 3 For spot-facing, see 2.6.
- 4 For reducing threaded, slip-on and weld neck flanges, see 2.4.4.2.
- 5 For threads in threaded flanges, see 2.4.3.
- 6 The neck thickness dimension  $S$  is applicable to the majority of flanges, but for sizes above DN 600 or for flanges to be used with other pipe wall thicknesses, the neck thickness is subject to agreement between the manufacturer and purchaser.
- 7 The neck diameter  $N_3$  is the theoretical maximum which will permit the use of ISO ring spanners or the fitting, if required, of the normal series of ISO washers (ISO 887) without some form of additional machining such as spot-facing (see 2.6). The washer, if used, may theoretically overlap slightly the corner radius but in practice it is deemed that there is sufficient space to fit the washer satisfactorily.
- 8 The bore diameter  $B$  in sizes generally above DN 600 should be specified by the purchaser.

The bore for a welding neck (type 11) or a socket weld (type 14) flange should be specified by the purchaser if required to differ from the dimensions given in tables 8 to 11, 13 and 14.

9 In respect of threaded flanges, the outside diameters of DN 65, DN 125 and DN 150 pipes should be as shown in the following table.

Dimensions in millimetres

<b>Nominal size DN</b>	<b>Outside diameter</b>	
	threaded to ISO 7-1	threaded to ANSI/ASME B1.20.1
65	76,1	73
125	139,7	141,3
150	165,1	168,3

10 Up to and including nominal size DN 600, the flanges have been recalculated recently according to the relevant German (DIN) calculation method. For this reason it was necessary to increase certain flange thicknesses. Above nominal size DN 600, flange thicknesses remain as they were, but the previous pressure/temperature ratings are no longer applicable (see E.1).

**Notes to tables 12, 15, 16, 17, 18 and 19**

- 1 For tolerances, see 2.7 and section 4.
- 2 For facings, see 2.5, figure 7 and tables 5, 6 and 7.
- 3 For spot-facing, see 2.6.
- 4 For reducing threaded, slip-on and weld neck flanges, see 2.4.4.2.
- 5 For threads in threaded flanges, see 2.4.3.
- 6 Blank flanges may be with or without hubs at the manufacturer's option.
- 7 For welding of unequal wall thicknesses, see the acceptable bevel designs in annex B.
- 8 Dimensions for  $B_3$  correspond to the inside diameter of the pipe as given in ANSI/ASME B36.10 for Standard Wall pipe. The thickness of Standard Wall is the same as Schedule 40 in sizes DN 250 and smaller. Tolerances in table 20 apply.
- 9 When PN 20 and PN 50 flanges are required with flat face, either the full thickness or the thickness with the raised face removed may be furnished. Users are reminded that removing the raised face will make the length through the hub non-standard. See 2.5.2.
- 10 The bore for a welding neck (type 11) or a socket weld (type 14) flange should be specified by the purchaser if required to differ from the dimensions given in tables 12 and 15 to 19.
- 11 In respect of threaded flanges, the outside diameters of DN 65, DN 125 and DN 150 pipes should be as shown in the following table.

Dimensions in millimetres

<b>Nominal size DN</b>	<b>Outside diameter</b>	
	threaded to ISO 7-1	threaded to ANSI/ASME B1.20.1
65	76,1	73
125	139,7	141,3
150	165,1	168,3

- 12 Attention is drawn to D.4 and annex F for DN 300 and above for pipeline applications.
- 13 The  $R_1$  dimension only applies to DN 300 and above for flanges used in pipeline applications.
- 14 Welding end diameters  $A$  given are for general application and not for pipeline applications.

## Section 4: Tolerances

**Table 20 — Tolerances**

Dimensions in millimetres

<b>Dimension</b>	<b>PN</b>	<b>Flange type</b>	<b>Tolerance</b>	<b>Size range</b>
Bore diameter $B_1, B_2, B_3$	All	11, 14 <sup>1)</sup> , 33	+0,5 -1,0	≤ DN 125
			+1,0 -1,5	DN 150 up to and including DN 300
			±2	≥ DN 350
		Other than 11, 14 <sup>1)</sup> and 33	+1 0	≤ DN 125
			+1,5 0	DN 150 up to and including DN 600
Flange thickness $C_1, C_2, C_3$	All	All (machined on both faces)	+2 0	thickness ≤ 18
			+3 0	18 < thickness ≤ 50
			+4 0	thickness > 50
		All (machined on front face only)	+3,5 0	thickness ≤ 18
			+5,5 0	18 < thickness ≤ 50
			+9 0	thickness > 50
Length through hub $H$	All	11	±1,5	≤ DN 250
			±3	DN 300 up to and including DN 600
			±4,5	≥ DN 650
Outside diameter of neck $A$	All	04,11	+2,5 -1,0	≤ DN 150
			+4 -1	DN 200 up to and including DN 600
			+5,5 -1,5	≥ DN 650
Facing diameter $d_1$	2, 5, 6, 10, 16, 25, 40	All	+2 -1	≤ DN 250
			+3 -1	≥ DN 300
			$f_1 = 2$	$f_1 = 7$
			±1	±0,5
			±2	±1
Facing height $f_1$	All	All	1 min.	All
Facing diameters $x_1, x_2, y_1, y_2, y_3$	All	All	±0,5	≤ DN 600
$w, y$	All	All	+0,5 0	≤ DN 600
$x, y$	All	All	0 -0,5	≤ DN 600
Diameter of bolt circle $K$	All	All	±1	bolt sizes M10 to M24
			±1,25	bolt sizes M27 to M33
			±1,5	bolt sizes M36 to M52
			±2	bolt sizes M56 to M95
			±2,5	bolt sizes M100

**Table 20 (concluded)**


Dimensions in millimetres

Dimension	PN	Flange type	Tolerance	Size range		
Centre-to-centre of adjacent bolt holes	All	All	±0,5	bolt sizes M14 to M24		
			±0,625	bolt sizes M27 to M33		
			±0,75	bolt sizes M36 to M52		
			±1	bolt sizes M56 to M95		
			±1,25	bolt sizes M100		
Eccentricity of machined facing diameters	All	All	0,5	≤ DN 65		
			1	DN 80 up to and including DN 150		
			2	DN 200 up to and including DN 500		
			3	≥ DN 600		
Bolting bearing faces shall be parallel with the flange gasket surface within 1°.						
1) Small bore only.						

**Table 21 — Minimum hub radius after back-facing**

Dimensions in millimetres


Flange nominal size	$R_{\min}$ and $R_{1\min}$
Up to and including DN 50	2
Over DN 50 and up to and including DN 200	3
Over DN 200	5

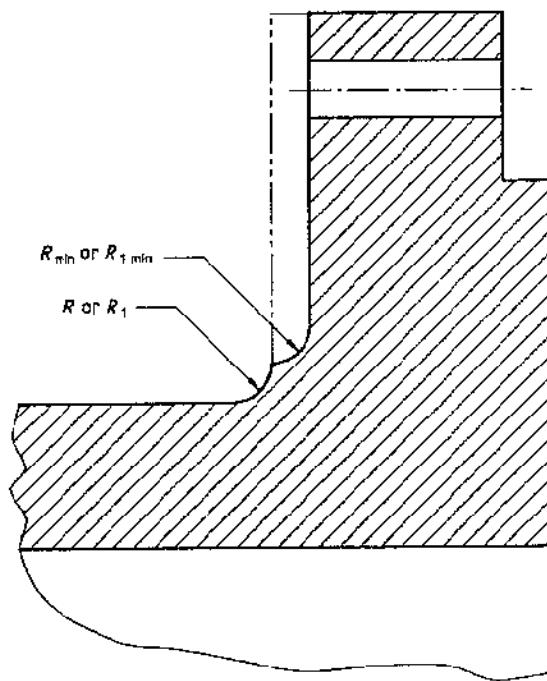NOTE — For dimensions of  $R$  and  $R_1$ , see tables 8 to 19.**Figure 8 — Minimum hub radius after back-facing**

## Annex A (normative)

### **Bevel for specified wall thicknesses from 5 mm to 22 mm inclusive and greater than 22 mm**

Dimensions in millimetres

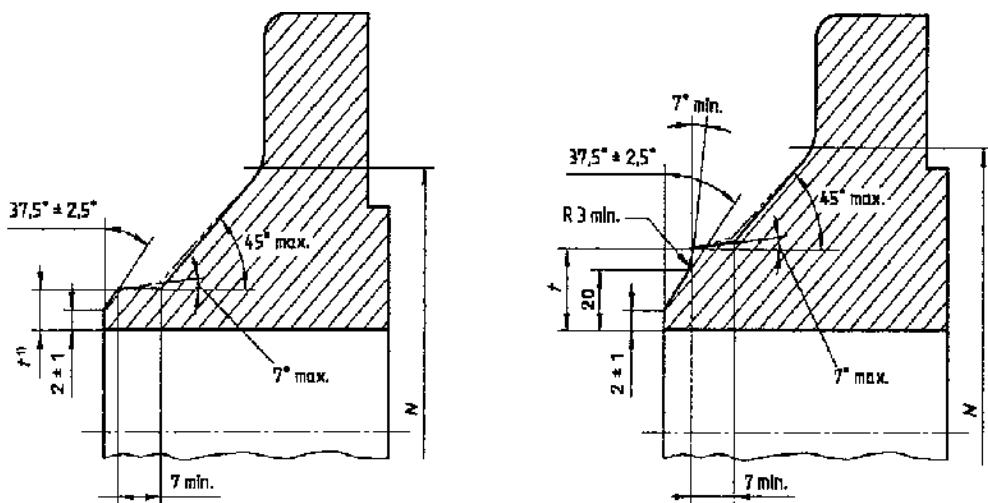

1)  $t$  is the specified wall thickness of pipe, in millimetres

a)  $t$  from 5 mm to 22 mm inclusive

b)  $t$  greater than 22 mm

#### NOTES

1 See 2.4.4.1, 2.4.5.3 and 2.4.6.

2 For flanges required to connect with ferritic steel pipe of nominal wall thickness less than 4,8 mm the welding ends shall be finished to a slight chamfer or shall be square, at the option of the manufacturer.

For flanges required to connect with austenitic stainless steel pipe of nominal wall thickness 3,2 mm or less, the welding ends shall be finished to a slight chamfer.


3 When flanges covered by this part of ISO 7005 are intended for service with light-wall high-strength pipe, the thickness of the hub at the bevel may be greater than that of the pipe to which the flange is joined. Under these conditions a single taper hub may be provided and the outside diameter of the hub at the base (dimension  $N$ ) may be modified.

4 For dimensions of welding-neck thickness (type 11), see the tables in section 3.

**Figure A.1 — Bevel for specified wall thicknesses  $t$**

## Annex B (normative)

### Acceptable bevel designs for unequal wall thicknesses (pipeline applications)

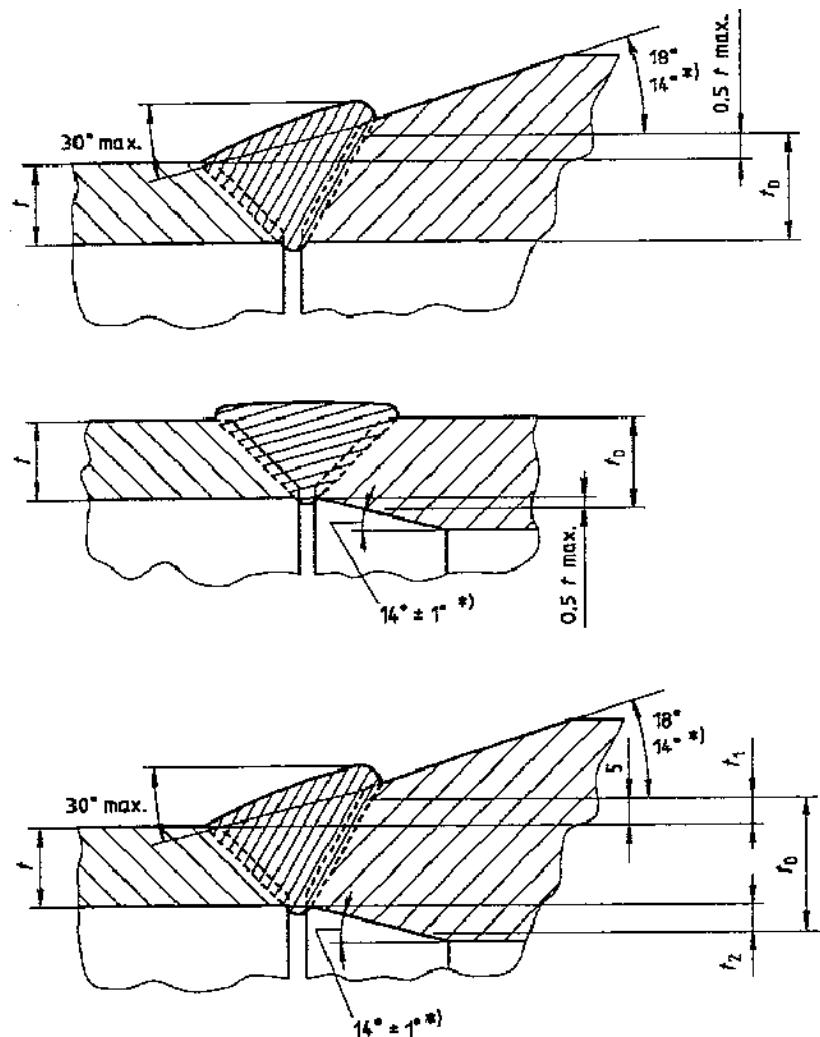

\*) No minimum when materials joined have equal yield strength.

NOTE — None of the dimensions  $t_1$ ,  $t_2$  or  $t_1 + t_2$  shall exceed  $0,5t$ .


**Figure B.1 — Acceptable bevel designs for unequal wall thicknesses**

When the minimum specified yield strengths of the sections to be joined are unequal, the deposited weld metal shall have mechanical properties at least equal to those of the section having the high strength, and the minimum thickness  $t_D$  shall equal at least  $t$  times the ratio of the minimum specified yield strength of the pipe and of the flange, but shall not exceed 1,5  $t$ .


## Annex C (informative)

**Recommended bevel for equal wall thicknesses  $t$  at the end of the flange hub from 5 mm to 22 mm inclusive and greater than 22 mm (pipeline applications)**

Dimensions in millimetres

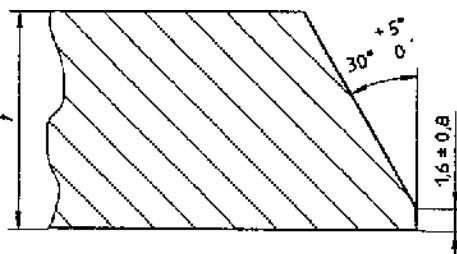

a)  $t$  from 5 mm to 22 mm inclusive (pipeline applications)

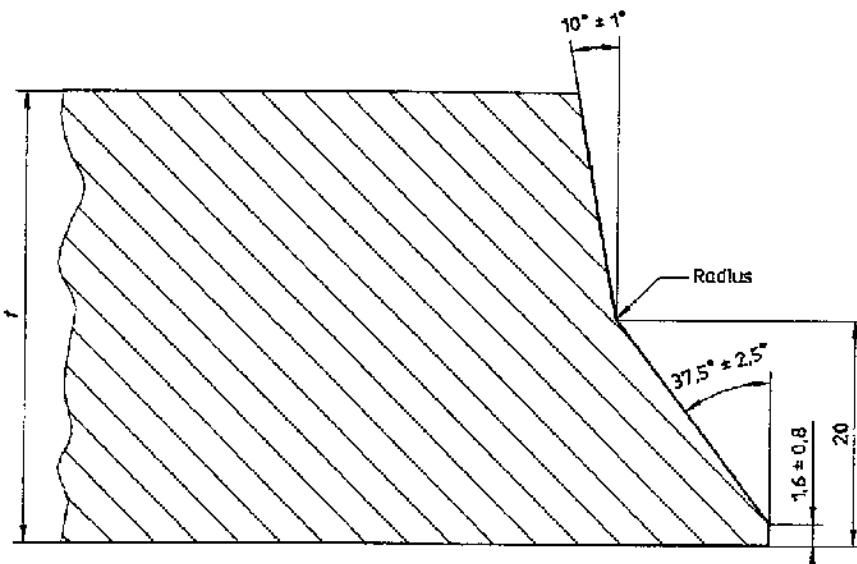

b)  $t$  greater than 22 mm (pipeline applications)

**Figure C.1 — Recommended bevel for equal wall thicknesses  $t$  at the end of the flange hub**

## Annex D (informative)

### Guidance on flange materials

#### **D.1 General**

When work started on this part of ISO 7005 it was decided to refer to the German and American steels which were used for the manufacture of the European and American steel flanges on which this part of ISO 7005 is based. Since then a number of ISO standards have been published, or are in preparation, which specify steels suitable for the manufacture of flanges. However, the complete suite of ISO standards has yet to be published, and therefore the materials specified in this annex are given for guidance only and users are entitled to select other steels from national standards in preference, as deemed necessary. Moreover, if specifying steels not given in this part of ISO 7005, users of this part of ISO 7005 have the responsibility to ensure that the steels are suitable for the PN designations given. In a future edition of this part of ISO 7005, steels from ISO standards only will be specified.

Guidance on pressure/temperature ratings for certain flanges made from the materials given in this annex is given in annex E.

#### **D.2 Range of materials**

Except for pipeline flanges, flanges specified in this part of ISO 7005 may be manufactured from materials selected from tables D.1 and D.2.

NOTE — See also 1.1.

When PN 20, PN 50, PN 110 and PN 150 flanges are specified for pipeline applications, materials may be selected from table D.3.

#### **D.3 Material groupings**

Materials in this part of ISO 7005 are identified by a basic material reference.

#### NOTES

1 Several materials have been placed in any one group with the provision that they give a compatible rating for the flanged joint i.e. materials likely to be used together are capable of maintaining the same rating). In this respect the characteristics of any material in a given group are compatible with the rating for that group. Consequently, ratings for some materials are conservative (see also annex E).

2 The specifications may not be equivalent in all details and therefore may not be equally suitable for all applications.

#### **D.4 Materials for PN 20, PN 50, PN 110 and PN 150 flanges types 05 and 11 for nominal sizes DN 300 and larger for pipeline applications**

The steel used in the manufacture of PN 20, PN 50, PN 110 and PN 150 flanges types 05 and 11 for nominal sizes DN 300 and larger for pipeline applications given in table D.3 should be selected by the manufacturer to meet the following recommendations.

**D.4.1** The 4.A.330 and higher grades of steel for PN 110 and PN 150 flanges should be killed steel.

**D.4.2** The steel used should be suitable for field welding to other flanges, fittings or pipe manufactured to the appropriate International Standards.

**D.4.3** The steel used should have a maximum carbon content of 0,35 % (*m/m*) and a carbon equivalent (C.E.) computed using the following equation:

$$C.E. = C + \frac{Mn}{8} + \frac{Cr + Mo + V}{5} + \frac{Ni + Cu}{15}$$

which should not exceed 0,50, based on check analysis. If the carbon equivalent exceeds 0,50, the acceptance of the flanges should be based on agreement between the purchaser and the manufacturer.

The choice and use of alloying elements, combined with the elements within the limits given above to give the required tensile properties prescribed in D.4.4, should be made by the flange manufacturer and included and reported in the ladle or check analyses to identify the type of steel.

**D.4.4** The steel used should have tensile properties conforming to the requirements given in table D.3 and be capable of meeting the flange manufacturer's design conditions as given in annex F.

The test specimens should be taken from the forgings or, at the manufacturer's option, from the billets or forging bars used to manufacture the finished product, provided that such a test specimen has undergone substantially the same forming and the equivalent heat treatment as the finished flange. The dimensions of the test specimen should be such as to reflect adequately

the heat treatment properties of the hub of the flange. Specimens should be obtained from the midwall of the thinnest section of the hub of the flange or 19 mm from the surface of the test specimen. The orientation of specimens taken from a flange should be longitudinal. If a separate test bar is used, it should be heat treated in a heat treat batch with the flanges it represents.

**D.4.5** The 4.A.290 and higher grades of steel for PN 20, PN 50, PN 110 and PN 150 flanges and the 4.A.250 grade of steel for PN 110 and PN 150 flanges should be normalized or quenched and tempered.

NOTE — It is recognized that the cooling rate in a quenching operation may be slower in the thicker ring section of the flange than in the thinner hub section. Hence, the increase in yield strength due to the quenching operations may be less in the ring section than in the hub section. This factor is accounted for in D.4.6.

**D.4.6** The flange ring should have sufficient pressure capacity for the service based on its strength in the normalized condition. This capacity should be substantiated by design calculations using the allowable design stresses as given in annex F of this part of ISO 7005.

**Table D.1 — Basic properties and reference standards for materials used for PN 2,5, PN 6, PN 10, PN 16, PN 25 and PN 40 flanges**

Description	Group	DIN steel		ISO steel		
		Limiting thickness mm	Original DIN standard and grade	Limiting thickness mm	ISO standard and grade	Service temperature <sup>1)</sup> °C
Casting	1E0	—	DIN 1681 GS-38,3	—	ISO 3755 200-400W	—
Forging		≤ 16 > 16 ≤ 40 > 40 ≤ 63	DIN 17100 RSt 37-2	≤ 63	ISO 2604-1 F8	-10 to 300
Plate		≤ 16 > 16 ≤ 40 > 40 ≤ 63	DIN 17100 RSt 37-2	≤ 63	ISO 630 Fe 360B	-10 to 300
Forging	2E0	60 — —	DIN 2528 C 16.8 C 21 C22.3	—	ISO 2604-1 F9	-10 to 360
Plate		≤ 16 > 16 ≤ 40 > 40 ≤ 60	DIN 17155	≤ 60	ISO 9328-2 PH 235	-10 to 480
Casting	3E0	—	DIN 17245 GS-C25	—	ISO 4991 C23-45AH	—
Forging		≤ 100	DIN 17243 C 22.8	≤ 100	ISO 2604-1 F13	-10 to 420
Plate		> 16 ≤ 40	DIN 17155 H11	≤ 60	ISO 9328-2 PH 265	-10 to 480
Casting	4E0	—	DIN 17245 GS-22 Mo4	—	ISO 4991 C28H	—
Forging		≤ 16 > 16 ≤ 40 > 40 ≤ 60	DIN 17175 15 Mo 3	≤ 60	ISO 2604-1 F26	-10 to 530
Plate		≤ 16 > 16 ≤ 40 > 40 ≤ 60	DIN 17155 15 Mo 3	≤ 60	ISO 9328-2 16 Mo 3	-10 to 530
		—	DIN 2528 16 Mo 5	—	—	—

Table D.1 (continued)

Description	Group	DIN steel		ISO steel		
		Limiting thickness mm	Original DIN standard and grade	Limiting thickness mm	ISO standard and grade	Service temperature <sup>1)</sup> °C
Casting	5E0	—	DIN 17245 GS-17 CrMo 5 5	—	ISO 4991 C32H	—
Forging		≤ 60	DIN 17243 13 CrMo 4 4	≤ 60	ISO 2604-1 F32	-10 to 570
Plate		≤ 16 > 16 ≤ 40 > 40 ≤ 63	DIN 17155 13 CrMo 4 4	≤ 60	ISO 9328-2 14 CrMo 4 5	-10 to 570
Casting	6E0	—	DIN 17245 GS-18 CrMo 9 10	—	ISO 4991 C34BH	—
Forging		—	DIN 17243 10 CrMo 9 10	—	ISO 2604-1 F34	-10 to 600
Plate		≤ 16 > 16 ≤ 40 > 40 ≤ 60	DIN 17155 10 CrMo 9 10	—	ISO 9328-2 13 CrMo 9 10 T1	—
Casting	7E1	30	DIN 17245 GS-10 Ni 19	< 35	ISO 4991 C43L	—
	7E1	35	DIN 17245 GS-10 Ni 14			
Forging	7E1	—	DIN 17280 10 Ni 14	—	—	—
	7E0	—	DIN 17102 TStE 315	—	—	—
	7E0	—	DIN 17102 TStE 355	—	—	—
	7E1	—	DIN 17102 TStE 380	—	ISO 2604-1 F44	—
	7E1	—	DIN 17102 TStE 420	—	—	—
	7E2	—	DIN 17280 X8 Ni 9	—	ISO 2604-1 F45	—
	7E1	—	DIN 17280 12 Ni 19	—	—	—
Plate	7E1	—	DIN 17280 10 Ni 14	—	—	—
	7E0	—	DIN 17102 TStE 315	—	ISO 9328-4 P 315 TN	—
	7E0	—	DIN 17102 TStE 355	—	ISO 9328-4 P 355 TN	—
	7E1	—	DIN 17102 TStE 380	—	ISO 9328-4 PL 390 TN	—
	7E1	—	DIN 17102 TStE 420	—	ISO 9328-4 PL 420 TN	—
	7E2	—	DIN 17280 X 8 Ni 9	—	ISO 9328-3 X 8 Ni 9	—
	7E1	—	DIN 17280 12 Ni 19	—	ISO 9328-3 12 Ni 14 G2	—

Table D.1 (continued)

Description	Group	DIN steel		ISO steel		
		Limiting thickness mm	Original DIN standard and grade	Limiting thickness mm	ISO standard and grade	Service temperature <sup>1)</sup> °C
Forging	8E0	—	DIN 17102 WStE 255	—	—	—
	8E1	—	WStE 285	—	—	—
	8E2	—	WStE 315	—	—	—
	8E3	—	WStE 355	—	—	—
Plate	8E0	—	DIN 17102 WStE 255	—	ISO 9328-4 P 255 TN	—
	8E1	—	WStE 285	—	P 285 TN	—
	8E2	—	WStE 315	—	P 315 TN	—
	8E3	—	WStE 355	—	P 355 TN	—
Casting	9E0	—	DIN 17245 G-X 22 CrMoV 12 1	—	ISO 4991 C40H	—
Forging		≤ 16 > 16 ≤ 40 > 40 ≤ 60	DIN 17175 X 20 CrMoV 12 1	60	ISO 2604-1 F40	—
Casting	10E0	—	—	—	ISO 4991 C46	—
Forging		—	DIN 17440 X 2 CrNi 19 11 X 2 CrNiN 18 10	—	ISO 2604-1 F46	—
Plate		—	DIN 17440 X 2 CrNi 19 11 X 2 CrNiN 18 10	—	ISO 9328-5 — X 2 CrNi 18 10	—196 to 550
Casting	11E0	—	DIN 17445 G-X 6 CrNi 18 9	—	ISO 4991 C47	—
Forging		—	DIN 17440 X 5 CrNi 18 10	—	ISO 2604-1 F47	—196 to 550
Plate		—	DIN 17440 X 5 CrNi 18 9	—	ISO 9328-5 — X 5 CrNi 18 9	—196 to 550
Casting	12E0	—	DIN 17445 G-X 5 CrNiNb 18 9	—	ISO 4991 C50	—
Forging		—	DIN 17440 X 6 CrNiTi 18 10	—	ISO 2604-1 F53	—196 to 550
Plate		—	DIN 17440 X 6 CrNiNb 18 10 X 6 CrNiTi 18 10 X 6 CrNiNb 18 10	—	ISO 2604-1 F50 ISO 9328-5 — X 6 CrNiTi 18 10 X 6 CrNiNb 18 10	— —196 to 550
Casting	13E0	—	DIN 17445 G-X 3 CrMoN 17 13 5	—	ISO 4991 C57 C612C	— —
Forging		—	DIN 17440 X 2 CrNiMo 17 13 2	—	ISO 2604-1 F59	—60 to 550
Plate		13E0	DIN 17440 X 2 CrNiMo 17 13 2	—	ISO 9328-5 — X 2 CrNiMo 17 12	—60 to 550
		13E1	X 2 CrNiMoN 17 12 2	—	X 2 CrNiMoN 17 12	—

Table D.1 (concluded)

Description	Group	DIN steel		ISO steel		
		Limiting thickness mm	Original DIN standard and grade	Limiting thickness mm	ISO standard and grade	Service temperature <sup>1)</sup> °C
Casting	14E0	—	DIN 17445 G-X 6 CrNiMo 18 10	—	ISO 4991 C60 C61	—
Forging		—	DIN 17440 X 5 CrNiMo 17 12 2	—	ISO 2604-1 F62	-60 to 550
Plate		—	DIN 17440 X 5 CrNiMo 17 12 2	—	ISO 9328-5 X 5 CrNiMo 17 12	-60 to 550
Casting	15E0	—	DIN 17445 G-X 5 CrNiMoNb 18 10	—	ISO 4991 C60Nb	—
Forging		—	DIN 17440 X 6 CrNiMoTi 17 12 2	—	ISO 2604-1 F66	-60 to 550
Plate		—	DIN 17440 X 6 CrNiMoTi 17 12 2 X 10 CrNi 18 10	—	ISO 9328-5 X 6 CrNiMoTi 17 12 X 6 CrNiMoNb 17 12	—
Forging	16E0	—	SEW 470 X 7 CrNi 23 14	—	ISO 4955 H14	—
Forging	17E0	—	SEW 470 X 15 CrNiSi 25 20	—	ISO 4955 H15	—
		—	X 12 CrNi 25 21	—	H16	—

1) The upper limiting value indicates that prolonged use above the given temperature is not recommended.

NOTE — The mechanical properties given in the standards referred to should be regarded as the minimum values for which the pressure/temperature ratings given in annex E are valid.

**Table D.2 — Reference standards for materials used for PN 20, PN 50, PN 110, PN 150, PN 260 and PN 420 flanges**

Material group	Description	ASTM specification and grade	Remarks	ISO standard and grade	Limiting thickness mm	Remarks
1A1	Casting	ASTM A216 WCB	1), 2)	ISO 4991 C26 — 52H	—	1), 2)
	Forging	ASTM A105 ASTM A350 LF2	1), 2) 3)	ISO 2604-1 F22  F13 F18	≤ 63  ≤ 63 > 63 ≤ 250	1), 2) 3) 3)
	Plate	ASTM A515 70 ASTM A516 70 ASTM A537 CL1	1), 2) 1), 4) 3)	ISO 9328-2 PH290  PH315  PH355	≤ 60  > 60 ≤ 100  ≤ 100	1), 4) 1), 4) 3)
1A2	Casting	ASTM A216 WCC ASTM A352 LC2 LC3 LCC	1), 2) 3) 3) 3)	ISO 4991 C26 — 52H, N(+T)  C26 — 52L C43L	— —	1), 2) 3) 3)
	Forging	ASTM A350 LF3	3)	ISO 2604-1 F44	≤ 250	3)
	Plate	ASTM A203 B E	1), 2) 1), 2)	ISO 9328-3 12 Ni 14 G1	≤ 50	1), 2)
1A3	Casting	ASTM A352 LCB	1)	ISO 4991 C23 — 46BL	—	1)
	Plate	ASTM A203 A D ASTM A515 65 ASTM A516 65	1), 2) 1), 2) 1), 2) 1), 4)	ISO 9328-2 PH290 PH315 ISO 9328-3 12 Ni 14 G1	≤ 100 > 100 ≤ 50	1), 4) 1), 4) 1), 2)
1A4	Forging	ASTM A350 LF1	3)	ISO 2604-1 F9	≤ 250	3)
	Plate	ASTM A515 60 ASTM A516 60	1), 2) 1), 4)	ISO 9328-2 PH235 PH265 PH290	≤ 40 > 40 ≤ 60 > 60 ≤ 150	1), 4) 1), 4) 1), 4)
1A5	Casting	ASTM A217 WC1 ASTM A325 LC1	2), 5) 3)	ISO 4991 C28H	—	2), 5)
	Forging	ASTM A182 F1	2), 5)	ISO 2604-1 F28	—	2), 5)
	Plate	ASTM A204 A B	2), 5) 2), 5)	ISO 9328-2 16 Mo 3	≤ 60	2), 5)

Table D.2 (continued)

Material group	Description	ASTM specification and grade	Remarks	ISO standard and grade	Limiting thickness mm	Remarks
1A7	Casting	ASTM A217 WC4 WC5	2) 6)	—	—	—
	Forging	ASTM A182 F2	2)	—	—	—
	Plate	ASTM A204 C	4)	—	—	—
1A9	Casting	ASTM A217 WC6	7)	ISO 4991 C32H	—	7)
	Forging	ASTM A182 F11 F12	8) 8)	—	—	—
	Plate	ASTM A387 11 CL2	8)	—	—	—
1A10	Casting	ASTM A217 WC9	7)	ISO 4991 C34AH	—	7)
	Forging	ASTM A182 F22	7)	ISO 2604-1 F34Q	—	8)
	Plate	ASTM A387 22 CL2	8)	ISO 9328-2 13 CrMo 9 10 T2	≤ 100	8)
1A13	Casting	ASTM A217 C5	—	ISO 4991 C37H	—	—
	Forging	ASTM A182 F5 F5a	— —	ISO 2604-1 F37	—	—
1A14	Casting	ASTM A217 C12	—	ISO 4991 C38H	—	—
	Forging	ASTM A182 F9	—	—	—	—
2A1	Casting	ASTM A351 CF8 CF3	— 9)	ISO 4991 C46 C47	— —	9)
	Forging	ASTM A182 F304 F304H	— —	ISO 2604-1 F49	—	—
	Plate	ASTM A240 304 304H	— 9)	ISO 9328-5 X 5 CrNi 18 9	—	—
2A2	Casting	ASTM A351 CF8M CF3M	— 4)	ISO 4991 C57 C61LC C60 C61	— — — —	4) 4) 4) 4)
	Forging	ASTM A182 F316 F316H	— —	ISO 2604-1 F62 F64	— —	—
	Plate	ASTM A240 316 317 316H	— — 4)	ISO 9328-5 X 5 CrNiMo 17 12 — X 7 CrNiMo 17 12	— — —	— — 4)

Table D.2 (concluded)

Material group	Description	ASTM specification and grade	Remarks	ISO standard and grade	Limiting thickness mm	Remarks
2A3	Forging	ASTM A182 F304L F316L	9) 4)	ISO 2604-1 F46 F59	— —	— —
	Plate	ASTM A240 304L 316L	9) 4)	ISO 9328-5 X 2 CrNi 18 10 X 2 CrNiMo 17 12 X 2 CrNiMo 17 13	— — —	9) 4) 4)
2A4	Forging	ASTM A182 F321 F321H	2) —	ISO 2604-1 F53 F54B)	— —	2) —
	Plate	ASTM A240 321 321H	2) —	ISO 9328-5 X 6 CrNiTi 18 10 X 7 CrNiTi 18 10	— —	2) —
2A5	Forging	ASTM A182 F347 F347H F348 F348H	2) — 2) —	ISO 2604-1 F50 F51 — —	— — — —	2) — — —
	Plate	ASTM A240 347 347H 348 348H	2) — 2) —	ISO 9328-5 X 6 CrNiNb 18 10 X 7 CrNiNb 18 10	— — — —	2) — — —
2A6	Casting	ASTM A351 CH8 CH20	— —	— —	— —	— —
	Plate	ASTM A240 309S	—	ISO 4955 H14	—	—
2A7	Casting	ASTM A351 CK20	—	—	—	—
	Forging	ASTM A182 F310	10)	ISO 2604-1 F68	—	10)
	Plate	ASTM A240 310S	10)	ISO 4955 H15	—	10)
1) Permissible but not recommended for prolonged use above about 425°C.						
2) Not to be used over 540°C.						
3) Not to be used over 345°C.						
4) Not to be used over 455°C.						
5) Permissible but not recommended for prolonged use above about 455°C.						
6) Not to be used over 565°C.						
7) Not to be used over 590°C.						
8) Permissible but not recommended for prolonged use above about 590°C.						
9) Not to be used over 425°C.						
10) For service temperature 565°C and above, should be used only when assurance is provided that grain size is not finer than ASTM No. 6.						

**Table D.3 — Materials applicable to tables 12, 15, 16 and 17 covering PN 20, PN 50, PN 110 and PN 150 flanges types 05 and 11 in the size range DN 300 and larger for pipeline applications<sup>1)</sup>**

Material group and grade identification number	Yield point min. N/mm <sup>2</sup>	Tensile strength min. N/mm <sup>2</sup>	Minimum elongation on a length $L_0$ of 50,8 mm
			%
4.A.250	250	410	20
4.A.290	290	410	20
4.A.315	315	410	20
4.A.330	330	430	20
4.A.345	345	440	20
4.A.360	360	460	20
4.A.385	385	470	20
4.A.415	415	520	20
4.A.450	450	530	18
4.A.485	485	550	18

1) See also D.4.

## D.5 Reference documents

ISO 630 : 1980, *Structural steels*.

ISO 2604-1 : 1975, *Steel products for pressure purposes — Quality requirements — Part 1: forgings*.

ISO 3755 : 1991, *Cast carbon steels for general engineering purposes*.

ISO 4955: 1983, *Heat-resisting steels and alloys*.

ISO 4991 :—<sup>1)</sup>, *Steel castings for pressure purposes*.

ISO 9328-1 : 1991, *Steel plates and strips for pressure purposes — Technical delivery conditions — Part 1: General requirements*.

ISO 9328-2 : 1991, *Steel plates and strips for pressure purposes — Technical delivery conditions — Part 2: Unalloyed and low-alloyed steels with specified room temperature and elevated temperature properties*.

ISO 9328-3 : 1991, *Steel plates and strips for pressure purposes — Technical delivery conditions — Part 3: Nickel-alloyed steels with specified low temperature properties*.

ISO 9328-4 : 1991, *Steel plates and strips for pressure purposes — Technical delivery conditions — Part 4: Weldable fine grain steels with high proof stress supplied in the normalized or quenched and tempered condition*.

ISO 9328-5 : 1991, *Steel plates and strips for pressure purposes — Technical delivery conditions — Part 5: Austenitic steels*.

ASTM A 105/A105M-87a, *Specification for forgings, Carbon Steel, for Piping Components*.

ASTM A 182/A182M-88, *Specification for Forged or Rolled Alloy-Steel Pipe Flanges, Forged Fittings, and Valves and Parts for High-Temperature Service*.

ASTM A 203/A203M-82(1988), *Specification for Pressure Vessel Plates, Alloy Steel, Nickel*.

ASTM A 204/A204M-88, *Specification for Pressure Vessel Plates, Alloy Steel, Molybdenum*.

ASTM A 216/A216M-84b, *Specification for Steel Castings, Carbon Suitable for Fusion Welding for High-Temperature Service*.

ASTM A 217/A217M-87, *Specification for Steel Castings, Martensitic Stainless and Alloy, for Pressure-Containing Parts Suitable for High-Temperature Service*.

ASTM A 240-88a, *Specification for Heat-Resisting Chromium and Chromium-Nickel Stainless Steel Plate, Sheet, and Strip for Pressure Vessels*.

ASTM A 325-88a, *Specification for High-Strength Bolts for Structural Steel Joints*.

ASTM A 350/A350M-87a, *Specification for forgings, Carbon and Low-Alloy Steel, Requiring Notch Toughness Testing for Piping Components*.

ASTM A 351/A351M-88, *Specification for Steel Castings, Austenitic, for High-Temperature Service*.

ASTM A 352/A352M-88, *Specification for Steel Castings, Ferritic and Martensitic, for Pressure-Containing Parts Suitable for Low-Temperature Service*.

1) To be published.

ASTM A 387/A387M-88, *Specification for Pressure Vessel Plates, Alloy Steel, Chromium-Molybdenum.*

ASTM A 515/A515M-82(1987), *Specification for Pressure Vessel Plates, Carbon Steel, for Intermediate-and Higher-Temperature Service.*

ASTM A 516/A516M-86, *Specification for Pressure Vessel Plates, Carbon Steel, for Moderate- and Lower-Temperature Service.*

ASTM A 537/A537M-86, *Specification for Pressure Vessel Plates, Heat-treated, Carbon-Manganese-Silicon Steel.*

DIN 1681 : 1985, *Cast steels for general engineering purposes.*

DIN 2528 : 1987, *Flanges; steel flanges ready for use; materials.*

DIN 17100 : 1980, *Steels for general structural purposes-quality standard.*

DIN 17102 : 1983, *Weldable normalized fine grain structural steels; technical delivery conditions for plate strip, wide flats, sections and bars.*

DIN 17155 : 1983, *Creep resistant steel plate and strip; technical delivery conditions.*

DIN 17175 : 1979, *Seamless tubes of heat-resistant steels; technical conditions of delivery.*

DIN 17243 : 1987, *Weldable heat resisting steel forgings and rolled or forged steel bars; technical delivery conditions.*

DIN 17245 : 1987, *Ferritic steel castings with elevated temperature properties; technical delivery conditions.*

DIN 17280 : 1985, *Steels with low temperature toughness; technical delivery conditions for plate, sheet, strip, wide flats, sections, bars and forgings.*

DIN 17440 : 1985, *Stainless steels; technical delivery conditions for plate and sheet, hot rolled strip, wire rod, drawn wire, steel bars, forgings and semi-finished products.*

DIN 17445 : 1984, *Stainless steel castings; technical delivery conditions.*

SEW 470 : 1976, *Heat resisting wrought steels.*

## Annex E (informative)

### Guidance on pressure/temperature ratings

#### **E.1 General**

The pressure/temperature ratings given in this annex apply only to certain flanges made using the materials listed in annex D.

Where given, the pressure/temperature ratings of the materials specified are maximum allowable non-shock working pressures (expressed as gauge pressure in bar) at the temperatures given in the respective tables for the applicable material. Linear interpolation is permitted for intermediate temperatures.

The ratings of the flange materials are given in the following tables.

**Tables E.1 to E.4** — Pressure/temperature ratings for PN 2,5, PN 6, PN 10, PN 16, PN 25 and PN 40 for the material groups given in table D.1 and valid only for flanges of types 05, 11, 12, 13 and 21 in nominal sizes up to and including DN 600.

For all flanges of types 01, 02, 03 and 04 and for types 05, 11, 12, 13 and 21 having nominal sizes greater than DN 600, pressure/temperature ratings applied are the responsibility of the user.

For austenitic stainless steels, pressure/temperature ratings are based on a reference stress of 205 N/mm<sup>2</sup> for the 0,2 % proof stress and a reference stress of 225 N/mm<sup>2</sup> for the 1% proof stress, the rating being given in tables E.3 and E.4 respectively. Two tables of pressure/temperature ratings for austenitic stainless steels are given because some codes of practice for the design of flanged equipment use the 0,2% proof stress value and others use the 1% proof stress value.

**Tables E.5 to E.21** — Pressure/temperature ratings for PN 20, PN 50, PN 110, PN 150, PN 260 and PN 420 for the material groups given in table D.2. The ratings are in accordance with the standard ratings for flanged and butt weld end fittings specified in ANSI/ASME B16.5.

**Table E.22** — Pressure/temperature ratings for PN 20, PN 50, PN 110 and PN 150 for the material groups given in table D.3 for use in pipeline applications in the size range DN 300 and larger for types 05 and 11 only.

**NOTE** — There is not yet in existence a common internationally accepted procedure to evaluate pressure/temperature ratings for flanges. Before introducing tables E.1 to E.22 into national standards, it should be checked whether they comply with the relevant national codes and regulations.

#### **E.2 Rating of flanged joints**

If two flanges in a flanged joint do not have the same pressure/temperature rating, the rating of the joint at any temperature should not exceed the lower of the two flange ratings at that temperature.

#### NOTES

1 The temperature shown for a corresponding pressure rating is considered to be that of the contained fluid. The use of a pressure rating corresponding to a temperature other than that of the contained fluid is the responsibility of the user and is subject to the requirements of any applicable code or regulation.

2 Application of the ratings in this part of ISO 7005 to flanged joints should take into consideration the risk of leakage due to forces and moments developed in the connecting pipework.

3 At temperatures in the creep range, gradual relaxation of flanged joints may progressively reduce bolt loads and the tightness of the joint.

4 At low temperatures some of the materials listed in the rating tables undergo a sufficient decrease in impact resistance that they cannot safely sustain sudden changes in stress or temperature.

5 Owing to the nature of any thread sealant used, additional limitations may be placed on a threaded flange.

6 These notes on service conditions are not intended to be exhaustive.

**Table E.1 — Pressure/temperature (P/T) ratings<sup>1)</sup> for flanges made using material groups 1E0 to 6E0**

PN	Material group	Temperature (°C)												
		0 to 120	150	200	250	300	350	400	425	450	475	500	510	520
Maximum non-shock working pressure (bar)														
2,5	1E0	2,5	2,25	2	1,75	1,5	1,25	0,88						
	2E0	2,5	2,25	2	1,75	1,5	1,38	1,13						
	3E0	2,5	2,45	2,25	2	1,75								
6	1E0	6	5,4	4,8	4,2	3,6	3	2,1						
	2E0	6	5,4	4,8	4,2	3,6	4,2	3,3	2,7					
	3E0	6	5,9	5,7	5,4	4,8								
10	1E0	10	9	8	7	6	5	3,5						
	2E0	10	9	8	7	6	7	5,5						
	3E0	10	9,8	9,5	9	8	7,8	4,5						
	4E0	10	10	10	10	8,7	7,4	7,2	7					
16	1E0	16	14,4	12,8	11,2	9,6	8	5,6						
	2E0	16	14,4	12,8	11,2	9,6	8,8	8,8	7,2					
	3E0	16	15,7	15,2	14,4	12,8	11,2	11,8	11,5	11,2				
	4E0	16	16	16	16	13,9	12,5	14,6	14,2	13,9	13,1	11,8	9,9	7,8
	5E0	16	16	16	16	16	15,2							6,1
25	1E0	25	22,5	20	17,5	15	12,5	8,8						
	2E0	25	22,5	20	17,5	15	17,5	13,8	11,3					
	3E0	25	24,5	23,8	22,5	20	19,5	18,5	18	17,5				
	4E0	25	25	25	25	21,8	23,8	22,8	22,3	21,8	20,5	18,5	15,5	12,3
	5E0	25	25	25	25	25	25	22,8	22,3	21,8	20	13,8	12,5	9,5
	6E0	25	25	25	25	25								9,5
40	1E0	40	36	32	28	24	20	14						
	2E0	40	36	32	28	24	28	22	18					
	3E0	40	39,2	38	36	32	31,2	29,6	28,8	28				
	4E0	40	40	40	40	34,8	38	36,4	35,6	34,8	32,8	29,6	24,8	19,6
	5E0	40	40	40	40	40	40	36,4	35,6	34,8	32	22	20	15,2
	6E0	40	40	40	40	40								

1) Pressure/temperature ratings of flanges PN 2,5, PN 6, PN 10, PN 16, PN 25 and PN 40 are valid only for flanges of types 05, 11, 12, 13 and 21 having nominal sizes up to and including DN 600.

**Table E.2 — Pressure/temperature (P/T) ratings<sup>1)</sup> for flanges made using material groups 7E0 to 9E0**

PN	Material group	Temperature (°C)									
		≤ 20	100	150	200	250	300	350	400	450	500
Maximum non-shock working pressure (bar)											
2,5	7E0	3,5	2,44	2,27	2	1,82	1,56				
	7E1	3,94	2,72	2,5	2,28	2,11	1,89				
	7E2	5,44	4,11	3,91	3,72	3,5	3,33				
	8E0	2,39	2,18	1,97	1,86	1,63	1,31	1,09	0,98		
	8E1	2,72	2,51	2,29	2,07	1,86	1,52	1,31	1,09		
	8E2	3,06	2,72	2,51	2,29	2,07	1,74	1,52	1,31		
	8E3	3,5	3,06	2,83	2,61	2,4	2,18	1,97	1,63		
	9E0	5,44	5,12	4,94	4,78	4,61	4,33	4,22	4	3,67	2,87
											1,48
6	7E0	8,4	5,9	5,4	4,8	4,4	3,8				
	7E1	9,5	6,5	6	5,5	5,1	4,5				
	7E2	13,1	9,9	9,4	8,9	8,4	8				
	8E0	5,7	5,2	4,7	4,5	3,9	3,1	2,6	2,3		
	8E1	6,5	6	5,5	5	4,5	3,7	3,1	2,6		
	8E2	7,3	6,5	6	5,5	5	4,2	3,7	3,1		
	8E3	8,4	7,3	6,8	6,3	5,8	5,2	4,7	3,9		
	9E0	13,1	12,3	11,9	11,5	11,1	10,4	10,1	9,6	8,8	6,9
											3,5
10	7E0	14	9,8	9,1	8	7,3	6,3				
	7E1	15,8	10,9	10	9,1	8,4	7,6				
	7E2	21,8	16,4	15,6	14,9	14	13,3				
	8E0	9,6	8,7	7,9	7,4	6,5	5,2	4,4	3,9		
	8E1	10,9	10	9,2	8,3	7,4	6,1	5,2	4,4		
	8E2	12,2	10,9	10	9,2	8,3	7	6,1	5,2		
	8E3	14	12,2	11,3	10,4	9,6	8,7	7,9	6,5		
	9E0	21,8	20,5	19,8	19,1	18,4	17,3	16,9	16	14,7	11,5
											5,9
16	7E0	22,4	15,6	14,5	12,8	11,7	10				
	7E1	25,2	17,4	16	14,6	13,5	12,1				
	7E2	34,8	26,3	25	23,8	22,4	21,3				
	8E0	15,3	13,9	12,6	11,9	10,5	8,4	7	6,3		
	8E1	17,4	16,1	14,6	13,2	11,9	9,7	8,4	7		
	8E2	19,6	17,4	16,1	14,6	13,2	11,2	9,7	8,4		
	8E3	22,4	19,6	18,1	16,7	15,4	13,9	12,6	10,5		
	9E0	34,8	32,8	31,6	30,6	29,5	27,7	27	25,6	23,5	18,3
											9,5
25	7E0	35	24,4	22,7	20	18,2	15,7				
	7E1	39,4	27,2	25	22,8	21,1	18,9				
	7E2	54,4	41,1	39,1	37,2	35	33,3				
	8E0	23,9	21,8	19,7	18,6	16,3	13,1	10,9	9,8		
	8E1	27,2	25,1	22,9	20,7	18,6	15,2	13,1	10,9		
	8E2	30,6	27,2	25,1	22,9	20,7	17,4	15,2	13,1		
	8E3	35	30,6	28,3	26,1	24	21,8	19,7	16,3		
	9E0	54,4	51,2	49,4	47,8	46,1	43,3	42,2	40	36,7	28,7
											14,8
40	7E0	56	39,1	36,3	32	29,2	25,1				
	7E1	63,1	43,6	40	36,4	33,8	30,2				
	7E2	87,1	65,8	62,6	59,6	56,3	53,3				
	8E0	38,2	34,8	31,5	29,7	26,1	21	17,4	15,6		
	8E1	43,6	40,2	36,6	33,1	29,7	24,4	21	17,4		
	8E2	48,9	43,6	40,2	36,6	33,1	27,9	24,4	21		
	9E0	87,1	81,9	79,1	76,4	73,8	69,3	67,6	64	58,7	45,9
											23,6

1) Pressure/temperature ratings of flanges PN 2,5, PN 6, PN 10, PN 16, PN 25 and PN 40 are valid for flanges of types 05, 11, 12, 13 and 21 having nominal sizes up to and including DN 600.

**Table E.3 — Pressure/temperature (P/T) ratings<sup>1)</sup> for flanges made using austenitic stainless steels  
(based on 0,2% proof stress<sup>2)</sup>, material groups 10E0 to 15E0**

PN	Material group	Temperature (°C)										
		≤ 20	50	100	150	200	250	300	350	400	450	500
Maximum non-shock working pressure (bar)												
2,5	10E0	2	1,8	1,63	1,47	1,31	1,2	1,11	1,04	0,99	0,94	0,9
	10E1	3	2,72	2,28	1,94	1,74	1,61	1,51	1,44	1,39	1,34	1,32
	11E0	2,17	1,97	1,74	1,58	1,41	1,31	1,22	1,16	1,09	1,06	1,02
	12E0	2,22	2,11	1,96	1,86	1,74	1,63	1,51	1,44	1,39	1,34	1,32
	13E0	2,11	2,02	1,84	1,69	1,52	1,41	1,31	1,26	1,2	1,14	1,11
	13E1	3,11	2,78	2,34	2,06	1,86	1,72	1,61	1,56	1,5	1,46	1,43
	14E0	2,28	2,18	1,97	1,8	1,63	1,52	1,41	1,33	1,28	1,24	1,22
	15E0	2,33	2,24	2,06	1,97	1,86	1,74	1,61	1,56	1,5	1,46	1,43
6	10E0	4,8	4,3	3,9	3,5	3,1	2,9	2,7	2,5	2,4	2,3	2,2
	10E1	7,2	6,5	5,5	4,7	4,2	3,9	3,6	3,5	3,3	3,2	3,2
	11E0	5,2	4,7	4,2	3,8	3,4	3,1	2,9	2,8	2,6	2,5	2,5
	12E0	5,3	5,1	4,7	4,5	4,2	3,9	3,6	3,5	3,3	3,2	3,2
	13E0	5,1	4,9	4,4	4,1	3,7	3,4	3,1	3	2,9	2,7	2,7
	13E1	7,5	6,7	5,6	4,9	4,5	4,1	3,9	3,7	3,6	3,5	3,4
	14E0	5,5	5,2	4,7	4,3	3,9	3,7	3,4	3,2	3,1	3	2,9
	15E0	5,6	5,4	4,9	4,7	4,5	4,2	3,9	3,7	3,6	3,5	3,4
10	10E0	8	7,2	6,5	5,9	5,2	4,8	4,4	4,2	4	3,8	3,6
	10E1	12	10,9	9,1	7,8	7	6,4	6	5,8	5,6	5,4	5,3
	11E0	8,7	7,9	7	6,3	5,6	5,2	4,9	4,6	4,4	4,2	4,1
	12E0	8,9	8,4	7,8	7,4	7	6,5	6	5,8	5,6	5,4	5,3
	13E0	8,4	8,1	7,4	6,8	6,1	5,6	5,2	5	4,8	4,6	4,4
	13E1	12,4	11,1	9,4	8,2	7,4	6,9	6,4	6,2	6	5,8	5,7
	14E0	9,1	8,7	7,9	7,2	6,5	6,1	5,6	5,3	5,1	4,9	4,9
	15E0	9,3	9	8,2	7,9	7,4	7	6,4	6,2	6	5,8	5,7
16	10E0	12,8	11,5	10,5	9,4	8,4	7,7	7,1	6,7	6,3	6	5,8
	10E1	19,2	17,4	14,6	12,4	11,2	10,3	9,7	9,2	8,9	8,6	8,5
	11E0	13,9	12,6	11,2	10,1	9	8,4	7,8	7,4	7	6,8	6,5
	12E0	14,2	13,5	12,5	11,9	11,2	10,5	9,7	9,2	8,9	8,6	8,5
	13E0	13,5	12,9	11,8	10,8	9,7	9	8,4	8	7,7	7,3	7,1
	13E1	19,9	17,8	15	13,2	11,9	11	10,3	10	9,6	9,3	9,2
	14E0	14,6	13,9	12,6	11,5	10,5	9,7	9	8,5	8,2	8	7,8
	15E0	14,9	14,4	13,2	12,6	11,9	11,2	10,3	10	9,6	9,3	9,2
25	10E0	20	18	16,3	14,7	13,1	12	11,1	10,4	9,9	9,4	9
	10E1	30	27,2	22,8	19,4	17,4	16,1	15,1	14,4	13,9	13,4	13,2
	11E0	21,7	19,7	17,4	15,8	14,1	13,1	12,2	11,6	10,9	10,6	10,2
	12E0	22,2	21,1	19,6	18,6	17,4	16,3	15,1	14,4	13,9	13,4	13,2
	13E0	21,1	20,2	18,4	16,9	15,2	14,1	13,1	12,6	12	11,4	11,1
	13E1	31,1	27,8	23,4	20,6	18,6	17,2	16,1	15,6	15	14,6	14,3
	14E0	22,8	21,8	19,7	18	16,3	15,2	14,1	13,3	12,8	12,4	12,2
	15E0	23,3	22,4	20,6	19,7	18,6	17,4	16,1	15,6	15	14,6	14,3
40	10E0	32	28,8	26,1	23,5	21	19,2	17,8	16,7	15,8	15	14,4
	10E1	48	43,6	36,4	31,1	27,9	25,8	24,2	23,1	22,2	21,5	21,2
	11E0	34,7	31,5	27,9	25,2	22,6	21	19,6	18,5	17,4	16,9	16,4
	12E0	35,6	33,8	31,3	29,7	27,9	26,1	24,2	23,1	22,2	21,5	21,2
	13E0	33,8	32,4	29,5	27	24,4	22,6	21	20,1	19,2	18,3	17,8
	13E1	49,8	44,4	37,5	32,9	29,7	27,6	25,8	24,9	24	32,3	22,9
	14E0	36,4	34,8	31,5	28,8	26,1	24,4	22,6	21,3	20,4	19,9	19,6
	15E0	37,3	35,9	32,9	31,5	29,7	27,9	25,8	24,9	24	23,3	22,9

1) Pressure/temperature ratings of flanges PN 2,5, PN 6, PN 10, PN 16, PN 25 and PN 40 are valid only for flanges of types 05, 11, 12, 13 and 21 having nominal sizes up to and including DN 600.

2) Based on a reference stress of 205 N/mm<sup>2</sup>.

**Table E.4 — Pressure/temperature (P/T) ratings<sup>1)</sup> for flanges made using austenitic stainless steels  
(based on 1% proof stress<sup>2)</sup>, material groups 10E0 to 15E0**

PN	Material group	Temperature (°C)										
		≤ 20	50	100	150	200	250	300	350	400	450	500
Maximum non-shock working pressure (bar)												
2,5	10E0	2,39	2,23	2,01	1,8	1,63	1,52	1,41	1,34	1,29	1,24	1,21
	10E1	3,39	3,11	2,67	2,33	2,08	1,94	1,85	1,79	1,73	1,69	1,66
	11E0	2,56	2,34	2,12	1,91	1,74	1,61	1,5	1,43	1,39	1,36	1,33
	12E0	2,61	2,47	2,31	2,17	2,06	1,94	1,86	1,79	1,73	1,69	1,66
	13E0	2,5	2,41	2,21	2,01	1,86	1,74	1,61	1,54	1,5	1,44	1,42
	13E1	3,5	3,16	2,73	2,42	2,2	2,03	1,94	1,88	1,82	1,78	1,76
	14E0	2,67	2,56	2,34	2,12	1,97	1,86	1,73	1,67	1,6	1,57	1,54
	15E0	2,72	2,6	2,42	2,29	2,18	2,07	1,94	1,88	1,82	1,78	1,76
6	10E0	5,7	5,4	4,8	4,3	3,9	3,7	3,4	3,2	3,1	3	2,9
	10E1	8,1	7,5	6,4	5,6	5	4,7	4,5	4,3	4,2	4,1	4
	11E0	6,1	5,6	5,1	4,6	4,2	3,9	3,6	3,4	3,3	3,3	3,2
	12E0	6,3	5,9	5,5	5,2	4,9	4,7	4,5	4,3	4,2	4,1	4
	13E0	6	5,8	5,3	4,8	4,5	4,2	3,9	3,7	3,6	3,5	3,4
	13E1	8,4	7,6	6,6	5,8	5,3	4,9	4,7	4,5	4,4	4,3	4,2
	14E0	6,4	6,1	5,6	5,1	4,7	4,5	4,2	4	3,8	3,8	3,7
	15E0	6,5	6,2	5,8	5,5	5,2	5	4,7	4,5	4,4	4,3	4,2
10	10E0	9,6	8,9	8	7,2	6,5	6,1	5,6	5,4	5,2	5	4,8
	10E1	13,6	12,4	10,7	9,3	8,3	7,8	7,4	7,2	6,9	6,8	6,6
	11E0	10,2	9,4	8,5	7,6	7	6,4	6	5,7	5,6	5,4	5,3
	12E0	10,4	9,9	9,2	8,7	8,2	7,8	7,4	7,2	6,9	6,8	6,6
	13E0	10	9,6	8,8	8	7,4	7	6,4	6,2	6	5,8	5,7
	13E1	14	12,6	10,9	9,7	8,8	8,1	7,8	7,5	7,3	7,1	7
	14E0	10,7	10,2	9,4	8,5	7,9	7,4	6,9	6,7	6,4	6,3	6,2
	15E0	10,9	10,4	9,7	9,2	8,7	8,3	7,8	7,5	7,3	7,1	7
16	10E0	15,3	14,3	12,9	11,5	10,5	9,7	9	8,6	8,2	8	7,8
	10E1	21,7	19,9	17,1	14,9	13,3	12,4	11,9	11,4	11,1	10,8	10,6
	11E0	16,4	15	13,6	12,2	11,2	10,3	9,6	9,2	8,9	8,7	8,5
	12E0	16,7	15,8	14,8	13,9	13,2	12,4	11,9	11,4	11,1	10,8	10,6
	13E0	16	15,4	14,2	12,9	11,9	11,2	10,3	9,9	9,6	9,2	9,1
	13E1	22,4	20,2	17,5	15,5	14,1	13	12,4	12	11,7	11,4	11,2
	14E0	17,1	16,4	15	13,6	12,6	11,9	11,1	10,7	10,2	10	9,9
	15E0	17,4	16,6	15,5	14,6	13,9	13,2	12,4	12	11,7	11,4	11,2
25	10E0	23,9	22,3	20,1	18	16,3	15,2	14,1	13,4	12,9	12,4	12,1
	10E1	33,9	31,1	26,7	23,3	20,8	19,4	18,5	17,9	17,3	16,9	16,6
	11E0	25,6	23,4	21,2	19,1	17,4	16,1	15	14,3	13,9	13,6	13,3
	12E0	26,1	24,7	23,1	21,7	20,6	19,4	18,6	17,9	17,3	16,9	16,6
	13E0	25	24,1	22,1	20,1	18,6	17,4	16,1	15,4	15	14,4	14,2
	13E1	35	31,6	27,3	24,2	22	20,3	19,4	18,8	18,2	17,8	17,6
	14E0	26,7	25,6	23,4	21,2	19,7	18,6	17,3	16,7	16	15,7	15,4
	15E0	27,2	26	24,2	22,9	21,8	20,7	19,4	18,8	18,2	17,8	17,6
40	10E0	38,2	35,7	32,2	28,8	26,1	24,4	22,6	21,5	20,6	19,9	19,4
	10E1	54,2	49,8	42,7	37,3	33,2	31,1	29,7	28,6	27,7	27	26,5
	11E0	40,9	37,5	34	30,6	27,9	25,8	24	22,9	22,2	21,7	21,3
	12E0	41,8	39,5	37	34,7	32,9	31,1	29,7	28,6	27,7	27	26,5
	13E0	40	38,6	35,4	32,2	29,7	27,9	25,8	24,7	24	23,1	22,8
	13E1	56	50,5	43,7	38,8	35,2	32,5	31,1	30	29,2	28,4	28,1
	14E0	42,7	40,9	37,5	34	31,5	29,7	27,7	26,7	25,6	25,1	24,7
	15E0	43,6	41,6	38,8	36,6	34,8	33,1	31,1	30	29,2	28,4	28,1

1) Pressure/temperature ratings of flanges PN 2,5, PN 6, PN 10, PN 16, PN 25 and PN 40 are valid only for flanges of types 05, 11, 12, 13 and 21 having nominal sizes up to and including DN 600.

2) Based on a reference stress of 225 N/mm<sup>2</sup>.

**Table E.5 — Pressure/temperature (P/T) ratings for flanges made using group 1A1 materials**

Temperature (°C)	Maximum non-shock working pressure (bar)					
	PN 20	PN 50	PN 110	PN 150	PN 260	PN 420
-29 to 38	19,6	51,1	102,1	153,2	255,3	425,5
50	19,2	50,1	100,2	150,2	250,4	417,3
100	17,7	46,4	92,8	139,1	231,9	386,5
150	15,8	45,2	90,5	135,7	226,1	376,9
200	14	43,8	87,6	131,5	219,1	365,2
250	12,1	41,7	83,4	125,2	208,6	347,7
300	10,2	38,7	77,5	116,2	193,7	322,8
350	8,4	37	73,9	110,9	184,8	308
375	7,4	36,5	72,9	109,4	182,3	303,9
400	6,5	34,5	69	103,5	172,5	287,5
425	5,6	28,8	57,5	86,3	143,8	239,6
450	4,7	20	40,1	60,1	100,2	166,9
475	3,7	13,5	27,1	40,6	67,7	112,9
500	2,8	8,8	17,6	26,4	44	73,3
525	1,9	5,2	10,4	15,5	25,9	43,2
540	1,3	3,3	6,5	9,8	16,3	27,2

NOTE — Consult table D.2 and the notes to table D.2 for limitations on use.

**Table E.6 — Pressure/temperature (P/T) ratings for flanges made using group 1A2 materials**

Temperature (°C)	Maximum non-shock working pressure (bar)					
	PN 20	PN 50	PN 110	PN 150	PN 260	PN 420
-29 to 38	20	51,7	103,4	155,2	258,6	431
50	19,2	51,7	103,4	155,2	258,6	431
100	17,7	51,5	103,1	154,6	257,7	429,5
150	15,8	50,2	100,4	150,6	251	418,3
200	14	48,8	97,6	146,4	243,9	406,6
250	12,1	46,3	92,7	139	231,7	386,1
300	10,2	42,4	84,9	127,3	212,1	353,5
350	8,4	40,2	80,5	120,7	201,2	335,3
375	7,4	38,8	77,6	116,4	194	323,4
400	6,5	34,5	69	103,5	172,5	287,5
425	5,6	28,8	57,5	86,3	143,8	239,6
450	4,7	20	40,1	60,1	100,2	166,9
475	3,7	13,5	27,1	40,6	67,7	112,9
500	2,8	8,8	17,6	26,4	44	73,3
525	1,9	5,2	10,4	15,5	25,9	43,2
540	1,3	3,3	6,5	9,8	16,3	27,2

NOTE — Consult table D.2 and the notes to table D.2 for limitations on use.

**Table E.7 — Pressure/temperature (P/T) ratings for flanges made using group 1A3 materials**

Temperature (°C)	Maximum non-shock working pressure (bar)					
	PN 20	PN 50	PN 110	PN 150	PN 260	PN 420
-29 to 38	18,4	47,9	95,7	143,6	239,4	398,9
50	18,1	47,3	94,6	141,9	236,5	394,2
100	17,3	45,1	90,2	135,3	225,5	375,9
150	15,8	44	87,9	131,9	219,8	366,3
200	14	42,7	85,4	128	213,4	355,6
250	12,1	40,6	81,2	121,8	202,9	338,2
300	10,2	37,7	75,4	113,1	188,5	314,2
350	8,4	36	71,9	107,9	179,8	299,7
375	7,4	35,3	70,6	105,9	176,6	294,3
400	6,5	32,4	64,8	97,2	162	270
425	5,6	27,3	54,6	81,9	136,5	227,5
450	4,7	19,8	39,6	59,4	99	165
475	3,7	13,5	27,1	40,6	67,7	112,9
500	2,8	8,8	17,6	26,4	44	73,3
525	1,9	5,2	10,4	15,5	25,9	43,2
540	1,3	3,3	6,5	9,8	16,3	27,2

NOTE — Consult table D.2 and the notes to table D.2 for limitations on use.

**Table E.8 — Pressure/temperature (P/T) ratings for flanges made using group 1A4 materials**

Temperature (°C)	Maximum non-shock working pressure (bar)					
	PN 20	PN 50	PN 110	PN 150	PN 260	PN 420
-29 to 38	16,3	42,5	85,1	127,6	212,7	354,6
50	16	41,7	83,4	125,2	208,6	347,7
100	14,8	38,6	77,2	115,8	193,1	321,8
150	14,5	37,7	75,4	113,1	188,6	314,3
200	14	36,6	73,1	109,7	182,8	304,7
250	12,1	34,7	69,4	104,1	173,6	289,3
300	10,2	32,3	64,6	96,9	161,5	269,1
350	8,4	30,9	61,9	92,8	154,6	257,7
375	7,4	30,9	61,7	92,6	154,3	275,2
400	6,5	30,3	60,6	90,9	151,5	252,5
425	5,6	25,8	51,6	77,4	128,9	214,9
450	4,7	19,6	39,2	58,7	97,9	163,2
475	3,7	13,5	27,1	40,6	67,7	112,9
500	2,8	8,8	17,6	26,4	44	73,3
525	1,9	5,2	10,4	15,5	25,9	43,2
540	1,3	3,3	6,5	9,8	16,3	27,2

NOTE — Consult table D.2 and the notes to table D.2 for limitations on use.

**Table E.9 — Pressure/temperature (P/T) ratings for flanges made using group 1A5 materials**

Temperature (°C)	Maximum non-shock working pressure (bar)					
	PN 20	PN 50	PN 110	PN 150	PN 260	PN 420
-29 to 38	18,4	47,9	95,8	143,6	239,4	399
50	18,3	47,6	95,3	142,9	238,2	397,1
100	17,7	46,6	93,2	139,8	233	388,3
150	15,8	45	89,9	134,9	224,8	374,6
200	14	44,2	88,4	132,6	221	368,3
250	12,1	43,1	86,2	129,2	215,4	359
300	10,2	42	84,1	126,1	210,1	350,2
350	8,4	40,2	80,5	120,7	201,2	335,3
375	7,4	38,8	77,6	116,4	194	323,4
400	6,5	36,6	73,2	109,8	182,9	304,9
425	5,6	35,1	70,2	105,3	175,5	292,5
450	4,7	33,8	67,6	101,4	169	218,7
475	3,7	31,7	63,3	95	158,3	263,8
500	2,8	24,1	48,1	72,2	120,3	200,6
525	1,9	15	30,1	45,1	75,2	125,4
540	1,3	10,7	21,4	32,1	53,5	89,2

NOTE — Consult table D.2 and the notes to table D.2 for limitations on use.

**Table E.10 — Pressure/temperature (P/T) ratings for flanges made using group 1A7 materials**

Temperature (°C)	Maximum non-shock working pressure (bar)					
	PN 20	PN 50	PN 110	PN 150	PN 260	PN 420
-29 to 38	20	51,7	103,4	155,2	258,6	431
50	19,2	51,7	103,4	155,2	258,6	431
100	17,7	51,5	103,1	154,6	257,7	429,5
150	15,8	50,2	100,4	150,6	251	418,3
200	14	48,8	97,6	146,4	243,9	406,6
250	12,1	46,3	92,7	139	231,7	386,1
300	10,2	42,4	84,9	127,3	212,1	353,5
350	8,4	40,2	80,5	120,7	201,2	335,3
375	7,4	38,8	77,6	116,4	194	323,4
400	6,5	36,6	73,2	109,8	182,9	304,9
425	5,6	35,1	70,2	105,3	175,5	292,5
450	4,7	33,8	67,6	101,4	169	281,7
475	3,7	31,7	63,3	95	158,3	263,8
500	2,8	27,1	54,1	81,2	135,3	225,4
525	1,9	18,8	37,6	56,4	94	156,6
550	1,3 <sup>1)</sup>	13,9	27,9	41,8	69,7	116,1
575	—	12,4	24,9	37,3	62,2	103,7

1) The maximum non-shock working pressure is 1,3 bar at 540°C for PN 20.

NOTE — Consult table D.2 and the notes to table D.2 for limitations on use.

**Table E.11 — Pressure/temperature (P/T) ratings for flanges made using group 1A9 materials**

Temperature (°C)	Maximum non-shock working pressure (bar)					
	PN 20	PN 50	PN 110	PN 150	PN 260	PN 420
-29 to 38	20	51,7	103,4	155,2	258,6	431
50	19,2	51,1	102,3	153,4	255,7	426,2
100	17,7	48,8	97,5	146,3	243,8	406,4
150	15,8	46,4	92,7	139,1	231,9	386,4
200	14	45,5	91	136,4	227,4	379
250	12,1	44,5	88,9	133,4	222,3	370,6
300	10,2	42,4	84,9	127,3	212,1	353,5
350	8,4	40,2	80,5	120,7	201,2	335,3
375	7,4	38,8	77,6	116,4	194	323,4
400	6,5	36,6	73,2	109,8	182,9	304,9
425	5,6	35,1	70,2	105,3	175,5	292,5
450	4,7	33,8	67,6	101,4	169	281,7
475	3,7	31,7	63,3	95	158,3	263,8
500	2,8	27,8	55,6	83,4	139	231,6
525	1,9	20,3	40,5	60,8	101,3	168,9
550	1,3 <sup>1)</sup>	12,8	25,5	38,3	63,8	106,4
575	—	8,5	17	25,5	42,5	70,8
600	—	5,9	11,8	17,6	29,4	49
625	—	3,4	6,8	10,1	16,9	28,2
650	—	2,3	4,6	7	11,6	19,3

1) The maximum non-shock working pressure is 1,3 bar at 540°C for PN 20.

NOTE — Consult table D.2 and the notes to table D.2 for limitations on use.

**Table E.12 — Pressure/temperature (P/T) ratings for flanges made using group 1A10 materials**

Temperature (°C)	Maximum non-shock working pressure (bar)					
	PN 20	PN 50	PN 110	PN 150	PN 260	PN 420
-29 to 38	20	51,7	103,4	155,2	258,6	431
50	19,2	51,2	102,4	153,6	256	426,7
100	17,7	49	98,1	147,1	245,2	408,7
150	15,8	46,6	93,3	139,9	233,2	388,6
200	14	44,8	89,7	134,5	224,2	373,7
250	12,1	44,2	88,4	132,7	221,1	368,5
300	10,2	42,4	84,9	127,3	212,1	353,5
350	8,4	40,2	80,5	120,7	201,2	335,3
375	7,4	38,8	77,6	116,4	194	323,4
400	6,5	36,6	73,2	109,8	182,9	304,9
425	5,6	35,1	70,2	105,3	175,5	292,5
450	4,7	33,8	67,6	101,4	169	281,7
475	3,7	31,7	63,3	95	158,3	263,8
500	2,8	27,8	55,6	83,4	139	231,6
525	1,9	21,9	43,8	65,8	109,6	182,7
550	1,3 <sup>1)</sup>	16,4	32,7	49,1	81,8	136,4
575	—	11,7	23,4	35,1	58,5	97,5
600	—	7,6	15,3	22,9	38,2	63,6
625	—	6,6	13,3	19,9	33,2	55,3
650	—	3,7	7,3	11	18,3	30,4

1) The maximum non-shock working pressure is 1,3 bar at 540°C for PN 20.

**Table E.13 — Pressure/temperature (P/T) ratings for flanges made using group 1A13 materials**

Temperature (°C)	Maximum non-shock working pressure (bar)					
	PN 20	PN 50	PN 110	PN 150	PN 260	PN 420
-29 to 38	20	51,7	103,4	155,2	258,6	431
50	19,2	51,7	103,4	155,2	258,6	431
100	17,7	51,5	103,1	154,6	257,7	429,5
150	15,8	50,2	100,4	150,6	251	418,3
200	14	48,8	97,6	146,4	243,9	406,6
250	12,1	46,3	92,7	139	231,7	386,1
300	10,2	42,4	84,9	127,3	212,1	353,5
350	8,4	40,2	80,5	120,7	201,2	335,3
375	7,4	38,8	77,6	116,4	194	323,4
400	6,5	36,6	73,2	109,8	182,9	304,9
425	5,6	34,5	69	103,5	172,5	287,5
450	4,7	30,9	61,8	92,7	154,5	257,6
475	3,7	25,9	51,8	77,7	129,5	215,8
500	2,8	20,3	40,5	60,8	101,3	168,9
525	1,9	15,4	30,8	46,3	77,1	128,5
550	1,3 <sup>1)</sup>	11,7	23,4	35	58,4	97,3
575	—	8,8	17,6	26,4	44,1	73,4
600	—	6,5	13,1	19,6	32,6	54,4
625	—	4,5	9	13,5	22,5	37,5
650	—	3	6	9	15	25,1

1) The maximum non-shock working pressure is 1,3 bar at 540°C for PN 20.

**Table E.14 — Pressure/temperature (P/T) ratings for flanges made using group 1A14 materials**

Temperature (°C)	Maximum non-shock working pressure (bar)					
	PN 20	PN 50	PN 110	PN 150	PN 260	PN 420
-29 to 38	20	51,7	103,4	155,2	258,6	431
50	19,2	51,7	103,4	155,2	258,6	431
100	17,7	51,5	103,1	154,6	257,7	429,5
150	15,8	50,2	100,4	150,6	251	418,3
200	14	48,8	97,6	146,4	243,9	406,6
250	12,1	46,3	92,7	139	231,7	386,1
300	10,2	42,4	84,9	127,3	212,1	353,5
350	8,4	40,2	80,5	120,7	201,2	335,3
375	7,4	38,8	77,6	116,4	194	323,4
400	6,5	36,6	73,2	109,8	182,9	304,9
425	5,6	35,1	70,2	105,3	175,5	292,5
450	4,7	33,8	67,6	101,4	169	281,7
475	3,7	31,7	63,3	95	158,3	263,8
500	2,8	27,5	55	82,5	137,5	229,1
525	1,9	22,6	45,2	67,8	113	188,3
550	1,3 <sup>1)</sup>	17	34	50,9	84,9	141,5
575	—	11,2	22,5	33,7	56,2	93,6
600	—	7,2	14,4	21,5	35,9	59,8
625	—	5	9,9	14,9	24,9	41,4
650	—	3,5	7	10,4	17,4	29

1) The maximum non-shock working pressure is 1,3 bar at 540°C for PN 20.

NOTE — Consult table D.2 and the notes to table D.2 for limitations on use.

**Table E.15 — Pressure/temperature (P/T) ratings for flanges made using group 2A1 materials**

Temperature (°C)	Maximum non-shock working pressure (bar)					
	PN 20	PN 50	PN 110	PN 150	PN 260	PN 420
-29 to 38	19	49,6	99,3	148,9	248,2	413,6
50	18,4	47,8	95,7	143,5	239,2	398,6
100	15,7	40,9	81,8	122,6	204,4	340,7
150	13,9	36,3	72,7	109	181,7	302,8
200	12,6	32,8	65,5	98,3	163,8	273
250	11,7	30,5	61,1	91,6	152,7	254,5
300	10,2	29,1	58,1	87,2	145,3	242,1
350	8,4	28,1	56,1	84,2	140,3	233,8
375	7,4	27,8	55,5	83,3	138,8	231,3
400	6,5	27,5	54,9	82,4	137,3	228,9
425	5,6	27,2	54,3	81,5	135,8	226,4
450	4,7	26,9	53,7	80,6	134,3	223,9
475	3,7	26,6	53,1	79,7	132,8	221,4
500	2,8	26,1	52,1	78,2	130,3	217,2
525	1,9	23,9	47,8	71,6	119,4	199
550	1,3 <sup>1)</sup>	21,8	43,6	65,4	109,1	181,8
575	—	20,1	40,1	60,2	100,4	167,3
600	—	16,7	33,4	50,1	83,6	139,3
625	—	13,1	26,2	39,2	65,4	109
650	—	10,5	21	31,6	52,6	87,6
675	—	7,8	15,5	23,3	38,8	64,6
700	—	6	12	17,9	29,9	49,8
725	—	4,6	9,3	13,9	23,1	38,5
750	—	3,7	7,3	11	18,3	30,4
775	—	2,8	5,6	8,4	14	23,3
800	—	2,1	4,1	6,2	10,3	17,1

1) The maximum non-shock working pressure is 1,3 bar at 540°C for PN 20.

NOTE — Consult table D.2 and the notes to table D.2 for limitations on use.

**Table E.16 — Pressure/temperature (P/T) ratings for flanges made using group 2A2 materials**

Temperature (°C)	Maximum non-shock working pressure (bar)					
	PN 20	PN 50	PN 110	PN 150	PN 260	PN 420
-29 to 38	19	49,6	99,3	148,9	248,2	413,6
50	18,4	48,1	96,3	144,4	240,6	401
100	16,2	42,2	84,4	126,6	211	351,7
150	14,8	38,5	77	115,5	192,5	320,9
200	13,7	35,7	71,3	107	178,4	297,3
250	12,1	33,4	66,8	100,2	166,9	278,2
300	10,2	31,6	63,3	94,9	158,1	263,6
350	8,4	30,4	60,8	91,3	152,1	253,8
375	7,4	29,7	59,4	89,1	148,5	247,5
400	6,5	29,1	58,2	87,3	145,6	242,6
425	5,6	28,7	57,3	86	143,3	238,9
450	4,7	28,1	56,2	84,2	140,4	234
475	3,7	27,4	54,7	82,1	136,8	228
500	2,8	26,8	53,7	80,5	134,1	223,6
525	1,9	25,8	51,6	77,4	129	214,9
550	1,3 <sup>1)</sup>	25	49,9	74,9	124,8	208
575	—	24,1	48,2	72,3	120,5	200,8
600	—	21,4	42,9	64,3	107,2	178,6
625	—	18,3	36,5	54,8	91,3	152,1
650	—	14,1	28,2	42,4	70,6	117,7
675	—	12,6	25,3	37,9	63,2	105,3
700	—	9,9	19,9	29,8	49,7	82,9
725	—	7,7	15,4	23,1	38,5	64,2
750	—	5,9	11	17,6	29,4	49
775	—	4,6	9,1	13,7	22,8	38
800	—	3,5	7	10,5	17,5	29,2

1) The maximum non-shock working pressure is 1,3 bar at 540°C for PN 20.

NOTE — Consult table D.2 and the notes to table D.2 for limitations on use.

**Table E.17 — Pressure/temperature (P/T) ratings for flanges made using group 2A3 materials**

Temperature (°C)	Maximum non-shock working pressure (bar)					
	PN 20	PN 50	PN 110	PN 150	PN 260	PN 420
-29 to 38	15,9	41,4	82,7	124,1	206,8	344,6
50	15,3	40	79,9	119,9	199,8	333
100	13,2	34,5	69	103,5	172,4	287,4
150	12	31,2	62,5	93,7	156,1	260,2
200	11	28,7	57,4	86,1	143,5	239,1
250	10,2	26,7	53,4	80,1	133,5	222,5
300	9,7	25,2	50,5	75,7	126,2	210,4
350	8,4	24	48,1	72,1	120,2	200,4
375	7,4	23,6	47,2	70,8	118	196,7
400	6,5	23,2	46,3	69,5	115,8	192,9
425	5,6	22,7	45,4	68,1	113,5	189,2
450	4,7	22,3	44,5	66,8	111,3	185,5

NOTE — Consult table D.2 and the notes to table D.2 for limitations on use.

**Table E.18 — Pressure/temperature (P/T) ratings for flanges made using group 2A4 materials**

Temperature (°C)	Maximum non-shock working pressure (bar)					
	PN 20	PN 50	PN 110	PN 150	PN 260	PN 420
-29 to 38	19	49,6	99,3	148,9	248,2	413,6
50	18,4	48	96	143,9	239,9	399,8
100	15,9	41,5	83	124,5	207,5	345,9
150	14,4	37,5	75	112,5	187,5	312,5
200	13,2	34,4	68,7	103,1	171,9	286,5
250	12,1	32,1	64,1	96,2	160,3	267,2
300	10,2	30,5	61,1	91,6	152,7	254,5
350	8,4	29,3	58,7	88	146,7	244,5
375	7,4	28,9	57,8	86,8	144,6	241
400	6,5	28,6	57,3	85,9	143,1	238,6
425	5,6	28,5	57	85,4	142,4	237,3
450	4,7	28,2	56,4	84,6	141	234,9
475	3,7	28	56	84	140,1	233,5
500	2,8	27,8	55,6	83,4	139	231,6
525	1,9	25,8	51,6	77,4	129	214,9
550	1,3 <sup>1)</sup>	25	49,9	74,9	124,8	208
575	—	22,8	45,6	68,4	113,9	189,9
600	—	19,8	39,6	59,4	99	165,1
625	—	15,8	31,6	47,4	79	131,6
650	—	12,5	25	37,4	62,4	104
675	—	9,8	19,7	29,5	49,2	81,9
700	—	7,7	15,4	23	38,4	64
725	—	6,2	12,4	18,6	31	51,6
750	—	4,8	9,6	14,4	24	40
775	—	3,8	7,5	11,3	18,8	31,3
800	—	3	6,1	9,1	15,2	25,2

1) The maximum non-shock working pressure is 1,3 bar at 540°C for PN 20.

NOTE — Consult table D.2 and the notes to table D.2 for limitations on use.

**Table E.19 — Pressure/temperature (P/T) ratings for flanges made using group 2A5 materials**

Temperature (°C)	Maximum non-shock working pressure (bar)					
	PN 20	PN 50	PN 110	PN 150	PN 260	PN 420
-29 to 38	19	49,6	99,3	148,9	248,2	413,6
50	18,5	48,4	96,8	145,1	241,9	403,2
100	16,7	43,5	86,9	130,4	217,3	362,2
150	15,5	40,5	81	121,5	202,5	337,5
200	14	38,4	76,8	115,3	192,1	320,2
250	12,1	36,2	72,4	108,6	181	301,7
300	10,2	34,4	68,9	103,3	172,2	287
350	8,4	32,9	65,8	98,7	164,5	274,2
375	7,4	32,2	64,4	96,6	161	268,4
400	6,5	31,8	63,5	95,3	158,8	264,7
425	5,6	31,5	62,9	94,4	157,3	262,2
450	4,7	30,8	61,5	92,3	153,8	256,3
475	3,7	30	60	90	150	250,1
500	2,8	27,8	55,6	83,4	139	231,6
525	1,9	25,8	51,6	77,4	129	214,9
550	1,3 <sup>1)</sup>	25	49,9	74,9	124,8	208
575	—	24,1	48,2	72,3	120,5	200,8
600	—	21,4	42,9	64,3	107,2	178,6
625	—	17,8	35,6	53,4	89	148,3
650	—	11,6	23,2	34,7	57,9	96,5
675	—	8,7	17,3	26	43,3	72,1
700	—	6,7	13,5	20,2	33,7	56,1
725	—	5,3	10,5	15,8	26,4	43,9
750	—	4	8	12,1	20,1	33,5
775	—	3,2	6,3	9,5	15,8	26,4
800	—	2,6	5,2	7,5	13,1	21,9

1) The maximum non-shock working pressure is 1,3 bar at 540°C for PN 20.

NOTE — Consult table D.2 and the notes to table D.2 for limitations on use.

**Table E.20 — Pressure/temperature (P/T) ratings for flanges made using group 2A6 materials**

Temperature (°C)	Maximum non-shock working pressure (bar)					
	PN 20	PN 50	PN 110	PN 150	PN 260	PN 420
-29 to 38	17,8	46,3	92,7	139	231,6	386,1
50	17,4	45,3	90,7	136	226,9	377,7
100	15,9	41,4	82,8	124,2	207,1	345,1
150	15	39,2	78,4	117,5	195,9	326,5
200	14	36,9	73,9	110,8	184,7	307,9
250	12,1	35,1	70,2	105,3	175,6	292,6
300	10,2	33,4	66,9	100,3	167,2	278,7
350	8,4	32	63,9	95,9	159,8	266,3
375	7,4	31,4	62,7	94,1	156,8	261,3
400	6,5	30,8	61,5	92,3	153,8	256,3
425	5,6	30	60	90	150	250,1
450	4,7	29,4	58,8	88,2	147	245
475	3,7	28,8	57,6	86,4	144	240,1
500	2,8	27,8	55,6	83,4	139	231,6
525	1,9	25,4	50,8	76,1	126,9	211,5
550	1,3 <sup>1)</sup>	21,8	43,6	65,5	109,1	181,8
575	—	18,5	37	55,5	92,4	154,1
600	—	14,5	29	43,5	72,6	121
625	—	11,4	22,8	34,3	57,1	95,2
650	—	8	16	24	40	66,7
675	—	7	14	21	34,9	58,2
700	—	5,7	11,3	17	28,3	47,2
725	—	4,4	8,8	13,2	21,9	36,6
750	—	3,4	6,8	10,2	17,1	28,4
775	—	2,6	5,1	7,7	12,8	21,4
800	—	1,9	3,8	5,8	9,6	16

1) The maximum non-shock working pressure is 1,3 bar at 540°C for PN 20.

**Table E.21 — Pressure/temperature (P/T) ratings for flanges made using group 2A7 materials**

Temperature (°C)	Maximum non-shock working pressure (bar)					
	PN 20	PN 50	PN 110	PN 150	PN 260	PN 420
-29 to 38	17,8	46,3	92,7	139	231,6	386,1
50	17,4	45,3	90,7	136	226,6	377,7
100	15,9	41,4	82,8	124,2	207,1	345,1
150	15	39,2	78,4	117,5	195,9	326,5
200	14	36,9	73,9	110,8	184,7	307,9
250	12,1	35,1	70,2	105,3	175,6	292,6
300	10,2	33,4	66,9	100,3	167,2	278,7
350	8,4	32	63,9	95,9	159,8	266,3
375	7,4	31,4	62,7	94,1	156,8	261,3
400	6,5	30,8	61,5	92,3	153,8	256,3
425	5,6	30	60	90	150	250,1
450	4,7	29,4	58,8	88,2	147	245
475	3,7	28,8	57,6	86,4	144	240,1
500	2,8	27,8	55,6	83,4	139	231,6
525	1,9	25,8	51,6	77,4	129	214,9
550	1,3 <sup>1)</sup>	23,6	47,2	70,8	118	196,7
575	—	22	43,9	65,9	109,9	183,1
600	—	19,4	38,7	58,1	96,8	161,3
625	—	16,6	33,3	49,9	83,1	138,6
650	—	14,1	28,1	42,2	70,3	117,2
675	—	11,3	22,6	33,9	56,5	94,1
700	—	8,7	17,5	26,2	43,6	72,7
725	—	6,2	12,4	18,5	30,9	51,5
750	—	4,4	8,8	13,1	21,9	36,5
775	—	3,1	6,3	9,4	15,7	26,2
800	—	2,2	4,4	6,6	10,9	18,2

1) The maximum non-shock working pressure is 1,3 bar at 540°C for PN 20.

**Table E.22 — Pressure/temperature (P/T) ratings for pipeline flanges**

Temperature (°C)	Maximum non-shock working pressure [bar (gauge)]			
	PN 20	PN 50	PN 110	PN 150
-30 to 120	19,6	51,1	102,1	153,2
150	19	49,3	98,6	147,9
175	18,3	47,6	95,1	142,7
200	17,6	45,9	91,7	137,9
230	17	44,1	88,6	132,7

## Annex F (informative)

### Design criteria (pipeline applications)

**F.1** For PN 50, PN 110 and PN 150 flanges, the slope and the outside diameter of the hub at the base are designed for welding ends having the same yield strength and thickness as those of the mating pipe. The wall thickness of the intended mating pipe was based on API 5LX-52 with a 0,68 design factor for the DN 650 to DN 900 sizes, and API 5LX-65 with a 0,72 design factor for the DN 950 to DN 1 500 sizes. When the manufacturer of the DN 650 to DN 900 sizes elects to utilize the alternative permitted in 2.4.5.1.2 or when the mating pipe has a minimum specified yield strength exceeding 448 N/mm<sup>2</sup>, it will be necessary to recalculate the design in accordance with the requirements of 2.4.5.1.2.

**F.2** The design of the DN 950 and larger sizes of the PN 50 and higher class of welding neck flanges is

based on the flange material having a minimum specified yield strength of at least 290 N/mm<sup>2</sup> in a ring section of the flange and a minimum yield strength at the welding end at least equal to that specified for the mating pipe. When the yield strength of the welding end of the flange is less than specified, compensation in accordance with 2.4.5.1.2 may be made, but the hub slope and diameter at the larger end have to be preserved.

**F.3** The design of all sizes is based on the use of heat-treated carbon steel bolt studs for PN 20 flanges and alloy steel bolt studs for PN 50, PN 110 and PN 150 flanges.

**Annex G**  
(informative)  
**Bibliography**

- [1] ISO 468: 1982, *Surface roughness — Parameters, their values and general rules for specifying requirements.*
- [2] ANSI/ASME B16.5: 1988, *Pipe flanges and flanged fittings.*
- [3] ANSI/ASME B36.10M: 1985, *Welded and seamless wrought steel pipe.*
- [4] API 5LX-52, *Specification for high-test line pipe.*
- [5] API 5LX-65, *Specification for high-test line pipe.*
- [6] MSS SP44, *Steel pipe line flanges.*

This page has been left intentionally blank.